

Anisotropic Ionic Conductivity in Fluorinated Ionic Liquid Crystals Suitable for Optoelectronic Applications

Antonio Abate^{1,2*}, Annamaria Petrozza³, Gabriella Cavallo^{1,3}, Guglielmo Lanzani^{3,4},
Francesco Matteucci⁵, Duncan W. Bruce⁶, Nikolay Houbenov⁷, Pierangelo Metrangolo^{1,3*}
and Giuseppe Resnati^{1,3*}

¹*NFMLab – D.C.M.I.C. “Giulio Natta”, Politecnico di Milano, Via L. Mancinelli 7, 20131
Milano, Italy*

²*Clarendon Laboratory, Department of Physics, University of Oxford, Parks Road, Oxford,
OX1 3PU, United Kingdom*

³*Center for Nano Science and Technology@PoliMi, Istituto Italiano di Tecnologia, Via
Pascoli 70/3, 20133 Milano, Italy*

⁴*Dipartimento di Fisica, Politecnico di Milano, Piazza L. da Vinci 32, 20133 Milano, Italy*

⁵*TRE Tozzi Renewable Energy SpA, I-48010 Mezzano, RA, Italy*

⁶*Department of Chemistry, University of York, Heslington, YORK YO10 5DD, UK*

⁷*Molecular Materials, Department of Applied Physics, Aalto University, School of Science,
P.O. Box 15100, FI-02015 Espoo, Finland*

[*] Corresponding authors: Tel.: +441865272354 (A.A.), +390223993041 (P.M.), 3032
(G.R.); Fax: +390223993180.

E-mail addresses: a.abate1@physics.ox.ac.uk, pierangelo.metrangolo@polimi.it,
giuseppe.resnati@polimi.it.

Supplementary Information


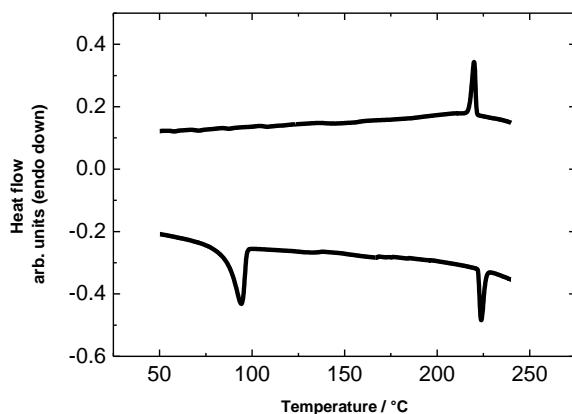


Figure S1. Differential scanning calorimetry trace of $R_{H7}ImC_2R_{F6}$ showing that FILCs have a strong tendency to supercool on cooling. The same trend was observed for the other FILCs by heating-stage polarising optical microscopy.

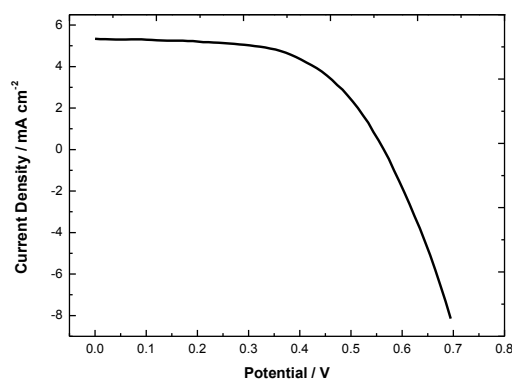

V_{oc} (V)	J_{sc} (mA cm ⁻²)	FF	η (%)
0.59	5.4	0.58	1.72

Figure S2: Photocurrent-voltage curve for a DSSC employing $R_{H8}ImC_3R_{F6}$ as electrolyte, under standard illumination conditions (AM 1.5, 100 mW cm⁻²). In the table below the figure, the device merit parameters: open circuit voltage (V_{oc}), short circuit current (J_{sc}), fill factor (FF) and efficiency (η).

Dye sensitized solar cell preparation: Prepared DSSCs consist of a conducting glass substrate (F-doped SnO₂) that was covered with a dense 500 nm TiO₂ layer, deposited by spray pyrolysis. On top of this layer, a nanoporous TiO₂ film was produced by doctor-blading a paste containing 50 nm anatase particles. After subsequent annealing to 250 °C a second layer of scattering TiO₂ film was formed containing 350/450 nm anatase particles. The resulting photoelectrodes of 15 μm thickness, were gradually heated up to 450 °C in air and subsequently sintered at that temperature for 10 min. The substrates were immersed in 0.04 M TiCl₄ solution for 30 min at 70 °C followed by calcination at 450 °C for 30 min. When the temperature decreased to 40 °C, the electrodes were immersed into a di-tetrabutylammonium *cis*-bis(isothiocyanato)bis(2,2'-bipyridyl-4,4'-dicarboxylato)ruthenium(II) (N719) dye solution (0.4 mM in acetonitrile and *tert*-butanol in volume ratio 1:1) for 16 hours. After the soaking of the dye solution, the electrodes were rinsed in acetonitrile. The devices were assembled with thermally platinized TCO as counter electrode, using a thermoplastic frame (Surllyn 25 μm thick). The prepared FILC electrolyte with iodine (0.25 eq), guanidinium thiocyanate (0.15 eq.) and *tert*-butylpyridine (0.8 eq.), was infiltrated by heating the prepared mixture at 70 °C.

^1H NMR (CDCl_3 , 500 MHz)


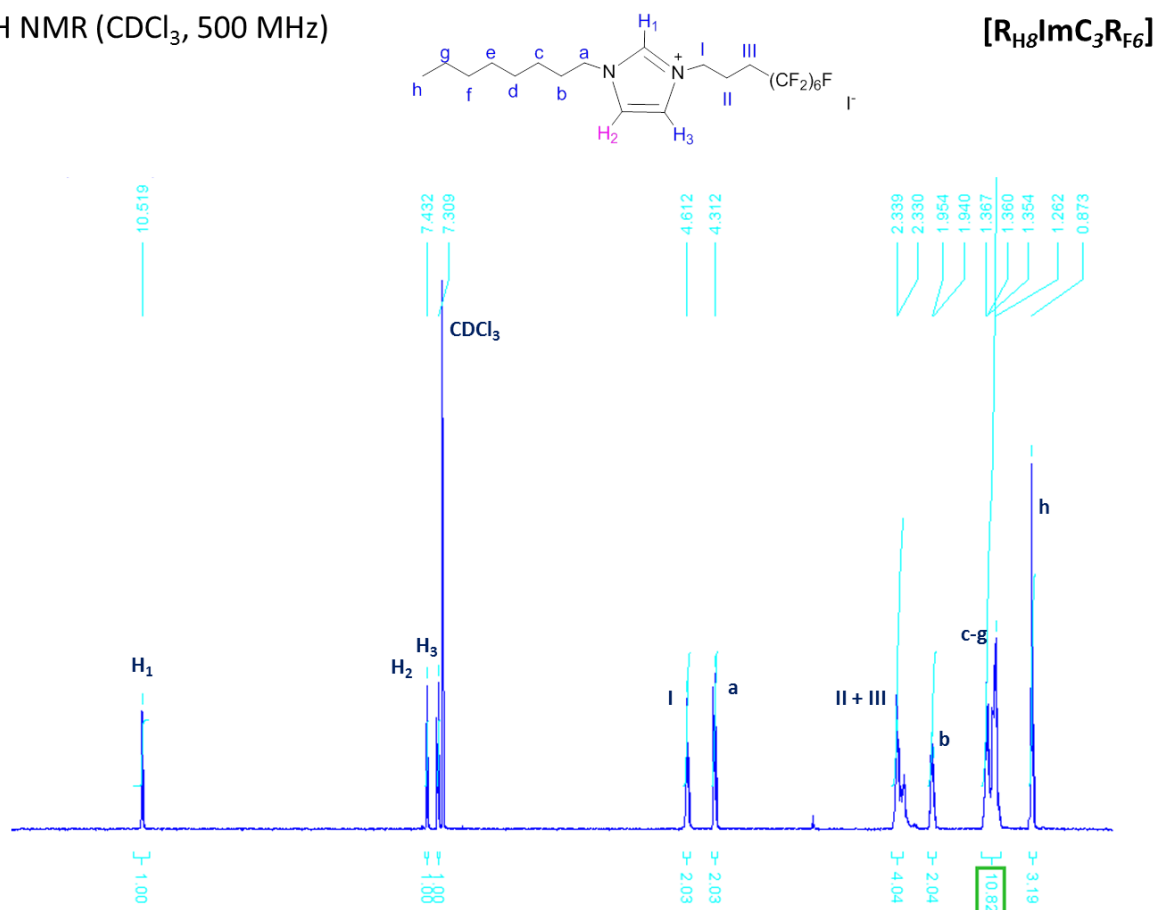


Figure S3: ^1H NMR spectrum of $\text{R}_{\text{H}8}\text{ImC}_3\text{R}_{\text{F}6}$.

^{19}F NMR (CDCl_3 , 500 MHz)

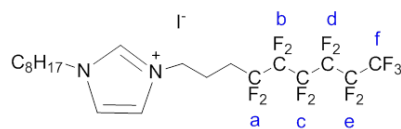

$[\text{R}_{\text{H}8}\text{ImC}_3\text{R}_{\text{F}6}]$

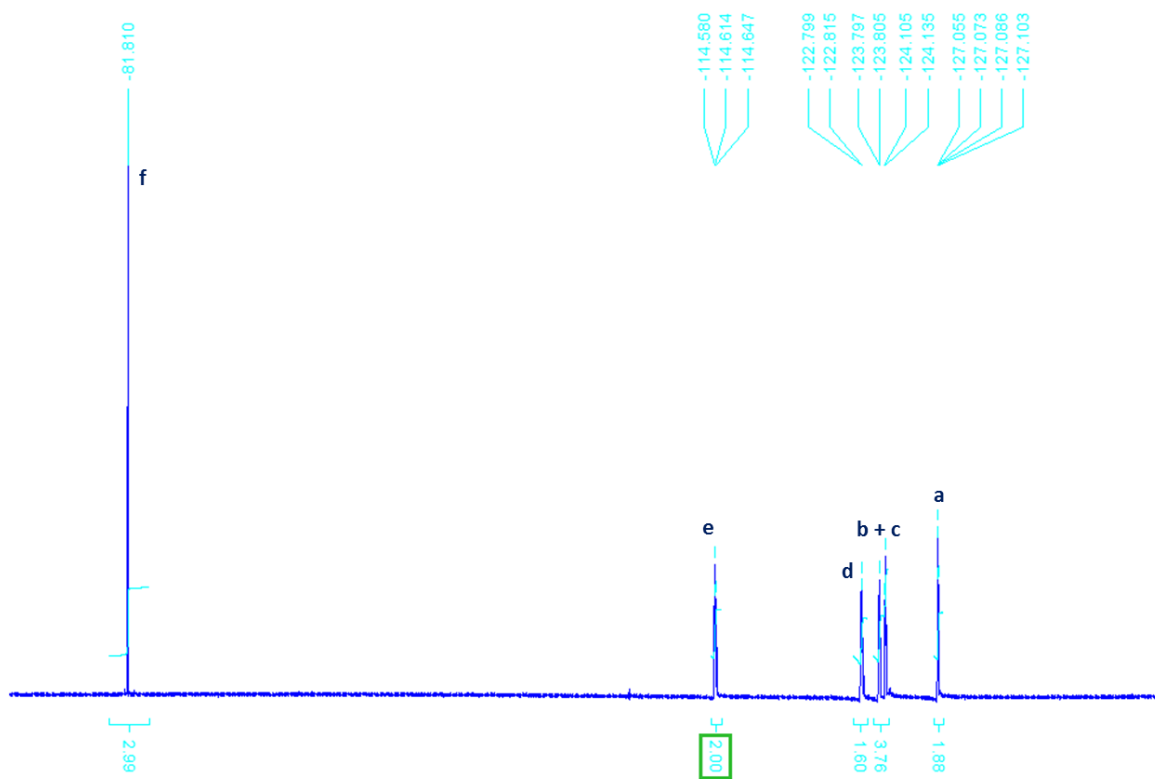


Figure S4: ^{19}F NMR spectrum of $\text{R}_{\text{H}8}\text{ImC}_3\text{R}_{\text{F}6}$.