

SUPPLEMENTARY INFORMATION

Theoretical insights into the nature of synergistic enhancement in bimetallic CoTiAlPO-5 catalysts for ammonia activation

Matthew E. Potter,^{a*} Kit McColl,^b Furio Corà,^b Alan B. Levy^c and Robert Raja^a

^a Department of Chemistry, University of Southampton, Department of Chemistry, University Road, Southampton, Hants, SO17 1BJ, UK.

^b Department of Chemistry, University College London, 20 Gordon Street, London, WC1H 0AJ, UK.

^c Honeywell Int, 101 Columbia Road, Morristown, NJ 07962, USA.

Contents

Calculated equilibrium geometries of mono- and bi-metallic catalysts	Page S2
Calculated equilibrium geometries of bound monometallic catalysts	Page S4
Calculated equilibrium geometries of bound bimetallic catalysts	Page S7
DFT calculated NH ₃ coordination geometries	Page S8
Non catalytic N-H activation energy profile	Page S9
Hydrogen abstraction step	Page S10
Evolution of spin	Page S10
Evolution of bond lengths	Page S11
Oxygen addition step	Page S12
Evolution of bond lengths	Page S12
Evolution of spin	Page S13
Transition state vibrational frequency calculations	Page S14
Monometallic hydrogen abstraction transition state	Page S14
Bimetallic hydrogen abstraction transition state	Page S15
Monometallic oxygen addition transition state	Page S16
Bimetallic oxygen addition transition state	Page S17
Transition state figures	Page S19
Complete energetics	Page S21
Electronic energy + dispersion	Page S21
Free energy	Page S21
Free energy + dispersion	Page S22

Calculated equilibrium geometries of mono- and bi-metallic catalysts

Monometallic Co(II)AlPO-5

Table S1: Bond lengths in monometallic Co(II)AlPO-5.

Atom 1	Atom 2	Bond length/Å
Co1	O1 (H1)	2.120
Co1	O2	1.871
Co1	O3	1.897
Co1	O4	1.876
O1 (H1)	P1 (H1)	1.608
O2	P2	1.518
O3	P3	1.520
O4	P4	1.524
O1	H1	0.992

Monometallic Co(III)AlPO-5

Table S2: Bond lengths in monometallic Co(III)AlPO-5.

Atom 1	Atom 2	Bond length/Å
Co1	O1	1.816
Co1	O2	1.820
Co1	O3	1.837
Co1	O4	1.822
O1	P1	1.548
O2	P2	1.545
O3	P3	1.541
O4	P4	1.546

Monometallic Ti(IV)AlPO-5

Table S3: Bond lengths in monometallic Ti(IV)AlPO-5.

Atom 1	Atom 2	Bond length/Å
Ti1	O1 (H1)	1.987
Ti1	O2	1.775
Ti1	O3	1.765
Ti1	O4	1.751
O1 (H1)	Al1 (H1)	1.792
O2	Al2	1.700
O3	Al3	1.711
O4	Al4	1.751
O1	H1	0.970

Bimetallic Co(II)Ti(IV)AlPO-5**Table S4:** Bond lengths in bimetallic Co(II)Ti(IV)AlPO-5.

Atom 1	Atom 2	Bond length/Å
Co1	O1 (H1) (Bridge)	1.973
Co1	O2	1.909
Co1	O3	1.782
Co1	O4	2.005
Ti1	O1 (H1) (Bridge)	1.961
Ti1	O5 (H2)	1.983
Ti1	O6	1.731
Ti1	O7	1.719
O2	P1	1.514
O3	P2	1.519
O4	P3	1.540
O5 (H2)	Al1 (H2)	1.801
O6	Al2	1.703
O7	Al3	1.731
O1 (H1) (Bridge)	H1	0.973
O5 (H2)	H2	0.982

Bimetallic Co(III)Ti(IV)AlPO-5**Table S5:** Bond lengths in bimetallic Co(III)Ti(IV)AlPO-5.

Atom 1	Atom 2	Bond length/Å
Co1	O1 (Bridge)	1.757
Co1	O2	1.860
Co1	O3	1.743
Co1	O4	1.931
Ti1	O1 (Bridge)	1.928
Ti1	O5 (H1)	1.988
Ti1	O6	1.744
Ti1	O7	1.768
O2	P1	1.534
O3	P2	1.534
O4	P3	1.557
O5 (H1)	Al1 (H1)	1.805
O6	Al2	1.665
O7	Al3	1.726
O5 (H1)	H1	0.975

Calculated equilibrium geometries of bound monometallic catalysts

Table S6: Bond lengths in monometallic Co(II)AlPO-5 bound to O₂.

Atom 1	Atom 2	Bond length/Å
Co1	O1 (H)	2.120
Co1	O2	1.881
Co1	O3	1.900
Co1	O4	1.876
O1 (H)	P1 (H)	1.608
O2	P2	1.517
O3	P3	1.519
O4	P4	1.518
O1 (H)	H1	0.992
Co1	O5	3.215
Co1	O6	4.135
O5	O6	1.227

Table S7: Bond lengths in monometallic Co(III)AlPO-5 bound to O₂.

Atom 1	Atom 2	Bond length/Å
Co1	O1	1.838
Co1	O2	1.826
Co1	O3	1.835
Co1	O4	1.819
O1	P1	1.541
O2	P2	1.548
O3	P3	1.540
O4	P4	1.545
Co1	O5	3.423
Co1	O6	4.097
O5	O6	1.227

Table S8: Bond lengths in monometallic Ti(IV)AlPO-5 bond to O₂.

Atom 1	Atom 2	Bond length/Å
Ti1	O1 (H)	1.995
Ti1	O2	1.760
Ti1	O3	1.768
Ti1	O4	1.751

O1 (H)	Al1 (H)	1.791
O2	Al2	1.701
O3	Al3	1.713
O4	Al4	1.711
O1 (H)	H1	0.696
Ti1	O5	3.001
Ti1	O6	3.746
O5	O5	1.227

Table S9: Bond lengths in monometallic Co(II)AlPO-5 bound to NH₃.

Atom 1	Atom 2	Bond length/Å
Co1	O1	1.814
Co1	O2	1.838
Co1	O3	1.852
Co1	O4	1.964
O1	P1	1.536
O2	P2	1.535
O3	P3	1.527
O4	P4	1.526
Co1	N1	2.208
N1	H1	1.017
N1	H2	1.017
N2	H3	1.019

Table S10: Bond lengths in monometallic Co(III)AlPO-5 bound to NH₃.

Atom 1	Atom 2	Bond length/Å
Co1	O1 (H)	2.136
Co1	O2	1.953
Co1	O3	1.981
Co1	O4	1.923
O1 (H)	P1 (H)	1.596
O2	P2	1.509
O3	P3	1.512
O4	P4	1.508
O1 (H)	H1	1.001
Co1	N1	2.215
N1	H2	1.017
N1	H3	1.018
N2	H4	1.018

Table S11: Bond lengths in monometallic Ti(IV)AlPO-5 bound to NH₃.

Atom 1	Atom 2	Bond length/Å
Ti1	O1 (H)	2.097
Ti1	O2	1.789
Ti1	O3	1.801
Ti1	O4	1.760
O1 (H)	Al1 (H)	1.759
O2	Al2	1.709
O3	Al3	1.690
O4	Al4	1.704
O1 (H)	H1	0.968
Ti1	N1	2.254
N1	H2	1.017
N1	H3	1.019
N2	H4	1.021

Calculated equilibrium geometries of bound bimetallic catalysts

Table S12: Bond lengths in bimetallic Co(III)Ti(IV)AlPO-5 with ammonia bound to the cobalt site.

Atom 1	Atom 2	Bond length/Å
Co1	O1 (Bridge)	1.733
Co1	O2	1.862
Co1	O3	1.887
Co1	O4	2.122
Ti1	O1 (Bridge)	1.745
Ti1	O5	1.747
Ti1	O6	1.806
Ti1	O7 (H1)	1.978
O2	P1	1.514
O3	P2	1.543
O4	P3	1.530
O5	Al1	1.726
O6	Al2	1.722
O7 (H1)	Al3	1.776
O7 (H1)	H1	0.969
Co1	N1	2.186
N1	H2	1.017
N1	H3	1.018
N1	H4	1.019

Table S13: Bond lengths in bimetallic Co(III)Ti(IV)AlPO-5 with ammonia bound to the titanium site.

Atom 1	Atom 2	Bond length/Å
Co1	O1 (Bridge)	1.726
Co1	O2	1.844
Co1	O3	1.871
Co1	O4	1.873
Ti1	O1	1.750
Ti1	O5	1.761
Ti1	O6	1.844
Ti1	O7 (H1)	2.008
O2	P1	1.514
O3	P2	1.543
O4	P3	1.530
O5	Al1	1.729
O6	Al2	1.722
O7 (H1)	Al3	1.776
O7 (H1)	H1	0.969
Ti1	N1	2.239
N1	H2	1.019
N1	H3	1.020
N1	H4	1.021

DFT Calculated NH₃ coordination geometries

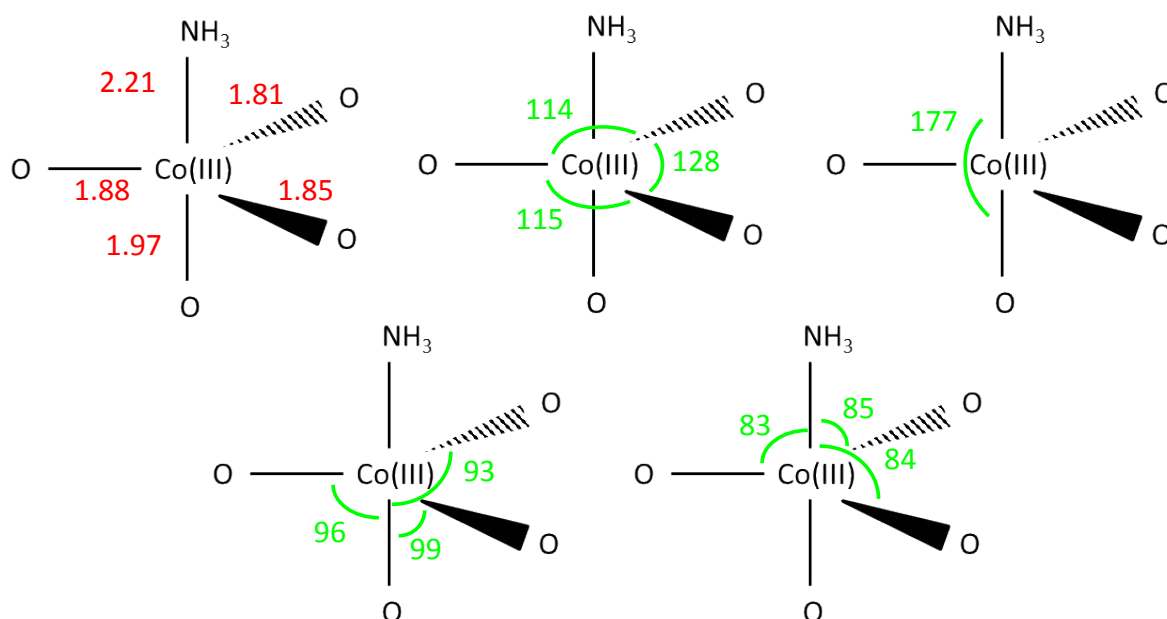


Figure S1: Geometric coordination of NH₃ to monometallic Co(III)AlPO-5 showing the trigonal bipyramidal shape. Red numbers represent lengths in angstroms, green values are angles in degrees.

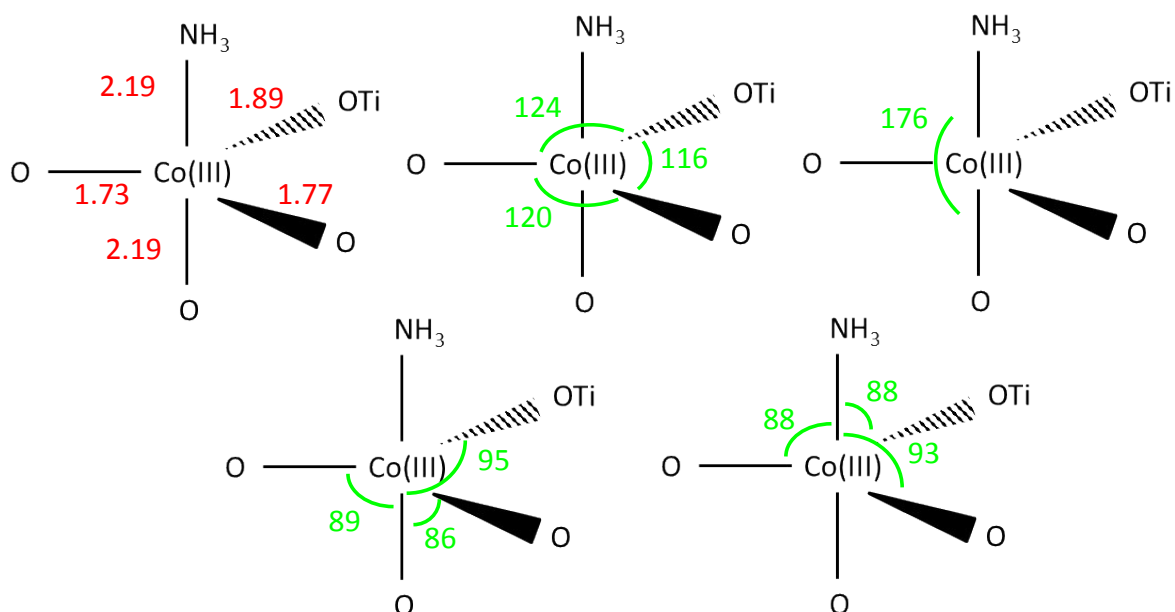


Figure S2: Geometric coordination of NH₃ to bimetallic Co(III)Ti(IV)AlPO-5 showing the trigonal bipyramidal shape. Red numbers represent lengths in angstroms, green values are angles in degrees.

Non-catalytic N-H activation energy profile

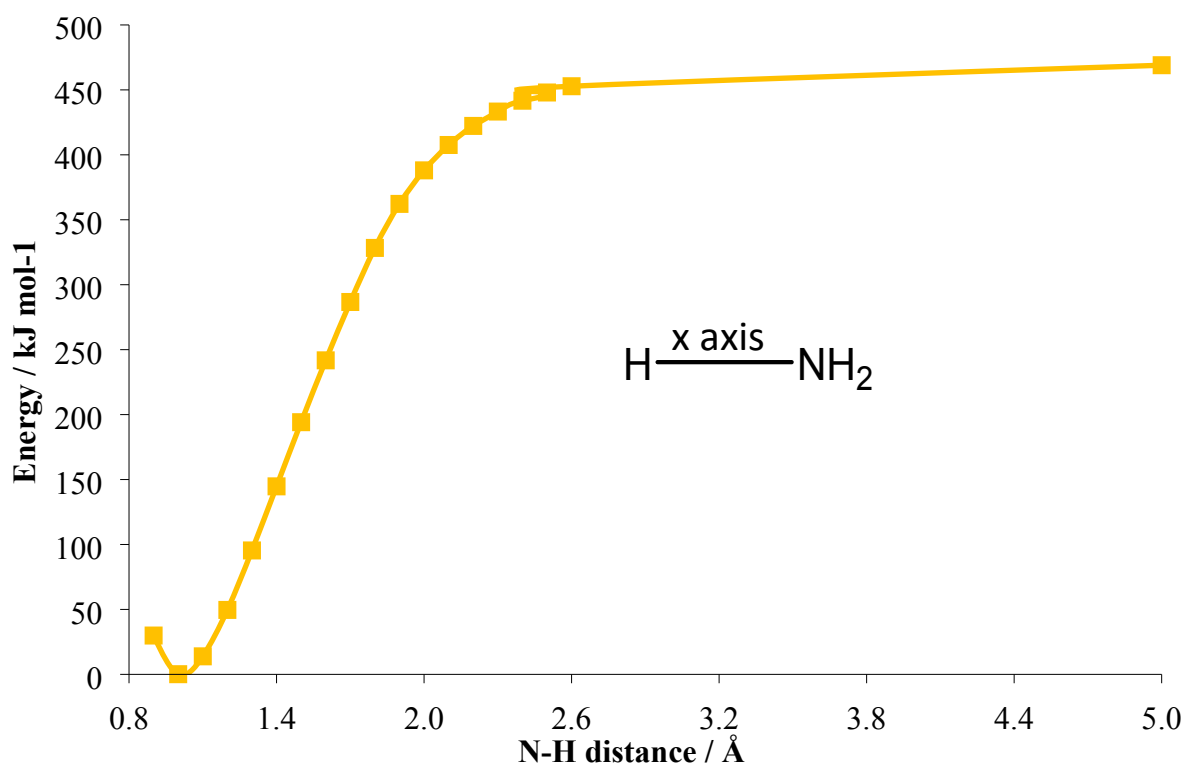


Figure S3: Energy profile showing that 470 kJ/mol is required to break the H—NH₂ bond non-catalytically.

Hydrogen abstraction step

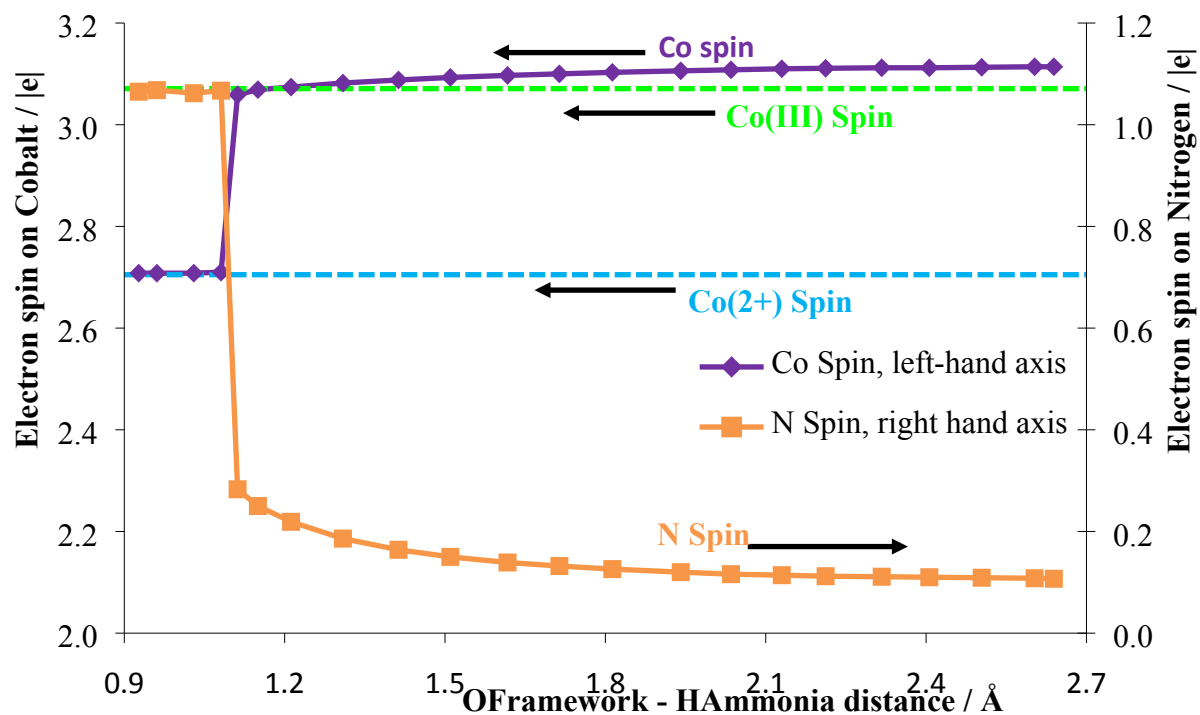


Figure S4: Spin evolution of monometallic CoAlPO-5 for the activation of ammonia.

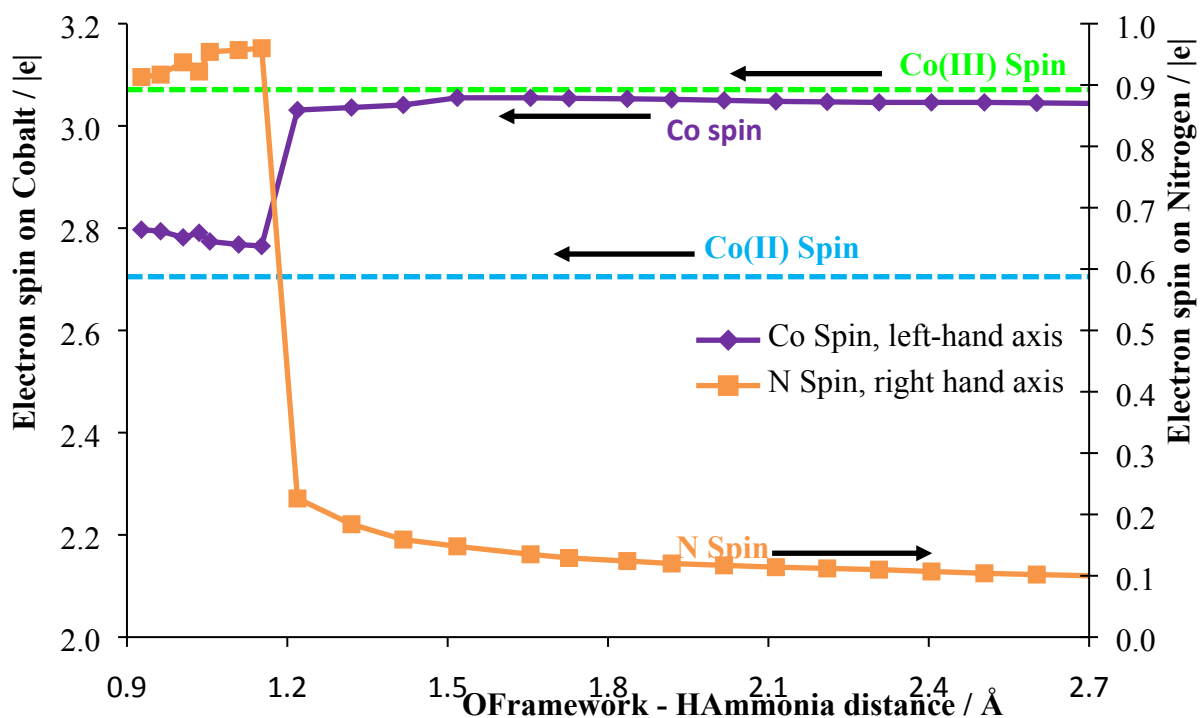


Figure S5: Spin evolution of bimetallic CoTiAlPO-5 for the activation of ammonia.

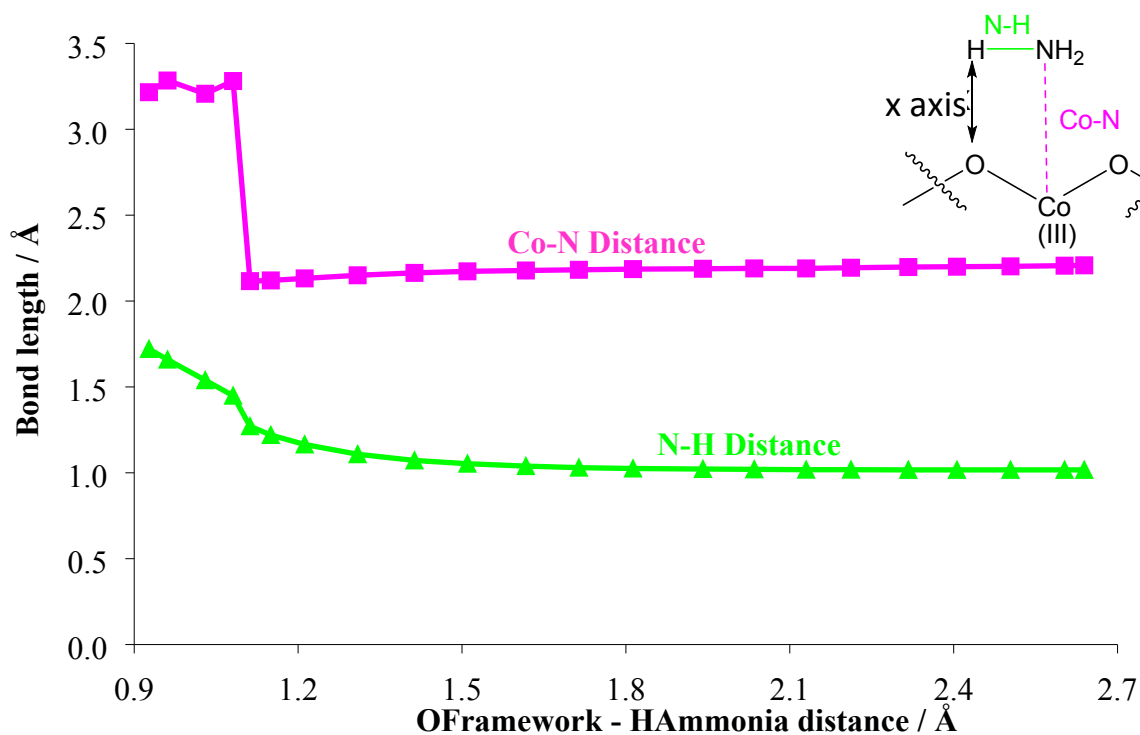


Figure S6: The evolution of bond lengths in the monometallic CoAlPO-5 system for the initial ammonia activation step.

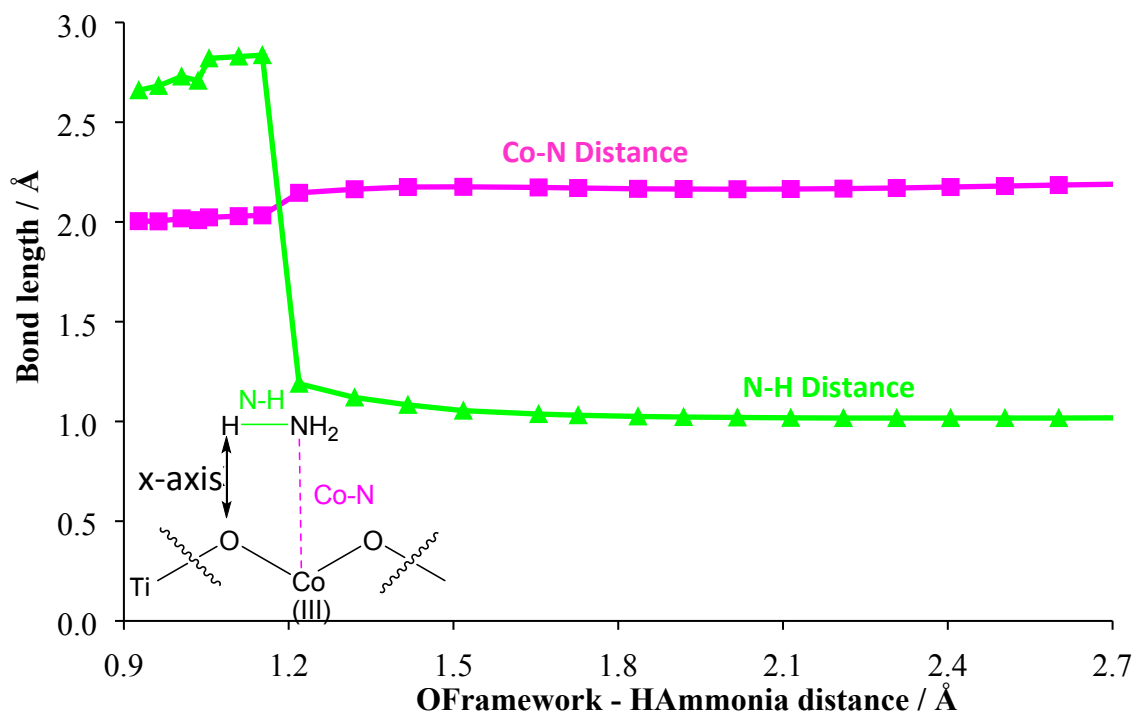


Figure S7: The evolution of bond lengths in the bimetallic CoTiAlPO-5 system for the initial ammonia activation step.

Oxygen addition step

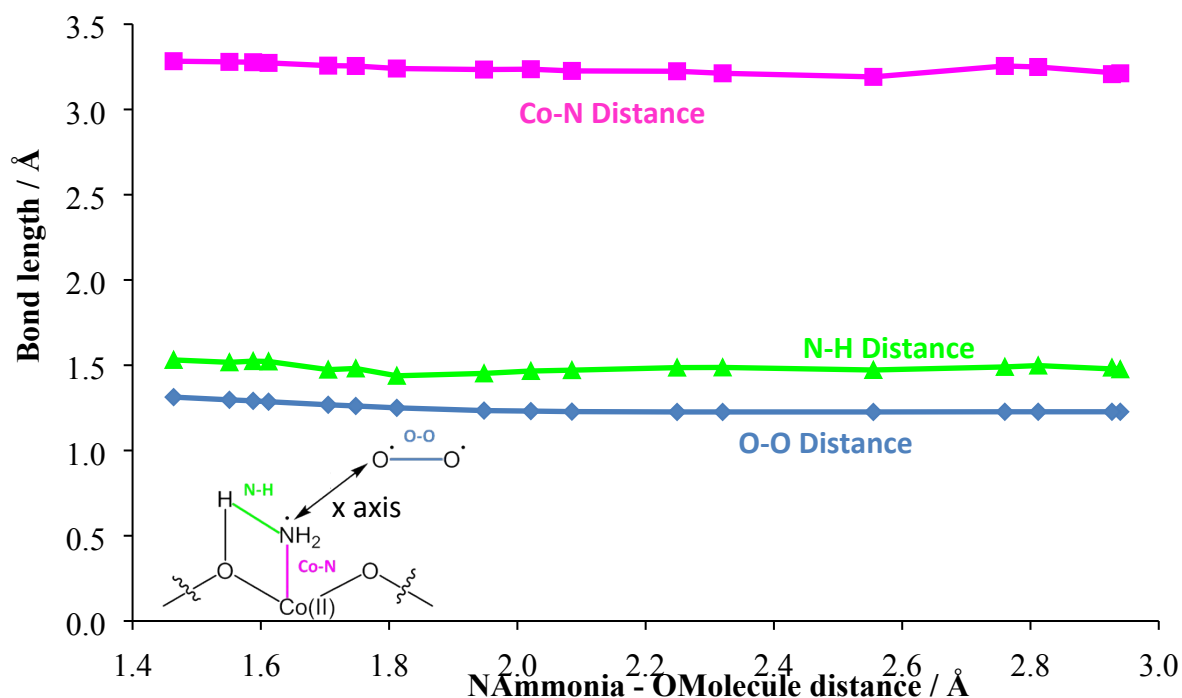


Figure S8: The evolution of bond lengths in the monometallic CoAlPO-5 system for the NH₂OO formation step.

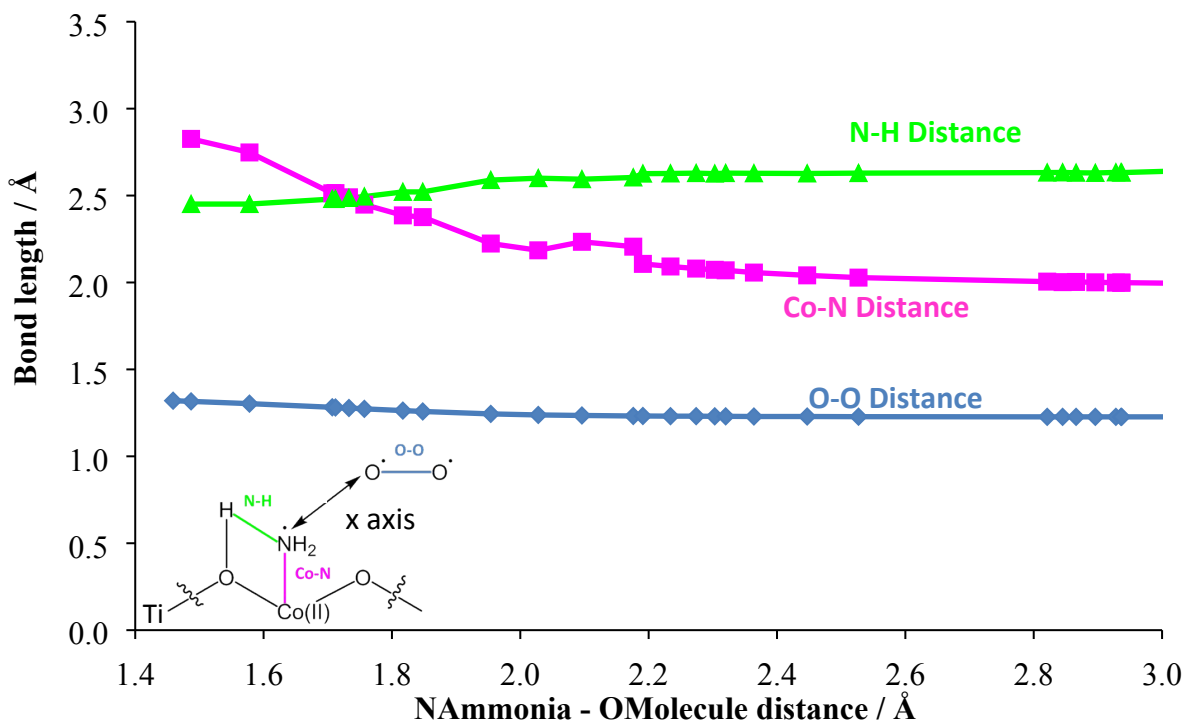


Figure S9: The evolution of bond lengths in the bimetallic CoTiAlPO-5 system for the NH₂OO formation step.

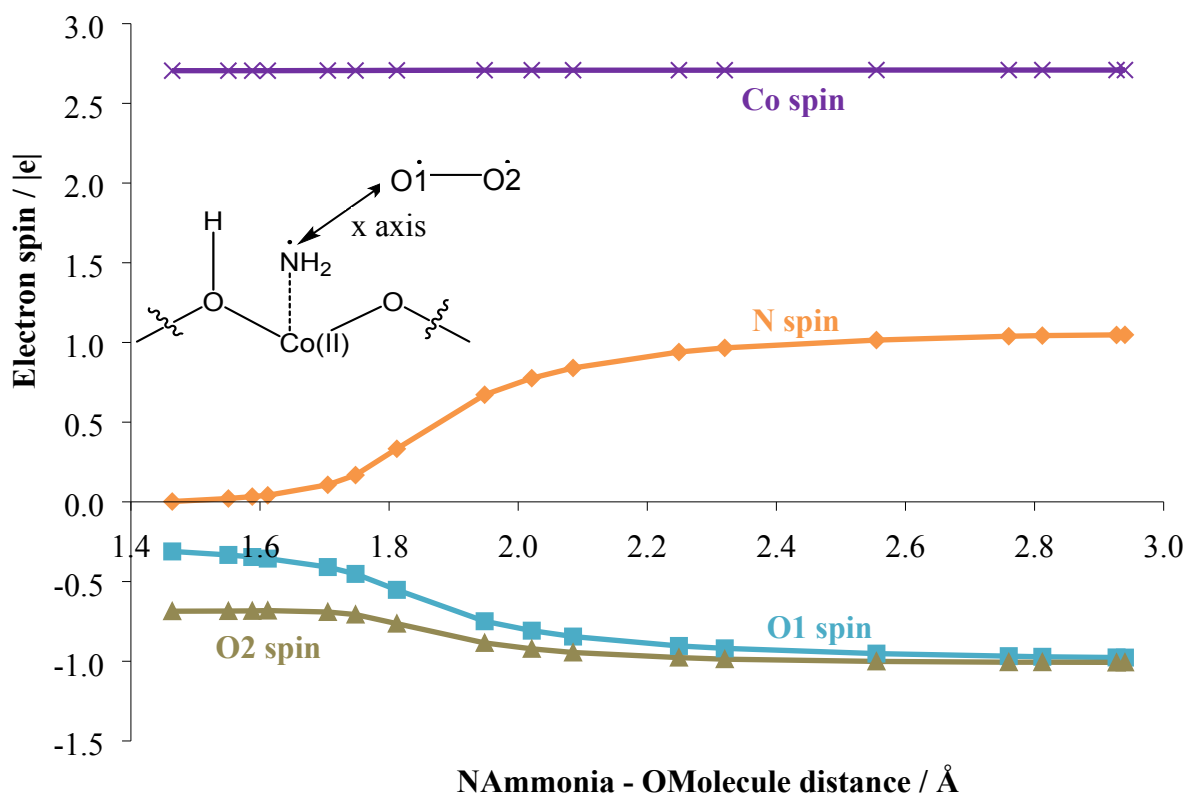


Figure S10: The evolution of spin in the monometallic CoAlPO-5 system for the formation of the NH₂OO radical species.

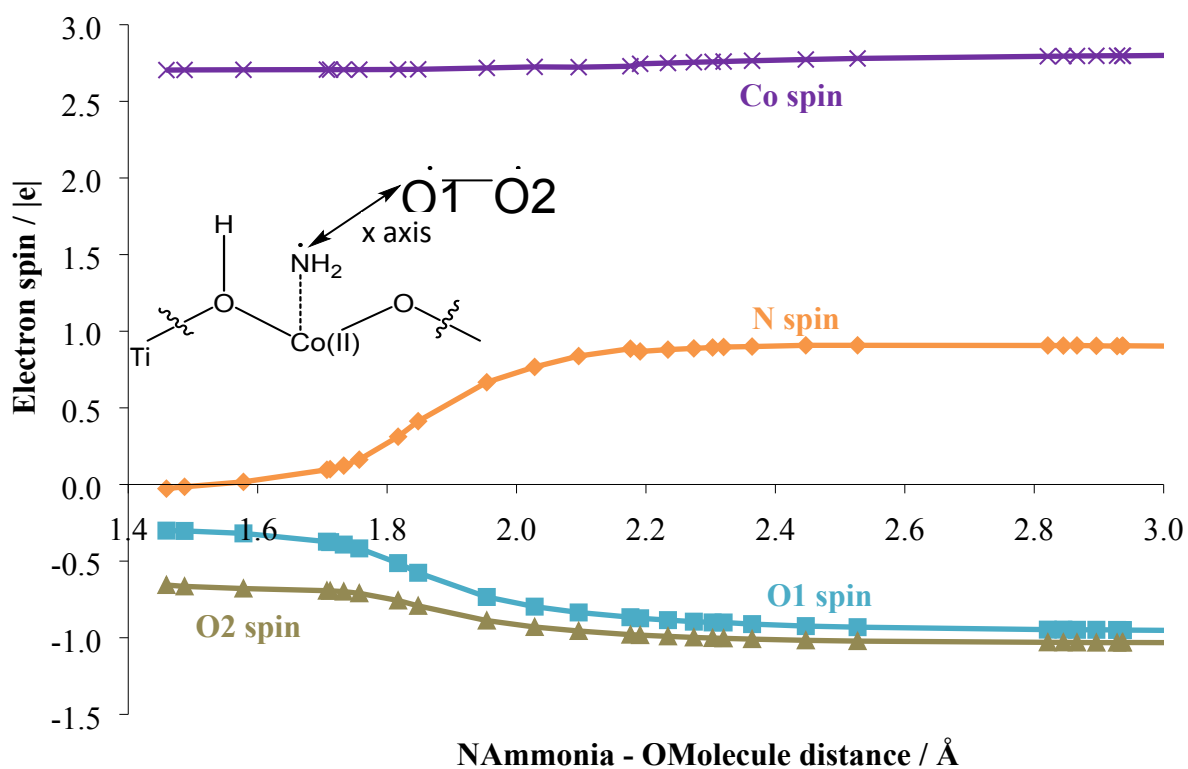


Figure S11: The evolution of spin in the bimetallic CoTiAlPO-5 system for the formation of the NH₂OO radical species

Transition state vibrational frequency calculations reported as they appear from the CRYSTAL output

Monometallic hydrogen abstraction step

Modes	EIGV (HARTREE**2)	FREQUENCIES (CM**1)	(THZ)	IRREP	IR	INTENS (KM/MOL)	RAMAN
1- 1	-0.2263E-06	-104.4045	-3.1300	(A)	(A)	(0.00)	A
2- 2	0.3989E-16	0.0000	0.0000	(A)	(A)	(0.00)	A
3- 3	0.2222E-15	0.0000	0.0000	(A)	(A)	(0.00)	A
4- 4	0.3864E-15	0.0000	0.0000	(A)	(A)	(0.00)	A
5- 5	0.3954E-08	13.8010	0.4137	(A)	(A)	(0.00)	A
6- 6	0.8744E-07	64.8980	1.9456	(A)	(A)	(0.00)	A
7- 7	0.9419E-07	67.3592	2.0194	(A)	(A)	(0.00)	A
8- 8	0.1445E-06	83.4420	2.5015	(A)	(A)	(0.00)	A
9- 9	0.1608E-06	88.0056	2.6383	(A)	(A)	(0.00)	A
10- 10	0.1647E-06	89.0673	2.6702	(A)	(A)	(0.00)	A
11- 11	0.1759E-06	92.0465	2.7595	(A)	(A)	(0.00)	A
12- 12	0.2085E-06	100.2263	3.0047	(A)	(A)	(0.00)	A
13- 13	0.2378E-06	107.0246	3.2085	(A)	(A)	(0.00)	A
14- 14	0.2564E-06	111.1421	3.3320	(A)	(A)	(0.00)	A
15- 15	0.2806E-06	116.2594	3.4854	(A)	(A)	(0.00)	A
16- 16	0.2897E-06	118.1342	3.5416	(A)	(A)	(0.00)	A
17- 17	0.3054E-06	121.2979	3.6364	(A)	(A)	(0.00)	A
18- 18	0.3144E-06	123.0580	3.6892	(A)	(A)	(0.00)	A
19- 19	0.3273E-06	125.5572	3.7641	(A)	(A)	(0.00)	A
20- 20	0.3623E-06	132.0988	3.9602	(A)	(A)	(0.00)	A
21- 21	0.3820E-06	135.6484	4.0666	(A)	(A)	(0.00)	A
22- 22	0.3944E-06	137.8362	4.1322	(A)	(A)	(0.00)	A
23- 23	0.4226E-06	142.6684	4.2771	(A)	(A)	(0.00)	A
24- 24	0.4420E-06	145.9165	4.3745	(A)	(A)	(0.00)	A
25- 25	0.4877E-06	153.2678	4.5949	(A)	(A)	(0.00)	A
26- 26	0.5023E-06	155.5505	4.6633	(A)	(A)	(0.00)	A
27- 27	0.5248E-06	159.0003	4.7667	(A)	(A)	(0.00)	A
28- 28	0.5629E-06	164.6584	4.9363	(A)	(A)	(0.00)	A
29- 29	0.5723E-06	166.0349	4.9776	(A)	(A)	(0.00)	A
30- 30	0.5949E-06	169.2856	5.0751	(A)	(A)	(0.00)	A
31- 31	0.6228E-06	173.2041	5.1925	(A)	(A)	(0.00)	A
32- 32	0.6310E-06	174.3420	5.2266	(A)	(A)	(0.00)	A
33- 33	0.6677E-06	179.3418	5.3765	(A)	(A)	(0.00)	A
34- 34	0.6907E-06	182.3956	5.4681	(A)	(A)	(0.00)	A
35- 35	0.7045E-06	184.1846	5.5217	(A)	(A)	(0.00)	A
36- 36	0.7665E-06	192.1544	5.7606	(A)	(A)	(0.00)	A
37- 37	0.7937E-06	195.5233	5.8619	(A)	(A)	(0.00)	A
38- 38	0.8130E-06	197.8873	5.9325	(A)	(A)	(0.00)	A
39- 39	0.8274E-06	199.6357	5.9849	(A)	(A)	(0.00)	A
40- 40	0.8438E-06	201.6041	6.0439	(A)	(A)	(0.00)	A
41- 41	0.8690E-06	204.5911	6.1335	(A)	(A)	(0.00)	A
42- 42	0.9030E-06	208.5604	6.2525	(A)	(A)	(0.00)	A
43- 43	0.9256E-06	211.1515	6.3302	(A)	(A)	(0.00)	A
44- 44	0.9542E-06	214.3902	6.4273	(A)	(A)	(0.00)	A
45- 45	0.9650E-06	215.5993	6.4635	(A)	(A)	(0.00)	A
46- 46	0.1014E-05	221.0204	6.6260	(A)	(A)	(0.00)	A
47- 47	0.1027E-05	222.3889	6.6671	(A)	(A)	(0.00)	A
48- 48	0.1048E-05	224.6988	6.7363	(A)	(A)	(0.00)	A
49- 49	0.1095E-05	229.6950	6.8861	(A)	(A)	(0.00)	A
50- 50	0.1113E-05	231.5379	6.9413	(A)	(A)	(0.00)	A
51- 51	0.1153E-05	235.7121	7.0665	(A)	(A)	(0.00)	A
52- 52	0.1197E-05	240.1530	7.1996	(A)	(A)	(0.00)	A
53- 53	0.1225E-05	242.9128	7.2823	(A)	(A)	(0.00)	A
54- 54	0.1260E-05	246.3567	7.3856	(A)	(A)	(0.00)	A
55- 55	0.1294E-05	249.6375	7.4839	(A)	(A)	(0.00)	A
56- 56	0.1367E-05	256.6213	7.6933	(A)	(A)	(0.00)	A
57- 57	0.1433E-05	262.7253	7.8763	(A)	(A)	(0.00)	A
58- 58	0.1464E-05	265.5110	7.9598	(A)	(A)	(0.00)	A
59- 59	0.1481E-05	267.0562	8.0061	(A)	(A)	(0.00)	A
60- 60	0.1535E-05	271.9355	8.1524	(A)	(A)	(0.00)	A
61- 61	0.1554E-05	273.6323	8.2033	(A)	(A)	(0.00)	A
62- 62	0.1580E-05	275.9137	8.2717	(A)	(A)	(0.00)	A
63- 63	0.1623E-05	279.6203	8.3828	(A)	(A)	(0.00)	A
64- 64	0.1682E-05	284.6598	8.5339	(A)	(A)	(0.00)	A
65- 65	0.1700E-05	286.1828	8.5795	(A)	(A)	(0.00)	A
66- 66	0.1793E-05	293.8579	8.8096	(A)	(A)	(0.00)	A
67- 67	0.1932E-05	305.0999	9.1467	(A)	(A)	(0.00)	A
68- 68	0.1968E-05	307.8836	9.2301	(A)	(A)	(0.00)	A
69- 69	0.2018E-05	311.7467	9.3459	(A)	(A)	(0.00)	A
70- 70	0.2081E-05	316.6067	9.4916	(A)	(A)	(0.00)	A
71- 71	0.2104E-05	318.3263	9.5432	(A)	(A)	(0.00)	A
72- 72	0.2245E-05	328.8471	9.8586	(A)	(A)	(0.00)	A
73- 73	0.2361E-05	337.2430	10.1103	(A)	(A)	(0.00)	A
74- 74	0.2488E-05	346.2166	10.3793	(A)	(A)	(0.00)	A
75- 75	0.2497E-05	346.8343	10.3978	(A)	(A)	(0.00)	A
76- 76	0.2602E-05	354.0100	10.6130	(A)	(A)	(0.00)	A
77- 77	0.2755E-05	364.2947	10.9213	(A)	(A)	(0.00)	A
78- 78	0.2859E-05	371.0880	11.1249	(A)	(A)	(0.00)	A
79- 79	0.2936E-05	376.0546	11.2738	(A)	(A)	(0.00)	A
80- 80	0.2971E-05	378.3206	11.3418	(A)	(A)	(0.00)	A
81- 81	0.3001E-05	380.2122	11.3985	(A)	(A)	(0.00)	A
82- 82	0.3069E-05	384.4604	11.5258	(A)	(A)	(0.00)	A
83- 83	0.3108E-05	386.9123	11.5993	(A)	(A)	(0.00)	A
84- 84	0.3131E-05	388.3413	11.6422	(A)	(A)	(0.00)	A
85- 85	0.3170E-05	390.7693	11.7150	(A)	(A)	(0.00)	A
86- 86	0.3247E-05	395.5113	11.8571	(A)	(A)	(0.00)	A
87- 87	0.3349E-05	401.6331	12.0407	(A)	(A)	(0.00)	A
88- 88	0.3387E-05	403.9166	12.1091	(A)	(A)	(0.00)	A
89- 89	0.3443E-05	407.2158	12.2080	(A)	(A)	(0.00)	A
90- 90	0.3489E-05	409.9641	12.2904	(A)	(A)	(0.00)	A
91- 91	0.3530E-05	412.3655	12.3624	(A)	(A)	(0.00)	A
92- 92	0.3593E-05	416.0268	12.4722	(A)	(A)	(0.00)	A
93- 93	0.3678E-05	420.8985	12.6182	(A)	(A)	(0.00)	A
94- 94	0.3701E-05	422.2402	12.6584	(A)	(A)	(0.00)	A
95- 95	0.3736E-05	424.2245	12.7179	(A)	(A)	(0.00)	A
96- 96	0.3780E-05	426.7301	12.7930	(A)	(A)	(0.00)	A
97- 97	0.3848E-05	430.5093	12.9063	(A)	(A)	(0.00)	A
98- 98	0.3926E-05	434.8743	13.0372	(A)	(A)	(0.00)	A
99- 99	0.3948E-05	436.0965	13.0738	(A)	(A)	(0.00)	A
100- 100	0.4056E-05	442.0201	13.2514	(A)	(A)	(0.00)	A
101- 101	0.4085E-05	443.5947	13.2986	(A)	(A)	(0.00)	A
102- 102	0.4210E-05	450.3466	13.5011	(A)	(A)	(0.00)	A
103- 103	0.4321E-05	456.1998	13.6765	(A)	(A)	(0.00)	A
104- 104	0.4371E-05	458.8744	13.7567	(A)	(A)	(0.00)	A
105- 105	0.4434E-05	462.1347	13.8545	(A)	(A)	(0.00)	A
106- 106	0.4507E-05	465.9507	13.9689	(A)	(A)	(0.00)	A
107- 107	0.4534E-05	467.3300	14.0102	(A)	(A)	(0.00)	A
108- 108	0.4624E-05	471.9723	14.1494	(A)	(A)	(0.00)	A
109- 109	0.4687E-05	475.1536	14.2447	(A)	(A)	(0.00)	A
110- 110	0.4744E-05	478.0305	14.3310	(A)	(A)	(0.00)	A
111- 111	0.4837E-05	482.7013	14.4710	(A)	(A)	(0.00)	A
112- 112	0.4917E-05	486.6587	14.5897	(A)	(A)	(0.00)	A
113- 113	0.4984E-05	489.9512	14.6884	(A)	(A)	(0.00)	A
114- 114	0.5066E-05	494.0020	14.8098	(A)	(A)	(0.00)	A
115- 115	0.5163E-05	498.6894	14.9503	(A)	(A)	(0.00)	A
116- 116	0.5173E-05	499.1730	14.9648	(A)	(A)	(0.00)	A
117- 117	0.5275E-05	504.0751	15.1118	(A)	(A)	(0.00)	A
118- 118	0.5280E-05	504.3342	15.1196	(A)	(A)	(0.00)	A
119- 119	0.5344E-05	507.3850	15.2110	(A)	(A)	(0.00)	A
120- 120	0.5434E-05	511.6171	15.3379	(A)	(A)	(0.00)	A
121- 121	0.5546E-05	516.8773	15.4956	(A)	(A)	(0.00)	A
122- 122	0.5764E-05	526.9362	15.7972	(A)	(A)	(0.00)	A
123- 123	0.5870E-05	531.7645	15.9419	(A)	(A)	(0.00)	A
124- 124	0.6068E-05	540.6528	16.2084	(A)	(A)	(0.00)	A
125- 125	0.6159E-05	544.6631	16.3286	(A)	(A)	(0.00)	A
126- 126	0.6223E-05	547.5007	16.4137	(A)	(A)	(0.00)	A
127- 127	0.6457E-05	557.6860	16.7190	(A)	(A)	(0.00)	A
128- 128	0.6584E-05	563.1710	16.8834	(A)	(A)	(0.00)	A
129- 129	0.6697E-05	567.9576	17.0269	(A)	(A)	(0.00)	A
130- 130	0.6919E-05	577.3209	17.3076	(A)	(A)	(0.00)	A
131- 131	0.6940E-05	578.5703	17.3451	(A)	(A)	(0.00)	A
132- 132	0.7119E-05	585.5718	17.5550	(A)	(A)	(0.00)	A
133- 133	0.7179E-05	588.0434	17.6291	(A)	(A)	(0.00)	A
134- 134	0.7384E-05	596.4005	17.8796	(A)	(A)	(0.00)	A
135- 135	0.7469E-05	599.8206	17.9822	(A)	(A)	(0.00)	A
136- 136	0.7597E-05	604.9299	18.1353	(A)	(A)	(0.00)	A
137- 137	0.8390E-05	635.7041	19.0579	(A)	(A)	(0.00)	A
138- 138	0.8637E-05	644.9910	19.3363	(A)	(A)	(0.00)	A
139- 139	0.8992E-05	658.1197	19.7299	(A)	(A)	(0.00)	A
140- 140	0.9217E-05	666.3077	19.9754	(A)	(A)	(0.00)	A
141- 141	0.9354E-05	671.2408	20.1233	(A)	(A)	(0.00)	A
142- 142	0.9414E-05	673.4019	20.1881	(A)	(A)	(0.00)	A
143- 143	0.9565E-05	678.7936	20.3497	(A)	(A)	(0.00)	A
144- 144	0.9777E-05	686.2678	20.5738	(A)	(A)	(0.00)	A
145- 145	0.9843E-05	688.5788	20.6431	(A)	(A)	(0.00)	A
146- 146	0.1016E-04	699.5900	20.9732	(A)	(A)	(0.00)	A
147- 147	0.1045E-04	709.4631	21.2692	(A)	(A)	(0.00)	A
148- 148	0.1063E-04	715.5943	21.4530	(A)	(A)	(0.00)	A
149- 149	0.1110E-04	731.3179	21.9244	(A)	(A)	(0.00)	A
150- 150	0.1121E-04	734.9410	22.0330	(A)	(A)	(0.00)	A
151- 151	0.1130E-04						

213-	213	0.3206E-04	1242.6999	37.2552	(A)	A (	0.00)	A
214-	214	0.3252E-04	1251.4944	37.5189	(A)	A (	0.00)	A
215-	215	0.3275E-04	1255.9233	37.6516	(A)	A (	0.00)	A
216-	216	0.3278E-04	1256.5068	37.6691	(A)	A (	0.00)	A
217-	217	0.3287E-04	1258.2679	37.7219	(A)	A (	0.00)	A
218-	218	0.3325E-04	1265.4788	37.9381	(A)	A (	0.00)	A
219-	219	0.3347E-04	1269.7789	38.0670	(A)	A (	0.00)	A
220-	220	0.3375E-04	1274.9431	38.2218	(A)	A (	0.00)	A
221-	221	0.3391E-04	1278.1378	38.3176	(A)	A (	0.00)	A
222-	222	0.3427E-04	1284.7597	38.5161	(A)	A (	0.00)	A
223-	223	0.3456E-04	1290.2400	38.6804	(A)	A (	0.00)	A
224-	224	0.4318E-04	1442.2241	43.2368	(A)	A (	0.00)	A
225-	225	0.5580E-04	1639.4200	49.1486	(A)	A (	0.00)	A
226-	226	0.7061E-04	1844.2687	55.2898	(A)	A (	0.00)	A
227-	227	0.2632E-03	3560.7146	106.7475	(A)	A (	0.00)	A
228-	228	0.2798E-03	3671.3545	110.0644	(A)	A (	0.00)	A

Bimetallic hydrogen abstraction step

MODES	E1 (HARTREE*E2)	FREQUENCIES (CM-1)	(THZ)	IRREP	IR	INTENS (KM/MOL)	RAMAN
1- 1	-0.2288E-07	-33.1991	-0.9953	(A)	A (	0.00)	A
2- 2	-0.2827E-16	0.0000	0.0000	(A)	A (	0.00)	A
3- 3	0.1521E-16	0.0000	0.0000	(A)	A (	0.00)	A
4- 4	0.6593E-16	0.0000	0.0000	(A)	A (	0.00)	A
5- 5	0.7579E-07	60.4222	1.8114	(A)	A (	0.00)	A
6- 6	0.9525E-07	67.7341	2.0306	(A)	A (	0.00)	A
7- 7	0.1105E-06	72.9451	2.1868	(A)	A (	0.00)	A
8- 8	0.1401E-06	82.1353	2.4624	(A)	A (	0.00)	A
9- 9	0.1573E-06	87.0479	2.6096	(A)	A (	0.00)	A
10- 10	0.1719E-06	90.9951	2.7280	(A)	A (	0.00)	A
11- 11	0.1772E-06	92.3904	2.7698	(A)	A (	0.00)	A
12- 12	0.2133E-06	101.3611	3.0387	(A)	A (	0.00)	A
13- 13	0.2339E-06	106.1480	3.1822	(A)	A (	0.00)	A
14- 14	0.2505E-06	109.8577	3.2935	(A)	A (	0.00)	A
15- 15	0.2689E-06	113.8115	3.4120	(A)	A (	0.00)	A
16- 16	0.2772E-06	115.5531	3.4642	(A)	A (	0.00)	A
17- 17	0.2835E-06	116.8648	3.5035	(A)	A (	0.00)	A
18- 18	0.2893E-06	118.0481	3.5390	(A)	A (	0.00)	A
19- 19	0.3151E-06	123.2048	3.6936	(A)	A (	0.00)	A
20- 20	0.3329E-06	126.6388	3.7965	(A)	A (	0.00)	A
21- 21	0.3518E-06	130.1723	3.9025	(A)	A (	0.00)	A
22- 22	0.3740E-06	134.2130	4.0236	(A)	A (	0.00)	A
23- 23	0.3908E-06	137.2102	4.1135	(A)	A (	0.00)	A
24- 24	0.4093E-06	140.4194	4.2097	(A)	A (	0.00)	A
25- 25	0.4272E-06	143.4463	4.3004	(A)	A (	0.00)	A
26- 26	0.4670E-06	149.9775	4.4962	(A)	A (	0.00)	A
27- 27	0.4741E-06	151.1143	4.5303	(A)	A (	0.00)	A
28- 28	0.5024E-06	155.5653	4.6637	(A)	A (	0.00)	A
29- 29	0.5266E-06	159.2661	4.7747	(A)	A (	0.00)	A
30- 30	0.5341E-06	160.3933	4.8085	(A)	A (	0.00)	A
31- 31	0.5492E-06	162.6480	4.8761	(A)	A (	0.00)	A
32- 32	0.5541E-06	163.3783	4.8980	(A)	A (	0.00)	A
33- 33	0.5863E-06	168.0573	5.0382	(A)	A (	0.00)	A
34- 34	0.6286E-06	174.0038	5.2165	(A)	A (	0.00)	A
35- 35	0.6613E-06	178.4756	5.3506	(A)	A (	0.00)	A
36- 36	0.6755E-06	180.3810	5.4077	(A)	A (	0.00)	A
37- 37	0.7147E-06	185.5383	5.5623	(A)	A (	0.00)	A
38- 38	0.7550E-06	190.7059	5.7172	(A)	A (	0.00)	A
39- 39	0.7738E-06	193.0631	5.7879	(A)	A (	0.00)	A
40- 40	0.7855E-06	194.5152	5.8314	(A)	A (	0.00)	A
41- 41	0.8111E-06	197.6669	5.9259	(A)	A (	0.00)	A
42- 42	0.8400E-06	201.1561	6.0305	(A)	A (	0.00)	A
43- 43	0.8551E-06	202.9517	6.0843	(A)	A (	0.00)	A
44- 44	0.8934E-06	207.4433	6.2190	(A)	A (	0.00)	A
45- 45	0.9366E-06	212.4041	6.3677	(A)	A (	0.00)	A
46- 46	0.9638E-06	215.4687	6.4596	(A)	A (	0.00)	A
47- 47	0.9842E-06	217.7353	6.5275	(A)	A (	0.00)	A
48- 48	0.1027E-05	222.4378	6.6685	(A)	A (	0.00)	A
49- 49	0.1039E-05	223.7516	6.7079	(A)	A (	0.00)	A
50- 50	0.1061E-05	226.0592	6.7771	(A)	A (	0.00)	A
51- 51	0.1091E-05	229.2245	6.8720	(A)	A (	0.00)	A
52- 52	0.1137E-05	234.0042	7.0153	(A)	A (	0.00)	A
53- 53	0.1208E-05	241.1737	7.2302	(A)	A (	0.00)	A
54- 54	0.1239E-05	244.2813	7.3234	(A)	A (	0.00)	A
55- 55	0.1264E-05	246.7849	7.3984	(A)	A (	0.00)	A
56- 56	0.1295E-05	249.7146	7.4863	(A)	A (	0.00)	A
57- 57	0.1305E-05	250.7259	7.5166	(A)	A (	0.00)	A
58- 58	0.1344E-05	254.3988	7.6267	(A)	A (	0.00)	A
59- 59	0.1366E-05	256.5073	7.6899	(A)	A (	0.00)	A
60- 60	0.1389E-05	258.6496	7.7541	(A)	A (	0.00)	A
61- 61	0.1458E-05	265.0357	7.9456	(A)	A (	0.00)	A
62- 62	0.1508E-05	269.5235	8.0801	(A)	A (	0.00)	A
63- 63	0.1542E-05	272.5184	8.1699	(A)	A (	0.00)	A
64- 64	0.1580E-05	275.9045	8.2714	(A)	A (	0.00)	A
65- 65	0.1600E-05	277.6579	8.3240	(A)	A (	0.00)	A
66- 66	0.1657E-05	282.5290	8.4700	(A)	A (	0.00)	A
67- 67	0.1770E-05	291.9800	8.7533	(A)	A (	0.00)	A
68- 68	0.1805E-05	294.8521	8.8394	(A)	A (	0.00)	A
69- 69	0.1871E-05	300.1795	8.9992	(A)	A (	0.00)	A
70- 70	0.1904E-05	302.8806	9.0801	(A)	A (	0.00)	A
71- 71	0.1953E-05	306.7107	9.1950	(A)	A (	0.00)	A
72- 72	0.2044E-05	313.8166	9.4080	(A)	A (	0.00)	A
73- 73	0.2134E-05	320.5899	9.6110	(A)	A (	0.00)	A
74- 74	0.2199E-05	325.4940	9.7581	(A)	A (	0.00)	A
75- 75	0.2249E-05	329.1114	9.8665	(A)	A (	0.00)	A
76- 76	0.2331E-05	335.0725	10.0452	(A)	A (	0.00)	A
77- 77	0.2456E-05	343.9669	10.3119	(A)	A (	0.00)	A
78- 78	0.2482E-05	345.7678	10.3659	(A)	A (	0.00)	A
79- 79	0.2610E-05	354.5565	10.6293	(A)	A (	0.00)	A
80- 80	0.2715E-05	361.6505	10.8420	(A)	A (	0.00)	A
81- 81	0.2806E-05	367.6371	11.0215	(A)	A (	0.00)	A
82- 82	0.2826E-05	368.9531	11.0609	(A)	A (	0.00)	A
83- 83	0.2887E-05	372.9268	11.1801	(A)	A (	0.00)	A
84- 84	0.2979E-05	378.7816	11.3556	(A)	A (	0.00)	A
85- 85	0.3041E-05	382.7520	11.4746	(A)	A (	0.00)	A
86- 86	0.3073E-05	384.7191	11.5336	(A)	A (	0.00)	A
87- 87	0.3159E-05	390.0786	11.6943	(A)	A (	0.00)	A

88-88	0.3190E-05	391.9869	11.7515	(A)	A (	0.00)	A
89-89	0.3223E-05	394.0081	11.8121	(A)	A (	0.00)	A
90-90	0.3253E-05	395.8386	11.8669	(A)	A (	0.00)	A
91-91	0.3296E-05	398.4618	11.9456	(A)	A (	0.00)	A
92-92	0.3439E-05	406.9905	12.2013	(A)	A (	0.00)	A
93-93	0.3500E-05	410.6090	12.3097	(A)	A (	0.00)	A
94-94	0.3627E-05	417.9692	12.5304	(A)	A (	0.00)	A
95-95	0.3634E-05	418.3784	12.5427	(A)	A (	0.00)	A
96-96	0.3692E-05	421.6927	12.6420	(A)	A (	0.00)	A
97-97	0.3716E-05	423.0785	12.6836	(A)	A (	0.00)	A
98-98	0.3776E-05	426.4552	12.7848	(A)	A (	0.00)	A
99-99	0.3826E-05	429.3203	12.8707	(A)	A (	0.00)	A
100-100	0.3899E-05	433.3662	12.9920	(A)	A (	0.00)	A
101-101	0.3990E-05	438.4159	13.1434	(A)	A (	0.00)	A
102-102	0.4102E-05	444.4901	13.3255	(A)	A (	0.00)	A
103-103	0.4129E-05	445.9778	13.3701	(A)	A (	0.00)	A
104-104	0.4205E-05	450.0823	13.4931	(A)	A (	0.00)	A
105-105	0.4252E-05	452.5705	13.5677	(A)	A (	0.00)	A
106-106	0.4298E-05	455.0030	13.6406	(A)	A (	0.00)	A
107-107	0.4403E-05	460.5511	13.8070	(A)	A (	0.00)	A
108-108	0.4500E-05	465.5755	13.9576	(A)	A (	0.00)	A
109-109	0.4540E-05	467.6491	14.0198	(A)	A (	0.00)	A
110-110	0.4566E-05	468.9544	14.0589	(A)	A (	0.00)	A
111-111	0.4671E-05	474.3538	14.2208	(A)	A (	0.00)	A
112-112	0.4738E-05	477.7463	14.3225	(A)	A (	0.00)	A
113-113	0.4802E-05	480.9506	14.4185	(A)	A (	0.00)	A
114-114	0.4833E-05	482.4856	14.4646	(A)	A (	0.00)	A
115-115	0.4885E-05	485.1038	14.5430	(A)	A (	0.00)	A
116-116	0.4961E-05	488.8423	14.6551	(A)	A (	0.00)	A
117-117	0.4967E-05	489.1469	14.6643	(A)	A (	0.00)	A
118-118	0.4999E-05	490.7002	14.7108	(A)	A (	0.00)	A
119-119	0.5101E-05	495.6912	14.8604	(A)	A (	0.00)	A
120-120	0.5125E-05	496.8364	14.8948	(A)	A (	0.00)	A
121-121	0.5312E-05	505.8280	15.1643	(A)	A (	0.00)	A
122-122	0.5392E-05	509.6420	15.2787	(A)	A (	0.00)	A
123-123	0.5481E-05	513.8367	15.4044	(A)	A (	0.00)	A
124-124	0.5650E-05	521.7049	15.6403	(A)	A (	0.00)	A
125-125	0.5823E-05	529.5940	15.8768	(A)	A (	0.00)	A
126-126	0.5937E-05	534.7651	16.0319	(A)	A (	0.00)	A
127-127	0.5964E-05	535.9672	16.0679	(A)	A (	0.00)	A
128-128	0.6167E-05	545.3021	16.3397	(A)	A (	0.00)	A
129-129	0.6294E-05	550.6001	16.5066	(A)	A (	0.00)	A
130-130	0.6542E-05	561.3537	16.8290	(A)	A (	0.00)	A
131-131	0.6682E-05	567.3328	17.0082	(A)	A (	0.00)	A
132-132	0.6699E-05	568.0465	17.0296	(A)	A (	0.00)	A
133-133	0.6840E-05	574.0092	17.2084	(A)	A (	0.00)	A
134-134	0.7004E-05	580.8477	17.4134	(A)	A (	0.00)	A
135-135	0.7062E-05	583.2577	17.4856	(A)	A (	0.00)	A
136-136	0.7266E-05	591.5998	17.7357	(A)	A (	0.00)	A
137-137	0.7340E-05	594.6175	17.8262	(A)	A (	0.00)	A
138-138	0.7628E-05	606.1823	18.1729	(A)	A (	0.00)	A
139-139	0.8008E-05	621.0929	18.6199	(A)	A (	0.00)	A
140-140	0.8148E-05	626.4975	18.7819	(A)	A (	0.00)	A
141-141	0.8233E-05	629.7540	18.8795	(A)	A (	0.00)	A
142-142	0.8487E-05	639.3902	19.1684	(A)	A (	0.00)	A
143-143	0.8978E-05	657.6072	19.7146	(A)	A (	0.00)	A
144-144	0.9101E-05	662.1042	19.8494	(A)	A (	0.00)	A
145-145	0.9206E-05	665.9801	19.9634	(A)	A (	0.00)	A
146-146	0.9515E-05	677.0058	20.2961	(A)	A (	0.00)	A
147-147	0.9678E-05	682.7860	20.4694	(A)	A (	0.00)	A
148-148	0.1009E-04	697.2760	20.9038	(A)	A (	0.00)	A
149-149	0.1021E-04	701.1310	21.0194	(A)	A (	0.00)	A
150-150	0.1042E-04	708.4677	21.2393	(A)	A (	0.00)	A
151-151	0.1065E-04	716.2834	21.4736	(A)	A (	0.00)	A
152-152	0.1079E-04	720.7710	21.6082	(A)	A (	0.00)	A
153-153	0.1082E-04	721.8175	21.6395	(A)	A (	0.00)	A
154-154	0.1105E-04	729.7160	21.8763	(A)	A (	0.00)	A
155-155	0.1119E-04	734.0603	22.0062	(A)	A (	0.00)	A
156-156	0.1146E-04	743.0284	22.2754	(A)	A (	0.00)	A
157-157	0.1159E-04	747.2529	22.4021	(A)	A (	0.00)	A
158-158	0.1165E-04	748.9987	22.4541	(A)	A (	0.00)	A
159-159	0.1168E-04	750.0194	22.4850	(A)	A (	0.00)	A
160-160	0.1173E-04	751.7484	22.5368	(A)	A (	0.00)	A
161-161	0.1193E-04	758.1971	22.7302	(A)	A (	0.00)	A
162-162	0.1198E-04	759.6531	22.7738	(A)	A (	0.00)	A
163-163	0.1207E-04	762.3628	22.8551	(A)	A (	0.00)	A
164-164	0.1216E-04	765.2610	22.9419	(A)	A (	0.00)	A
165-165	0.1222E-04	767.2849	23.0026	(A)	A (	0.00)	A
166-166	0.1246E-04	774.8018	23.2280	(A)	A (	0.00)	A
167-167	0.1256E-04	777.7901	23.3176	(A)	A (	0.00)	A
168-168	0.1264E-04	780.2822	23.3923	(A)	A (	0.00)	A
169-169	0.1274E-04	783.3682	23.4848	(A)	A (	0.00)	A
170-170	0.1289E-04	788.0585	23.6254	(A)	A (	0.00)	A
171-171	0.1293E-04	789.2817	23.6621	(A)	A (	0.00)	A
172-172	0.1303E-04	792.1401	23.7478	(A)	A (	0.00)	A
173-173	0.1325E-04	798.8435	23.9487	(A)	A (	0.00)	A
174-174	0.1338E-04	802.8024	24.0674	(A)	A (	0.00)	A
175-175	0.1347E-04	805.4111	24.1456	(A)	A (	0.00)	A
176-176	0.1367E-04	811.3475	24.3236	(A)	A (	0.00)	A
177-177	0.1679E-04	899.3327	26.9613	(A)	A (	0.00)	A
178-178	0.1830E-04	938.7684	28.1436	(A)	A (	0.00)	A
179-179	0.1936E-04	956.6564	28.9496	(A)	A (	0.00)	A
180-180	0.2152E-04	1018.2350	30.5259	(A)	A (	0.00)	A
181-181	0.2325E-04	1058.2525	31.7256	(A)	A (	0.00)	A
182-182	0.2337E-04	1060.9772	31.8073	(A)	A (	0.00)	A
183-183	0.2500E-04	1097.2730	32.8954	(A)	A (	0.00)	A
184-184	0.2541E-04	1106.2486	33.1645	(A)	A (	0.00)	A
185-185	0.2552E-04	1108.7462	33.2394	(A)	A (	0.00)	A
186-186	0.2666E-04	1111.7516	33.3295	(A)	A (	0.00)	A
187-187	0.2587E-04	1116.2553	33.4648	(A)	A (	0.00)	A
188-188	0.2604E-04	1119.8820	33.5732	(A)	A (	0.00)	A
189-189	0.2614E-04	1122.1761	33.6420	(A)	A (	0.00)	A
190-190	0.2630E-04	1125.4806	33.7411	(A)	A (	0.00)	A
191-191	0.2642E-04	1128.1371	33.8207	(A)	A (	0.00)	A
192-192	0.2683E-04	1134.2585	34.0942	(A)	A (	0.00)	A
193-193	0.2863E-04	1136.0399	34.6084	(A)	A (	0.00)	A
194-194	0.2876E-04	1139.6703	34.1486	(A)	A (	0.00)	A
195-195	0.2703E-04	1141.1010	34.2093	(A)	A (	0.00)	A
196-196	0.2724E-04	1145.5328	34.3422	(A)	A (	0.00)	A
197-197	0.2727E-04	1146.1428	34.3605	(A)	A (	0.00)	A
198-198	0.2747E-04	1150.2197	34.4827	(A)	A (	0.00)	A
199-199	0.2759E-04	1152.8566	34.5618	(A)	A (	0.00)	A
200-200	0.2766E-04	1154.2068	34.6022	(A)	A (	0.00)	A
201-201	0.2774E-04	1156.0067	34.6562	(A)	A (	0.00)	A
202-202	0.2793E-04	1159.8198	34.7705	(A)	A (	0.00)	A
203-203	0.2804E-04	1162.0878	34.8385	(A)	A (	0.00)	A
204-204	0.2811E-04	1163.6607	34.8857	(A)	A (	0.00)	A
205-205	0.2851E-04	1171.9421	35.1339	(A)	A (	0.00)	A
206-206	0.2856E-04	1172.8977	35.1626	(A)	A (	0.00)	A

207- 207	0.2880E-04	1177.8628	35.3114	(A)	A (0.00)	A
208- 208	0.2885E-04	1178.7777	35.3389	(A)	A (0.00)	A
209- 209	0.2891E-04	1180.1111	35.3790	(A)	A (0.00)	A
210- 210	0.2899E-04	1181.6914	35.4262	(A)	A (0.00)	A
211- 211	0.2918E-04	1185.6612	35.5452	(A)	A (0.00)	A
212- 212	0.2926E-04	1187.2084	35.5916	(A)	A (0.00)	A
213- 213	0.2971E-04	1196.2821	35.8636	(A)	A (0.00)	A
214- 214	0.3042E-04	1210.4676	36.2889	(A)	A (0.00)	A
215- 215	0.3118E-04	1225.5455	36.7409	(A)	A (0.00)	A
216- 216	0.3184E-04	1238.4415	37.1275	(A)	A (0.00)	A
217- 217	0.3189E-04	1239.3097	37.1536	(A)	A (0.00)	A
218- 218	0.3250E-04	1251.1210	37.5077	(A)	A (0.00)	A
219- 219	0.3253E-04	1251.8235	37.5287	(A)	A (0.00)	A
220- 220	0.3301E-04	1261.0386	37.8050	(A)	A (0.00)	A
221- 221	0.3338E-04	1268.1036	38.0168	(A)	A (0.00)	A
222- 222	0.3368E-04	1273.6535	38.1832	(A)	A (0.00)	A
223- 223	0.3383E-04	1276.6045	38.2716	(A)	A (0.00)	A
224- 224	0.3391E-04	1278.0900	38.3162	(A)	A (0.00)	A
225- 225	0.3449E-04	1288.9224	38.6409	(A)	A (0.00)	A
226- 226	0.3588E-04	1314.6472	39.4121	(A)	A (0.00)	A
227- 227	0.5167E-04	1577.6966	47.2982	(A)	A (0.00)	A
228- 228	0.5303E-04	1598.2495	47.9143	(A)	A (0.00)	A
229- 229	0.2516E-03	3481.1061	104.3609	(A)	A (0.00)	A
230- 230	0.2636E-03	3563.6262	106.8348	(A)	A (0.00)	A
231- 231	0.2654E-03	3575.6994	107.1968	(A)	A (0.00)	A

Monometallic oxygen addition step

MODES		EIGV (HARTREE**2)	FREQUENCIES (CM**+1) (THZ)	IRREP	IR	INTENS (KM/MOL)	RAMAN
1- 1	0.1097E-05	-229.8879	-6.8919	(A)	A (0.00)	A	
2- 2	0.6256E-16	0.0000	0.0000	(A)	A (0.00)	A	
3- 3	0.8059E-16	0.0000	0.0000	(A)	A (0.00)	A	
4- 4	0.8496E-16	0.0000	0.0000	(A)	A (0.00)	A	
5- 5	0.2477E-07	34.5390	1.0355	(A)	A (0.00)	A	
6- 6	0.5755E-07	52.6527	1.5785	(A)	A (0.00)	A	
7- 7	0.6387E-07	55.4673	1.6629	(A)	A (0.00)	A	
8- 8	0.1087E-06	72.3622	2.1694	(A)	A (0.00)	A	
9- 9	0.1138E-06	74.0282	2.2193	(A)	A (0.00)	A	
10- 10	0.1369E-06	81.2121	2.4347	(A)	A (0.00)	A	
11- 11	0.1679E-06	89.9422	2.6984	(A)	A (0.00)	A	
12- 12	0.1823E-06	93.7070	2.8093	(A)	A (0.00)	A	
13- 13	0.2012E-06	98.4492	2.9514	(A)	A (0.00)	A	
14- 14	0.2212E-06	103.2235	3.0946	(A)	A (0.00)	A	
15- 15	0.2685E-06	113.9313	3.4156	(A)	A (0.00)	A	
16- 16	0.2739E-06	114.8552	3.4433	(A)	A (0.00)	A	
17- 17	0.2970E-06	119.6171	3.5860	(A)	A (0.00)	A	
18- 18	0.3056E-06	121.3345	3.6375	(A)	A (0.00)	A	
19- 19	0.3200E-06	124.1513	3.7220	(A)	A (0.00)	A	
20- 20	0.3279E-06	125.6752	3.7676	(A)	A (0.00)	A	
21- 21	0.3578E-06	131.2905	3.9360	(A)	A (0.00)	A	
22- 22	0.3631E-06	132.2447	3.9646	(A)	A (0.00)	A	
23- 23	0.4079E-06	140.1653	4.2020	(A)	A (0.00)	A	
24- 24	0.4333E-06	144.4744	4.3312	(A)	A (0.00)	A	
25- 25	0.4365E-06	144.9957	4.3469	(A)	A (0.00)	A	
26- 26	0.4641E-06	149.5136	4.4823	(A)	A (0.00)	A	
27- 27	0.4956E-06	154.5106	4.6321	(A)	A (0.00)	A	
28- 28	0.5067E-06	156.2296	4.6836	(A)	A (0.00)	A	
29- 29	0.5196E-06	158.2108	4.7430	(A)	A (0.00)	A	
30- 30	0.5400E-06	161.2831	4.8351	(A)	A (0.00)	A	
31- 31	0.5596E-06	164.1877	4.9222	(A)	A (0.00)	A	
32- 32	0.6082E-06	171.1600	5.1312	(A)	A (0.00)	A	
33- 33	0.6282E-06	173.9568	5.2151	(A)	A (0.00)	A	
34- 34	0.6482E-06	176.7064	5.2975	(A)	A (0.00)	A	
35- 35	0.6555E-06	177.6915	5.3271	(A)	A (0.00)	A	
36- 36	0.6767E-06	180.5438	5.4126	(A)	A (0.00)	A	
37- 37	0.6971E-06	183.2399	5.4934	(A)	A (0.00)	A	
38- 38	0.7087E-06	184.7633	5.5391	(A)	A (0.00)	A	
39- 39	0.7322E-06	187.8073	5.6303	(A)	A (0.00)	A	
40- 40	0.7569E-06	190.9464	5.7244	(A)	A (0.00)	A	
41- 41	0.7754E-06	193.2655	5.7940	(A)	A (0.00)	A	
42- 42	0.8240E-06	199.2247	5.9726	(A)	A (0.00)	A	
43- 43	0.8513E-06	202.5011	6.0708	(A)	A (0.00)	A	
44- 44	0.8696E-06	204.6668	6.1358	(A)	A (0.00)	A	
45- 45	0.8755E-06	205.3560	6.1564	(A)	A (0.00)	A	
46- 46	0.9257E-06	211.1591	6.3304	(A)	A (0.00)	A	
47- 47	0.9402E-06	212.8152	6.3800	(A)	A (0.00)	A	
48- 48	0.9617E-06	215.2351	6.4526	(A)	A (0.00)	A	
49- 49	0.9804E-06	217.3132	6.5149	(A)	A (0.00)	A	
50- 50	0.1007E-05	220.1907	6.6012	(A)	A (0.00)	A	
51- 51	0.1028E-05	222.5231	6.6711	(A)	A (0.00)	A	
52- 52	0.1094E-05	229.5274	6.8811	(A)	A (0.00)	A	
53- 53	0.1132E-05	233.5120	7.0005	(A)	A (0.00)	A	
54- 54	0.1164E-05	236.7928	7.0989	(A)	A (0.00)	A	
55- 55	0.1182E-05	238.5978	7.1530	(A)	A (0.00)	A	
56- 56	0.1196E-05	240.0142	7.1954	(A)	A (0.00)	A	
57- 57	0.1250E-05	245.3560	7.3556	(A)	A (0.00)	A	
58- 58	0.1293E-05	249.5173	7.4803	(A)	A (0.00)	A	
59- 59	0.1324E-05	252.5113	7.5701	(A)	A (0.00)	A	
60- 60	0.1354E-05	255.3736	7.6559	(A)	A (0.00)	A	
61- 61	0.1439E-05	263.2866	7.8931	(A)	A (0.00)	A	
62- 62	0.1466E-05	265.7666	7.9675	(A)	A (0.00)	A	
63- 63	0.1475E-05	266.5923	7.9922	(A)	A (0.00)	A	
64- 64	0.1515E-05	270.1076	8.0976	(A)	A (0.00)	A	
65- 65	0.1551E-05	273.2982	8.1933	(A)	A (0.00)	A	
66- 66	0.1595E-05	277.1835	8.3098	(A)	A (0.00)	A	
67- 67	0.1634E-05	280.5328	8.4102	(A)	A (0.00)	A	
68- 68	0.1669E-05	283.5016	8.4992	(A)	A (0.00)	A	
69- 69	0.1725E-05	288.2850	8.6426	(A)	A (0.00)	A	
70- 70	0.1758E-05	291.0003	8.7240	(A)	A (0.00)	A	
71- 71	0.1804E-05	294.8038	8.8380	(A)	A (0.00)	A	
72- 72	0.1863E-05	299.5440	8.9801	(A)	A (0.00)	A	
73- 73	0.1909E-05	303.2172	9.0902	(A)	A (0.00)	A	
74- 74	0.1958E-05	307.1024	9.2067	(A)	A (0.00)	A	
75- 75	0.2080E-05	316.4966	9.4883	(A)	A (0.00)	A	
76- 76	0.2153E-05	322.0307	9.6542	(A)	A (0.00)	A	
77- 77	0.2259E-05	329.8669	9.8892	(A)	A (0.00)	A	
78- 78	0.2392E-05	339.4219	10.1756	(A)	A (0.00)	A	
79- 79	0.2538E-05	349.6160	10.4812	(A)	A (0.00)	A	
80- 80	0.2608E-05	354.4317	10.6256	(A)	A (0.00)	A	
81- 81	0.2705E-05	360.9862	10.8221	(A)	A (0.00)	A	

82- 82	0.2725E-05	362.2984	10.8614	(A)	A (0.00)	A
83- 83	0.2932E-05	375.8137	11.2666	(A)	A (0.00)	A
84- 84	0.2993E-05	379.6700	11.3822	(A)	A (0.00)	A
85- 85	0.3012E-05	380.9282	11.4199	(A)	A (0.00)	A
86- 86	0.3072E-05	384.6608	11.5318	(A)	A (0.00)	A
87- 87	0.3150E-05	389.5358	11.6780	(A)	A (0.00)	A
88- 88	0.3168E-05	390.6555	11.7116	(A)	A (0.00)	A
89- 89	0.3200E-05	392.6258	11.7706	(A)	A (0.00)	A
90- 90	0.3228E-05	394.3248	11.8216	(A)	A (0.00)	A
91- 91	0.3243E-05	395.2635	11.8497	(A)	A (0.00)	A
92- 92	0.3386E-05	403.8653	12.1076	(A)	A (0.00)	A
93- 93	0.3465E-05	408.5557	12.2482	(A)	A (0.00)	A
94- 94	0.3497E-05	410.4154	12.3039	(A)	A (0.00)	A
95- 95	0.3588E-05	415.7570	12.4641	(A)	A (0.00)	A
96- 96	0.3623E-05	417.7561	12.5240	(A)	A (0.00)	A
97- 97	0.3676E-05	420.8170	12.6158	(A)	A (0.00)	A
98- 98	0.3703E-05	422.3467	12.6616	(A)	A (0.00)	A
99- 99	0.3744E-05	424.6588	12.7309	(A)	A (0.00)	A
100- 100	0.3770E-05	426.1204	12.7748	(A)	A (0.00)	A
101- 101	0.3846E-05	430.4187	12.9037	(A)	A (0.00)	A
102- 102	0.3876E-05	432.1071	12.9542	(A)	A (0.00)	A
103- 103	0.3943E-05	435.8281	13.0658	(A)	A (0.00)	A
104- 104	0.3989E-05	438.3322	13.1409	(A)	A (0.00)	A
105- 105	0.4105E-05	444.6486	13.3302	(A)	A (0.00)	A
106- 106	0.4148E-05	447.0112	13.4011	(A)	A (0.00)	A
107- 107	0.4289E-05	454.5124	13.6259	(A)	A (0.00)	A
108- 108	0.4333E-05	456.8438	13.6958	(A)	A (0.00)	A
109- 109	0.4382E-05	459.4423	13.7737	(A)	A (0.00)	A
110- 110	0.4393E-05	459.9975	13.7904	(A)	A (0.00)	A
111- 111	0.4415E-05	461.1521	13.8250	(A)	A (0.00)	A
112- 112	0.4521E-05	466.6641	13.9902	(A)	A (0.00)	A
113- 113	0.4605E-05	470.9714	14.1194	(A)	A (0.00)	A
114- 114	0.4653E-05	473.4442	14.1935	(A)	A (0.00)	A
115- 115	0.4723E-05	476.9842	14.2996	(A)	A (0.00)	A
116- 116	0.4751E-05	478.4007	14.3421	(A)	A (0.00)	A
117- 117	0.4872E-05	484.4311	14.5229	(A)	A (0.00)	A
118- 118	0.4930E-05	487.2977	14.6088	(A)	A (0.00)	A
119- 119	0.4960E-05	488.7780	14.6532	(A)	A (0.00)	A
120- 120	0.5013E-05	491.3889	14.7315	(A)	A (0.00)	A
121- 121	0.5026E-05	492.0322	14.7508	(A)	A (0.00)	A
122- 122	0.5106E-05	495.9243	14.8674	(A)	A (0.00)	A
123- 123	0.5155E-05	498.3175	14.9392	(A)	A (0.00)	A
124- 124	0.5239E-05	502.3720	15.0607	(A)	A (0.00)	A
125- 125	0.5323E-05	506.3746	15.1807	(A)	A (0.00)	A
126- 126	0.5420E-05	510.9787	15.3188	(A)	A (0.00)	A
127- 127	0.5553E-05	517.1820	15.5047	(A)	A (0.00)	A
128- 128	0.5583E-05	518.5854	15.5468	(A)	A (0.00)	A
129- 129	0.5675E-05	522.8175	15.6737	(A)	A (0.00)	A
130- 130	0.5776E-05	527.4693	15.8131	(A)	A (0.00)	A
131- 131	0.5914E-05	533.7211	16.0006	(A)	A (0.00)	A
132- 132	0.5998E-05	537.5131	16.1142	(A)	A (0.00)	A
133- 133	0.6181E-05	545.6361	16.3578	(A)	A (0.00)	A
134- 134	0.6331E-05	552.2267	16.5553	(A)	A (0.00)	A
135- 135	0.6461E-05	557.8535	16.7240	(A)	A (0.00)	A
136- 136	0.6697E-05	567.9545	17.0268	(A)	A (0.00)	A
137- 137	0.6722E-05	569.0171	17.0587	(A)	A (0.00)	A
138- 138	0.6892E-05	576.1625	17.2729	(A)	A (0.00)	A
139- 139	0.6982E-05	579.9202	17.3856	(A)	A (0.00)	A
140- 140	0.7117E-05	585.5057	17.5350	(A)	A (0.00)	A
141- 141	0.7243E-05	590.6647	17.7077	(A)	A (0.00)	A
142- 142	0.7960E-05	619.2269	18.5640	(A)	A (0.00)	A
143- 143	0.8501E-05	639.9622	19.1845	(A)	A (0.00)	A
144- 144	0.8626E-05	644.9119	19.3247	(A)	A (0.00)	A
145- 145	0.8973E-05	657.4259	19.7093	(A)	A (0.00)	A
146- 146	0.9133E-05	663.2851	19.8848	(A)	A (0.00)	A
147- 147	0.9203E-05	665.8107	19.9605	(A)	A (0.00)	A
148- 148	0.9243E-05	667.2624	20.0040	(A)	A (0.00)	A
149- 149	0.9305E-05	669.1929	20.0482	(A)	A (0.00)	A
150- 150	0.9715E-05	684.0932	20.5086	(A)	A (0.00)	A
151- 151	0.9874E-05	689.6631	20.6756	(A)	A (0.00)	A
152- 152	0.1033E-04	705.5299	21.1513	(A)	A (0.00)	A
153- 153	0.1071E-04	718.2265	21.5319	(A)	A (0.00)	A
154- 154	0.1106E-04	730.0204	21.8855	(A)	A (0.00)	A
155- 155	0.1117E-04	733.5090	21.9900	(A)	A (0.00)	A
156- 156	0.1124E-04	735.6894	22.0554	(A)	A (0.00)	A
157- 157	0.1145E-04	742.6319	22.2635	(A)	A (0.00)	A
158- 158	0.1155E-04	746.0478	22.3660	(A)	A (0.00)	A
159- 159	0.1182E-04	754.3995	22.6163	(A)	A (0.00)	A
160- 160	0.1190E-04	757.1358	22.6984	(A)	A (0.00)	A
161- 161	0.1195E-04	758.5807	22.7417	(A)	A (0.00)	A
162- 162	0.1214E-04	764.6297	22.9230	(A)	A (0.00)	A
163- 163	0.1222E-04	767.3009	23.0031	(A)	A (0.00)	A
164- 164	0.1225E-04	768.0361	23.0251	(A)	A (0.00)	A
165- 165	0.1231E-04	769.9649	23.0830	(A)	A (0.00)	A
166- 166	0.1246E-04	774.7397	23.2261	(A)	A (0.00)	A
167- 167	0.1254E-04	777.0469	23.2953	(A)	A (0.00)	A
168- 168	0.1265E-04	780.7221	23.4055	(A)	A (0.00)	A
169- 169	0.1272E-04	782.7297	23.4656	(A)	A (0.00)	A
170- 170	0.1296E-04	790.1920	23.6894	(A)	A (0.00)	A
171- 171	0.1303E-04	792.1452	23.7479	(A)	A (0.00)	A
172- 172	0.1315E-04	795.9460	23.8619	(A)	A (0.00)	A
173- 173	0.1319E-04	797.0122	23.8938	(A)	A (0.00)	A
174- 174	0.1327E-04	799.3608	23.9642	(A)	A (0.00)	A
175- 175	0.1364E-04	810.5021	24.2982	(A)	A (0.00)	A
176- 176	0.1373E-04	813.1901	24.3788	(A)	A (0.00)	A
177- 177	0.1404E-04	822.4322	24.6556	(A)	A (0.00)	A
178- 178	0.1748E-04	917.6030	27.5090	(A)	A (0.00)	A
179- 179	0.1911E-04	959.3772	28.7614	(A)	A (0.00)	A
180- 180	0.2144E-04	1016.1950	30.4648	(A)	A (0.00)	A
181- 181	0.2490E-04	1095.2026	32.8333	(A)	A (0.00)	A
182- 182	0.2502E-04	1097.8959	32.9139	(A)	A (0.00)	A
183- 183	0.2567E-04	1111.9329	33.3349	(A)	A (0.00)	A
184- 184	0.2572E-04	1113.1627	33.3718	(A)	A (0.00)	A
185- 185	0.2595E-04	1117.9982	33.5167	(A)	A (0.00)	A
186- 186	0.2613E-04	1121.8567	33.6324	(A)	A (0.00)	A
187- 187	0.2657E-04	1127.8575	33.7871	(A)	A (0.00)	A
188- 188	0.2652E-04	1130.1455	33.8389	(A)	A (0.00)	A
189- 189	0.2655E-04	1130.9276	33.9044	(A)	A (0.00)	A
190- 190	0.2667E-04	1133.3285	33.9633	(A)	A (0.00)	A
191- 191	0.2671E-04	1134.3646	34.0065	(A)	A (0.00)	A
192- 192	0.2679E-04	1136.0364	34.0575	(A)	A (0.00)	A
193- 193	0.2682E-04	1136.7085	34.0777	(A)	A (0.00)	A
194- 194	0.2685E-04	1137.1527	34.0910	(A)	A (0.00)	A
195- 195	0.2698E-04	1139.9928	34.1761	(A)	A (0.00)	A
196- 196	0.2703E-04	1140.9602	34.2051	(A)	A (0.00)	A
197- 197	0.2717E-04	1143.9233	34.2940	(A)	A (0.00)	A
198- 198	0.2724E-04	1145.4986	34.3412	(A)	A (0.00)	A
199- 199	0.2735E-04	1147.7566	34.4089	(A)	A (0.00)	A
200- 200	0.2739E-04	1148.5564	34.4329	(A)	A (0.00)	A

201-	201	0.2749E-04	1150.7221	34.4978	(A)	A (	0.00)	A
202-	202	0.2752E-04	1151.3347	34.5161	(A)	A (	0.00)	A
203-	203	0.2773E-04	1155.7153	34.6475	(A)	A (	0.00)	A
204-	204	0.2775E-04	1156.2115	34.6623	(A)	A (	0.00)	A
205-	205	0.2799E-04	1161.2093	34.8122	(A)	A (	0.00)	A
206-	206	0.2805E-04	1162.2858	34.8445	(A)	A (	0.00)	A
207-	207	0.2808E-04	1163.0723	34.8680	(A)	A (	0.00)	A
208-	208	0.2826E-04	1166.8079	34.9800	(A)	A (	0.00)	A
209-	209	0.2831E-04	1167.8176	35.0103	(A)	A (	0.00)	A
210-	210	0.2845E-04	1170.6148	35.0941	(A)	A (	0.00)	A
211-	211	0.2847E-04	1171.0242	35.1064	(A)	A (	0.00)	A
212-	212	0.2865E-04	1174.6730	35.2158	(A)	A (	0.00)	A
213-	213	0.2893E-04	1180.3938	35.3873	(A)	A (	0.00)	A
214-	214	0.2917E-04	1185.4670	35.5394	(A)	A (	0.00)	A
215-	215	0.2926E-04	1187.1537	35.5900	(A)	A (	0.00)	A
216-	216	0.3030E-04	1208.1783	36.2203	(A)	A (	0.00)	A
217-	217	0.3082E-04	1218.3595	36.5255	(A)	A (	0.00)	A
218-	218	0.3187E-04	1239.0714	37.1464	(A)	A (	0.00)	A
219-	219	0.3231E-04	1247.6139	37.4025	(A)	A (	0.00)	A
220-	220	0.3285E-04	1254.0028	37.5941	(A)	A (	0.00)	A
221-	221	0.3281E-04	1257.1799	37.6893	(A)	A (	0.00)	A
222-	222	0.3297E-04	1260.2408	37.7811	(A)	A (	0.00)	A
223-	223	0.3332E-04	1266.8853	37.9803	(A)	A (	0.00)	A
224-	224	0.3335E-04	1267.4535	37.9973	(A)	A (	0.00)	A
225-	225	0.3360E-04	1272.1440	38.1379	(A)	A (	0.00)	A
226-	226	0.3382E-04	1276.3044	38.2626	(A)	A (	0.00)	A
227-	227	0.3401E-04	1280.0054	38.3736	(A)	A (	0.00)	A
228-	228	0.3459E-04	1290.7510	38.6957	(A)	A (	0.00)	A
229-	229	0.4145E-04	1412.9474	42.3591	(A)	A (	0.00)	A
230-	230	0.4787E-04	1518.4887	45.5231	(A)	A (	0.00)	A
231-	231	0.4937E-04	1542.1849	46.2335	(A)	A (	0.00)	A
232-	232	0.9418E-04	2129.9445	63.8541	(A)	A (	0.00)	A
233-	233	0.2292E-03	3322.8680	99.6171	(A)	A (	0.00)	A
234-	234	0.2557E-03	3509.4879	105.2118	(A)	A (	0.00)	A

75-	75	0.1980E-05	308.9274	9.2584	(A)	A (	0.00)	A
76-	76	0.2007E-05	310.9189	9.3211	(A)	A (	0.00)	A
77-	77	0.2113E-05	318.9946	9.5632	(A)	A (	0.00)	A
78-	78	0.2142E-05	321.2168	9.6298	(A)	A (	0.00)	A
79-	79	0.2242E-05	328.6258	9.8520	(A)	A (	0.00)	A
80-	80	0.2297E-05	332.6500	9.9726	(A)	A (	0.00)	A
81-	81	0.2358E-05	337.0384	10.1042	(A)	A (	0.00)	A
82-	82	0.2437E-05	342.5849	10.2704	(A)	A (	0.00)	A
83-	83	0.2631E-05	356.0118	10.6730	(A)	A (	0.00)	A
84-	84	0.2647E-05	357.0534	10.7042	(A)	A (	0.00)	A
85-	85	0.2830E-05	369.1839	11.0679	(A)	A (	0.00)	A
86-	86	0.2897E-05	373.5276	11.1981	(A)	A (	0.00)	A
87-	87	0.2943E-05	376.5066	11.2874	(A)	A (	0.00)	A
88-	88	0.3004E-05	380.3818	11.4036	(A)	A (	0.00)	A
89-	89	0.3080E-05	385.1571	11.5467	(A)	A (	0.00)	A
90-	90	0.3115E-05	387.3749	11.6132	(A)	A (	0.00)	A
91-	91	0.3140E-05	388.9231	11.6596	(A)	A (	0.00)	A
92-	92	0.3190E-05	391.9894	11.7515	(A)	A (	0.00)	A
93-	93	0.3261E-05	396.3335	11.8818	(A)	A (	0.00)	A
94-	94	0.3328E-05	400.4031	12.0038	(A)	A (	0.00)	A
95-	95	0.3439E-05	407.0017	12.2016	(A)	A (	0.00)	A
96-	96	0.3501E-05	410.6674	12.3115	(A)	A (	0.00)	A
97-	97	0.3587E-05	415.6754	12.4616	(A)	A (	0.00)	A
98-	98	0.3619E-05	417.5497	12.5178	(A)	A (	0.00)	A
99-	99	0.3642E-05	418.8538	12.5569	(A)	A (	0.00)	A
100-	100	0.3666E-05	420.1616	12.5973	(A)	A (	0.00)	A
101-	101	0.3706E-05	422.4918	12.6660	(A)	A (	0.00)	A
102-	102	0.3754E-05	425.2097	12.7475	(A)	A (	0.00)	A
103-	103	0.3814E-05	428.6268	12.8499	(A)	A (	0.00)	A
104-	104	0.3853E-05	430.7956	12.9149	(A)	A (	0.00)	A
105-	105	0.3943E-05	435.8059	13.0651	(A)	A (	0.00)	A
106-	106	0.3991E-05	438.4700	13.1450	(A)	A (	0.00)	A
107-	107	0.4110E-05	444.9270	13.3386	(A)	A (	0.00)	A
108-	108	0.4153E-05	447.2504	13.4082	(A)	A (	0.00)	A
109-	109	0.4166E-05	447.9632	13.4296	(A)	A (	0.00)	A
110-	110	0.4279E-05	453.9853	13.6101	(A)	A (	0.00)	A
111-	111	0.4383E-05	459.4686	13.7745	(A)	A (	0.00)	A
112-	112	0.4489E-05	465.0260	13.9411	(A)	A (	0.00)	A
113-	113	0.4543E-05	467.8052	14.0244	(A)	A (	0.00)	A
114-	114	0.4574E-05	469.3736	14.0715	(A)	A (	0.00)	A
115-	115	0.4611E-05	471.2622	14.1281	(A)	A (	0.00)	A
116-	116	0.4686E-05	475.0976	14.2431	(A)	A (	0.00)	A
117-	117	0.4748E-05	478.2157	14.3365	(A)	A (	0.00)	A
118-	118	0.4851E-05	483.4015	14.4920	(A)	A (	0.00)	A
119-	119	0.4906E-05	486.1302	14.5738	(A)	A (	0.00)	A
120-	120	0.4947E-05	488.1312	14.6338	(A)	A (	0.00)	A
121-	121	0.4989E-05	489.2150	14.6663	(A)	A (	0.00)	A
122-	122	0.5007E-05	491.1053	14.7230	(A)	A (	0.00)	A
123-	123	0.5069E-05	494.1120	14.8131	(A)	A (	0.00)	A
124-	124	0.5155E-05	498.3223	14.9393	(A)	A (	0.00)	A
125-	125	0.5221E-05	501.4954	15.0345	(A)	A (	0.00)	A
126-	126	0.5338E-05	507.0635	15.2014	(A)	A (	0.00)	A
127-	127	0.5470E-05	513.3178	15.3889	(A)	A (	0.00)	A
128-	128	0.5532E-05	516.2201	15.4759	(A)	A (	0.00)	A
129-	129	0.5661E-05	522.1726	15.6543	(A)	A (	0.00)	A
130-	130	0.5850E-05	530.8384	15.9141	(A)	A (	0.00)	A
131-	131	0.5981E-05	536.7424	16.0911	(A)	A (	0.00)	A
132-	132	0.6115E-05	542.7170	16.2702	(A)	A (	0.00)	A
133-	133	0.6270E-05	549.5536	16.4752	(A)	A (	0.00)	A
134-	134	0.6450E-05	557.3789	16.7098	(A)	A (	0.00)	A
135-	135	0.6650E-05	565.9738	16.9675	(A)	A (	0.00)	A
136-	136	0.6882E-05	567.3485	17.0087	(A)	A (	0.00)	A
137-	137	0.6793E-05	572.0193	17.1487	(A)	A (	0.00)	A
138-	138	0.6857E-05	574.7085	17.2293	(A)	A (	0.00)	A
139-	139	0.7004E-05	580.8494	17.4134	(A)	A (	0.00)	A
140-	140	0.7144E-05	586.6122	17.5862	(A)	A (	0.00)	A
141-	141	0.7187E-05	588.3653	17.6387	(A)	A (	0.00)	A
142-	142	0.7358E-05	595.3251	17.8474	(A)	A (	0.00)	A
143-	143	0.8019E-05	621.4917	18.6319	(A)	A (	0.00)	A
144-	144	0.8058E-05	623.0015	18.6771	(A)	A (	0.00)	A
145-	145	0.8373E-05	635.0788	19.0392	(A)	A (	0.00)	A
146-	146	0.8650E-05	645.5031	19.3517	(A)	A (	0.00)	A
147-	147	0.8988E-05	657.9972	19.7263	(A)	A (	0.00)	A
148-	148	0.9170E-05	664.6066	19.9244	(A)	A (	0.00)	A
149-	149	0.9236E-05	667.0050	19.9963	(A)	A (	0.00)	A
150-	150	0.9536E-05	677.7388	20.3181	(A)	A (	0.00)	A
151-	151	0.9745E-05	685.1509	20.5403	(A)	A (	0.00)	A
152-	152	0.1000E-04	694.1116	20.8089	(A)	A (	0.00)	A
153-	153	0.1014E-04	698.8013	20.9495	(A)	A (	0.00)	A
154-	154	0.1051E-04	711.6355	21.3343	(A)	A (	0.00)	A
155-	155	0.1067E-04	716.7676	21.4882	(A)	A (	0.00)	A
156-	156	0.1089E-04	724.1207	21.7086	(A)	A (	0.00)	A
157-	157	0.1091E-04	724.8942	21.7318	(A)	A (	0.00)	A
158-	158	0.1102E-04	728.7211	21.8465	(A)	A (	0.00)	A
159-	159	0.1123E-04	735.3263	22.0445	(A)	A (	0.00)	A
160-	160	0.1140E-04	741.0228	22.2153	(A)	A (	0.00)	A
161-	161	0.1156E-04	746.3543	22.3751	(A)	A (	0.00)	A
162-	162	0.1162E-04	748.2574	22.4322	(A)	A (	0.00)	A
163-	163	0.1168E-04	750.1932	22.4902	(A)	A (	0.00)	A
164-	164	0.1187E-04	756.2149	22.6708	(A)	A (	0.00)	A
165-	165	0.1191E-04	757.4697	22.7084	(A)	A (	0.00)	A
166-	166	0.1204E-04	761.4758	22.8285	(A)	A (	0.00)	A
167-	167	0.1205E-04	761.9044	22.8413	(A)	A (	0.00)	A
168-	168	0.1231E-04	770.1026	23.0871	(A)	A (	0.00)	A
169-	169	0.1232E-04	770.3993	23.0960	(A)	A (	0.00)	A
170-	170	0.1238E-04	772.0727	23.1462	(A)	A (	0.00)	A
171-	171	0.1252E-04	776.6326	23.2829	(A)	A (	0.00)	A
172-	172	0.1257E-04	778.2594	23.3316	(A)	A (	0.00)	A
173-	173	0.1271E-04	782.4260	23.4565	(A)	A (	0.00)	A
174-	174	0.1286E-04	787.0126	23.5940	(A)	A (	0.00)	A
175-	175	0.1292E-04	788.9158	23.6511	(A)	A (	0.00)	A
176-	176	0.1302E-04	791.9073	23.7408	(A)	A (	0.00)	A
177-	177	0.1316E-04	796.1535	23.8681	(A)	A (	0.00)	A
178-	178	0.1333E-04	801.2522	24.0209	(A)	A (	0.00)	A
179-	179	0.1345E-04	804.8549	24.1289	(A)	A (	0.00)	A
180-	180	0.1368E-04	811.8610	24.3390	(A)	A (	0.00)	A
181-	181	0.1475E-04	916.7451	27.4393	(A)	A (	0.00)	A
182-	182	0.1876E-04	950.6993	28.5012	(A)	A (	0.00)	A
183-	183	0.1955E-04	970.3013	29.0889	(A)	A (	0.00)	A
184-	184	0.2258E-04	1042.8011	31.2624	(A)	A (	0.00)	A
185-	185	0.2328E-04	1058.9617	31.7469	(A)	A (	0.00)	A
186-	186	0.2392E-04	1073.3089	32.1770	(A)	A (	0.00)	A
187-	187	0.2467E-04	1090.1070	32.6806	(A)	A (	0.00)	A
188-	188	0.2483E-04	1093.6743	32.7875	(A)	A (	0.00)	A
189-	189	0.2524E-04	1102.5517	33.0537	(A)	A (	0.00)	A
190-	190	0.2545E-04	1107.1401	33.1912	(A)	A (	0.00)	A
191-	191	0.2569E-04	1112.3681	33.3480	(A)	A (	0.00)	A
192-	192	0.2582E-04	1115.1443	33.4312	(A)	A (	0.00)	A
193-	193	0.2591E-04	1117.0626	33.4887	(A)	A (	0.00)	A

194- 194	0.2616E-04	1122.5774	33.6540	(A)	A (	0.00)	A
195- 195	0.2631E-04	1125.7401	33.7488	(A)	A (	0.00)	A
196- 196	0.2647E-04	1129.1015	33.8496	(A)	A (	0.00)	A
197- 197	0.2655E-04	1130.9515	33.9051	(A)	A (	0.00)	A
198- 198	0.2665E-04	1133.0041	33.9666	(A)	A (	0.00)	A
199- 199	0.2678E-04	1135.8230	34.0511	(A)	A (	0.00)	A
200- 200	0.2689E-04	1138.1383	34.1205	(A)	A (	0.00)	A
201- 201	0.2698E-04	1140.0039	34.1765	(A)	A (	0.00)	A
202- 202	0.2712E-04	1143.0591	34.2680	(A)	A (	0.00)	A
203- 203	0.2725E-04	1145.6750	34.3465	(A)	A (	0.00)	A
204- 204	0.2743E-04	1149.5039	34.4613	(A)	A (	0.00)	A
205- 205	0.2758E-04	1152.6179	34.5546	(A)	A (	0.00)	A
206- 206	0.2782E-04	1157.7153	34.7074	(A)	A (	0.00)	A
207- 207	0.2787E-04	1158.6872	34.7366	(A)	A (	0.00)	A
208- 208	0.2794E-04	1160.1868	34.7815	(A)	A (	0.00)	A
209- 209	0.2806E-04	1162.6350	34.8549	(A)	A (	0.00)	A
210- 210	0.2824E-04	1166.3220	34.9655	(A)	A (	0.00)	A
211- 211	0.2829E-04	1167.3274	34.9956	(A)	A (	0.00)	A
212- 212	0.2847E-04	1171.1156	35.1092	(A)	A (	0.00)	A
213- 213	0.2856E-04	1172.8394	35.1606	(A)	A (	0.00)	A
214- 214	0.2885E-04	1178.8789	35.3419	(A)	A (	0.00)	A
215- 215	0.2886E-04	1179.0546	35.3472	(A)	A (	0.00)	A
216- 216	0.2892E-04	1180.2213	35.3821	(A)	A (	0.00)	A
217- 217	0.2923E-04	1186.6513	35.5749	(A)	A (	0.00)	A
218- 218	0.2954E-04	1192.9400	35.7634	(A)	A (	0.00)	A
219- 219	0.2956E-04	1193.1779	35.7706	(A)	A (	0.00)	A
220- 220	0.3054E-04	1212.8515	36.3604	(A)	A (	0.00)	A
221- 221	0.3180E-04	1237.7286	37.1062	(A)	A (	0.00)	A
222- 222	0.3196E-04	1240.7514	37.1968	(A)	A (	0.00)	A
223- 223	0.3208E-04	1243.0382	37.2653	(A)	A (	0.00)	A
224- 224	0.3272E-04	1255.3372	37.6341	(A)	A (	0.00)	A
225- 225	0.3275E-04	1256.0770	37.6562	(A)	A (	0.00)	A
226- 226	0.3331E-04	1266.6325	37.9727	(A)	A (	0.00)	A
227- 227	0.3360E-04	1272.2175	38.1401	(A)	A (	0.00)	A
228- 228	0.3388E-04	1277.4900	38.2982	(A)	A (	0.00)	A
229- 229	0.3424E-04	1284.3380	38.5035	(A)	A (	0.00)	A
230- 230	0.3458E-04	1290.6902	38.6939	(A)	A (	0.00)	A
231- 231	0.4332E-04	1444.4853	43.3046	(A)	A (	0.00)	A
232- 232	0.5193E-04	1581.6154	47.4156	(A)	A (	0.00)	A
233- 233	0.2491E-03	3463.8488	103.8436	(A)	A (	0.00)	A
234- 234	0.2628E-03	3557.6053	106.6543	(A)	A (	0.00)	A
235- 235	0.2639E-03	3565.0860	106.8786	(A)	A (	0.00)	A
236- 236	0.3138E-03	3888.0400	116.5605	(A)	A (	0.00)	A

Transition state figures

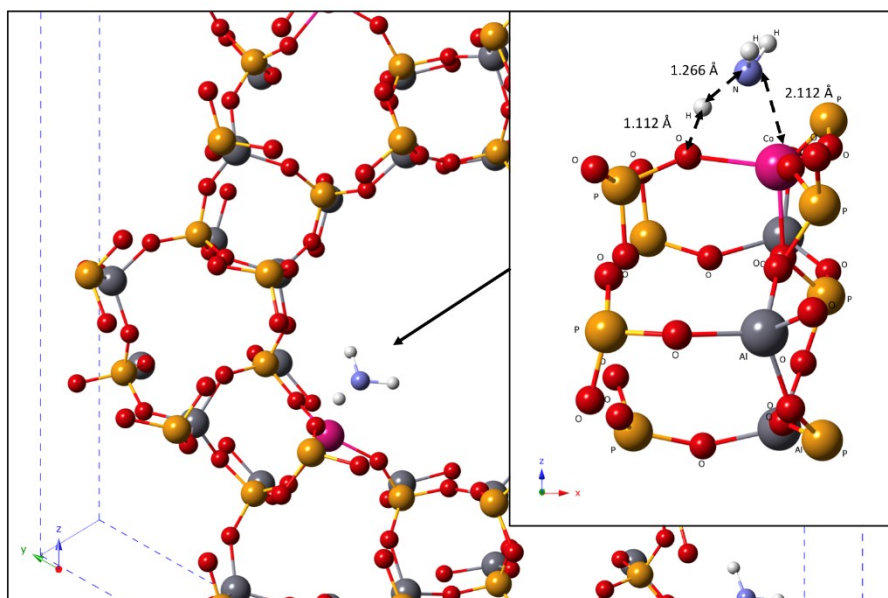


Figure S12: The calculated transition state for the monometallic CoAlPO-5 system during the hydrogen abstraction step. Pink = Cobalt, Red = Oxygen, Yellow = Phosphorus, Grey = Aluminium, White = Hydrogen, Blue = Nitrogen.

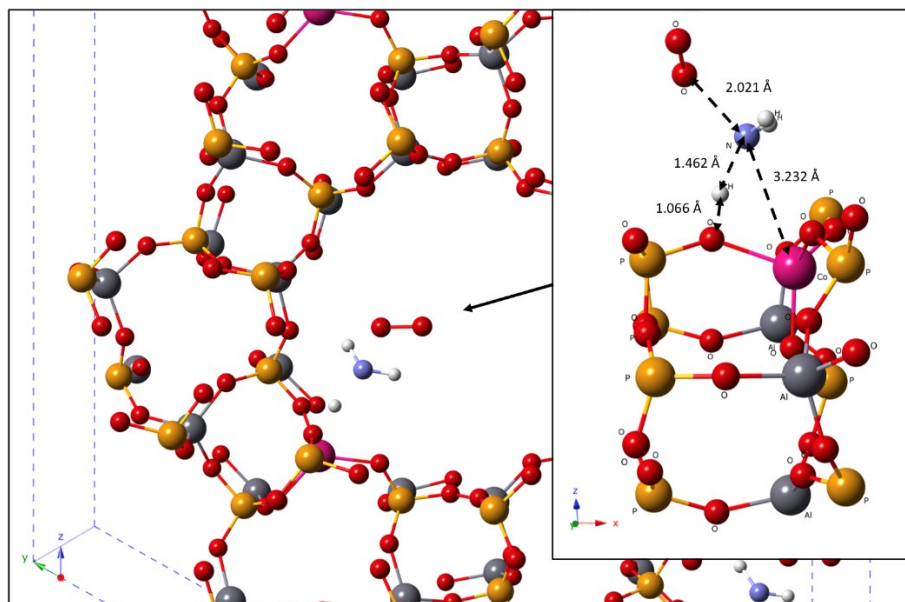


Figure S13: The calculated transition state for the monometallic CoAlPO-5 system during the oxygen addition step. Pink = Cobalt, Red = Oxygen, Yellow = Phosphorus, Grey = Aluminium, White = Hydrogen, Blue = Nitrogen.

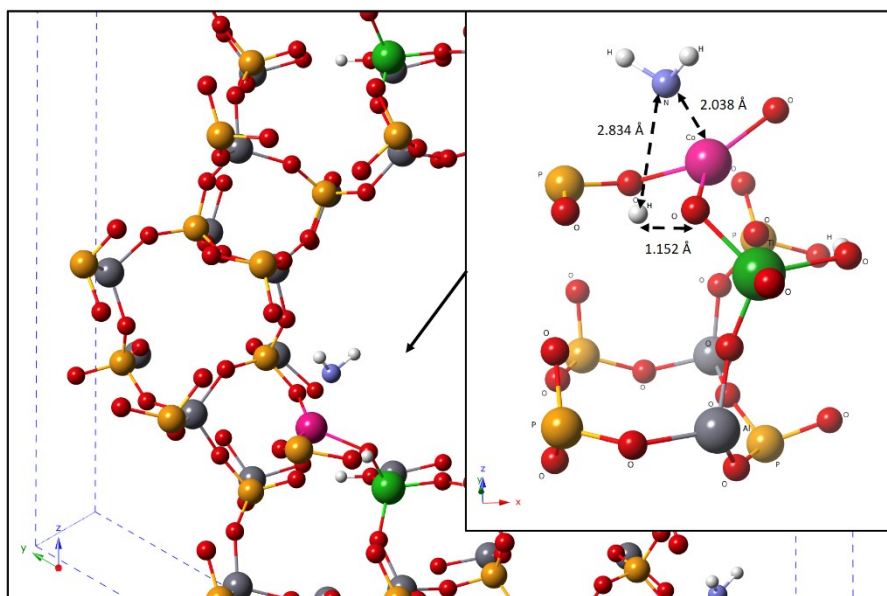


Figure S14: The calculated transition state for the bimetallic CoTiAlPO-5 system during the hydrogen abstraction step. Pink = Cobalt, Green = Titanium, Red = Oxygen, Yellow = Phosphorus, Grey = Aluminium, White = Hydrogen, Blue = Nitrogen.

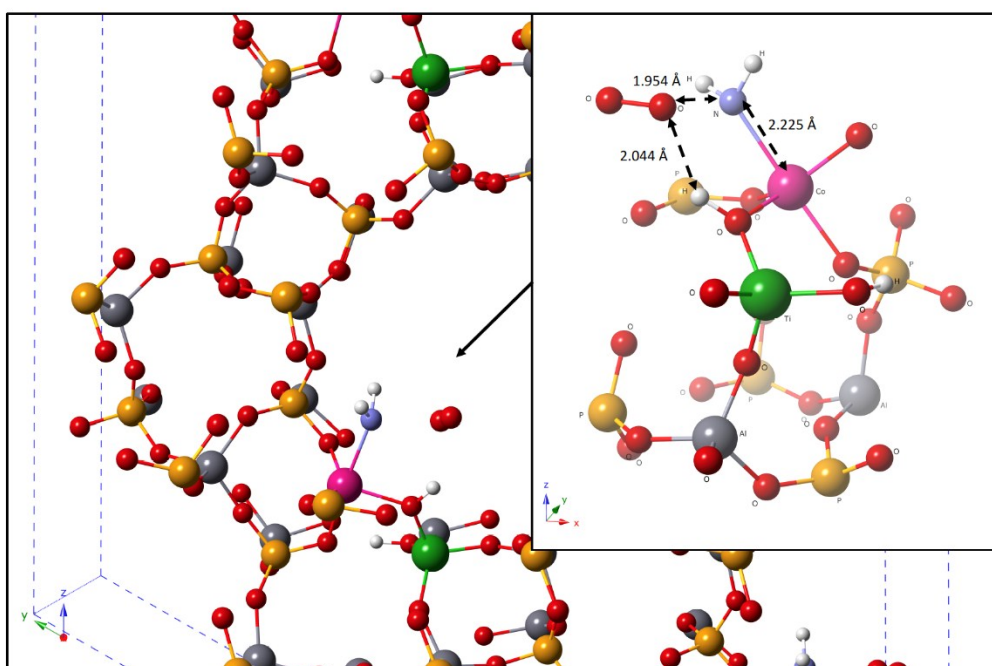


Figure S15: The calculated transition state for the bimetallic CoTiAlPO-5 system during the oxygen addition step. Pink = Cobalt, Green = Titanium, Red = Oxygen, Yellow = Phosphorus, Grey = Aluminium, White = Hydrogen, Blue = Nitrogen.

Complete reaction energetics

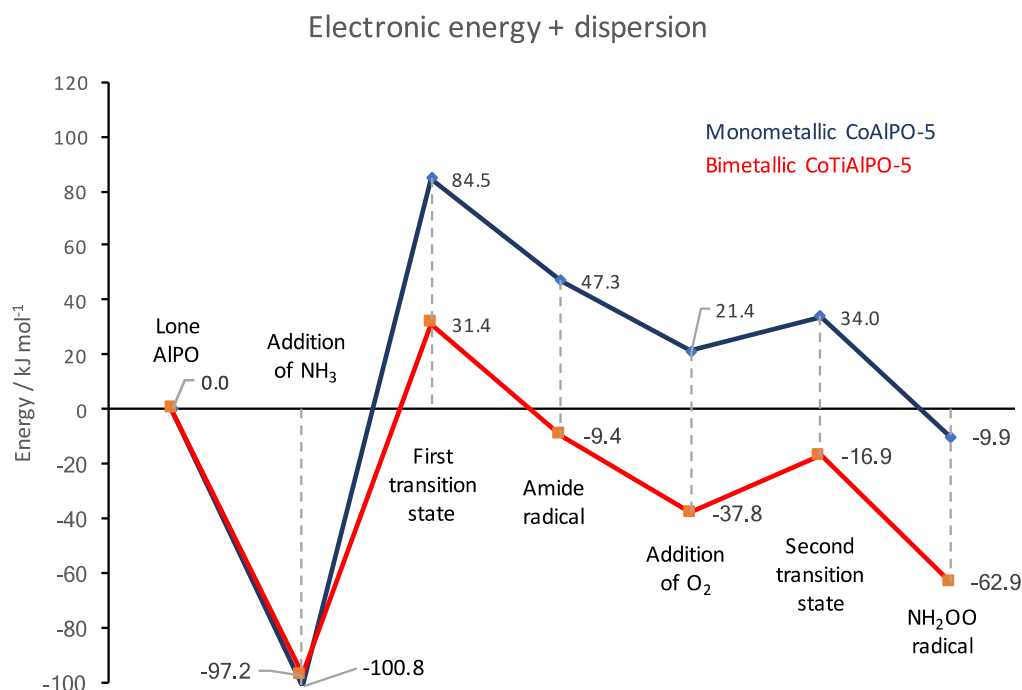


Figure S16: Full comparison of the complete electronic energetics required in the first two reaction steps, calculated with the addition of the dispersion correction.

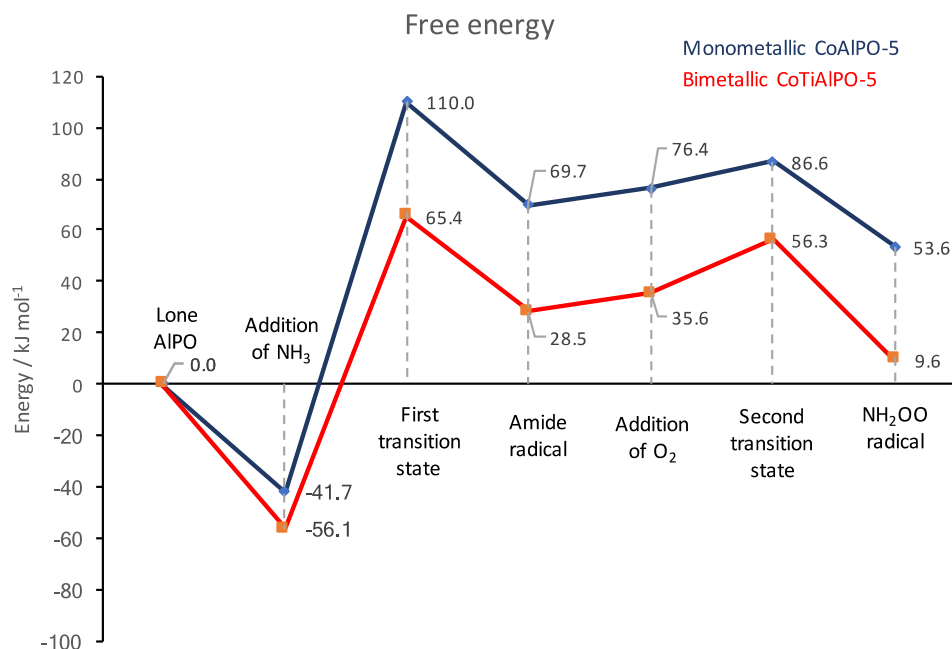


Figure S17: Full comparison of the complete free energy energetics required in the first two reaction steps, estimated by the addition of vibrational entropy and zero-point energy.

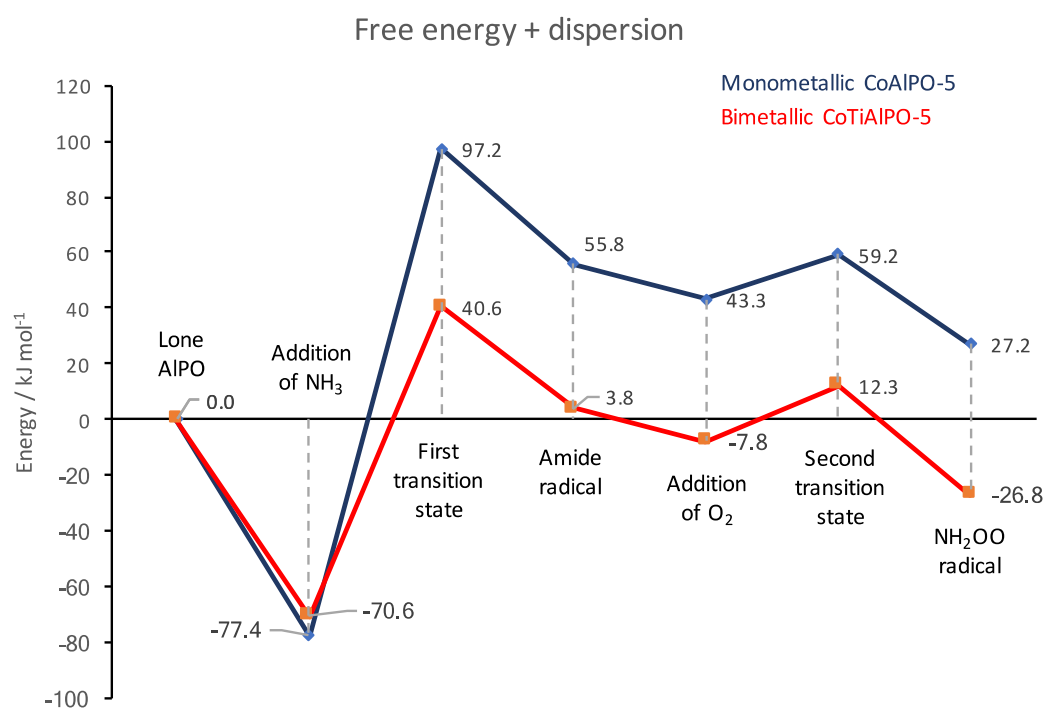


Figure S18: Full comparison of the complete free energy energetics required in the first two reaction steps, with the addition of the dispersion correction.