

Electronic Supplementary Information

Acceptor-Acceptor Type Isoindigo-Based Copolymers for High-Performance *n*-Channel Field-Effect Transistors

Gyoongsik Kim[‡], A-Reum Han[‡], Hae Rang Lee, Junghoon Lee, Joon Hak Oh*, and Changduk Yang*

School of Energy and Chemical Engineering, KIER-UNIST Advanced Center for Energy, Low Dimensional Carbon Materials Center, Ulsan National Institute of Science and Technology (UNIST), Ulsan 689-798, South Korea.

*E-mail: joonhoh@unist.ac.kr, yang@unist.ac.kr

Fax: +82-52-217-2909

[‡]These two authors contributed equally to this work.

Table of Contents	Page number
• General procedures and methods	S2
• Synthetic procedures	S4~S5
• OFET fabrication and measurements	S6
• Peak assignments for the out-of-plane XRD patterns	S7
• Detailed electrical parameters of OFET devices	S8
• OFET performance of the fractionated PIIG-TPD ($M_n = 32.0$ kDa, PDI = 1.5)	S9
• References	S9

Experimental Section

Materials and Instruments: 6-Bromooxindole was purchased from CAPOT chemical company, 6-bromoisoindole was purchased from TCI and other chemicals and solvent were purchased either from Aldrich or Acros and used without further purification. 6,6'-Dibromoisoindigo, 6,6'-(*N,N'*-2-octyldodecyl)-dibromoisoindigo (**M1**), were synthesized according to the literature.^{1, 2} ¹H NMR and ¹³C NMR spectra were recorded on a Varian VNRS 600 MHz (Varian USA) spectrophotometer using CDCl₃ as solvent and tetramethylsilane (TMS) as the internal standard and MALDI MS spectra were obtained from Ultraflex III (Bruker, Germany). UV-VIS-NIR spectra were taken on UV-1800 (SHIMADZU) spectrometer. Number-average (M_n) and weight average (M_w) molecular weights, and polydispersity index (PDI) of the polymer products were determined by gel permeation chromatography (GPC) with Perkin-Elmer Series 200 using a series of mono disperse polystyrene as standards in THF (HPLC grade) at 313 K. Preparative GPC (pre-GPC) was performed on FUTECS HPLC System NS-4000 with Shodex GPC K-2004 column using a chloroform (HPLC grade) at 298 K. Cyclic voltammetry (CV) measurements were performed on AMETEK VersaSTAT 3 with a three-electrode cell in a nitrogen bubbled 0.1 M tetra-*n*-butylammonium hexafluorophosphate (*n*-Bu₄NPF₆) solution in acetonitrile at a scan rate of 50 mV/s at room temperature. A used as the Ag/Ag⁺ (0.1 M of AgNO₃ in acetonitrile) reference electrode, platinum counter electrode and polymer coated platinum working electrode respectively. The Ag/Ag⁺ reference electrode was calibrated using a ferrocene/ferrocenium redox couple as an external standard, whose oxidation potential is set at -4.8 eV with respect to zero vacuum level. The HOMO energy levels were obtained from the equation: HOMO = - (E_{ox}^{onset} - E_(ferrocene)^{onset} + 4.8) eV. The LUMO levels of polymers were obtained from the equation: LUMO = - (E_{red}^{onset} - E_(ferrocene)^{onset} + 4.8) eV. Tapping-mode atomic force microscopy (AFM) measurements were performed using an Agilent 5500

scanning probe microscope (SPM) running with a Nanoscope V controller. The Rigaku high power X-ray diffractometer was used (D/MAZX 2500V/PC) to observe out-of-plane molecular packing in polymer films. X-ray diffraction (XRD) patterns were recorded under an X-ray power of 40 kV and a scan rate of 1 °/min.

Synthesis of 6,6'-(*N,N'*-2-octyldodecyl)-Pinacoldiboronisoindigo (3): 6,6'-(*N,N'*-2-octyldodecyl)-dibromoisoindigo (2 g, 2.04 mmol), bis(pinacolato)diboron (2.07 g, 8.16 mmol), potassium acetate (1.2 g, 12.24 mmol), and PdCl₂(dppf) (90 mg, 0.12 mmol) in anhydrous 1,4-dioxane (20 mL) were stirred at 80 °C for 2 d. The reaction was quenched by water and extracted with methylene chloride. The separated organic layer was washed with water and brine, then dried over MgSO₄ and removed under reduced pressure. The crude product was purified by column chromatography (silica gel, hexane to 50% methylene chloride in hexane) to afford 1.7 g (78%) of **3** as red-brown solid. ¹H NMR (600 MHz, CDCl₃) δ (ppm) 9.14 (d, 2H, *J*= 7.8 Hz), 7.48 (d, 2H, *J*= 7.8 Hz), 7.15 (s, 2H), 3.69 (d, 4H, *J*= 6.2 Hz), 1.95 (m, 2H), 1.40-1.26 (m, 88H), 0.87-0.84 (t, 12H, *J*= 6.6 Hz). ¹³C NMR (150 MHz, CDCl₃) δ (ppm) 168.24, 144.61, 134.46, 129.01, 128.86, 124.38, 113.64, 84.18, 44.60, 36.26, 32.07, 32.05, 31.73, 30.16, 29.79, 29.78, 29.74, 29.50, 29.46, 26.57, 25.02, 22.83, 22.82, 14.27. Elemental Analysis: C, 75.96; H, 10.50; N, 2.61; O, 8.93 Found: C, 75.97; H, 10.52; N, 2.61; O, 8.85. MALDI-TOF-MS *m/z*: [M]⁺ = 1076.24; calcd, 1075.25.

PIIG-BT: In a Schlenk flask, 6,6'-(*N,N'*-2-octyldodecyl)-dibromoisoindigo (**2**) (200 mg, 0.204 mmol) and 2,1,3-benzothiadiazole-4,7-bis(boronic acid pinacol ester) (79 mg, 0.204 mmol) was dissolved in toluene (7 mL), to this a solution of K₃PO₄ (217 mg, 1.02 mmol), tri-*o*-tolylphosphine (3.7 mg, 12.2 μmol) and deionized water (1.5 ml) was added. The mixture was vigorously stirred at room temperature under argon. After 30 min, Pd₂(dba)₃ (2.8 mg, 3.06 μmol) was added to the reaction mixture and stirred at 90 °C for 3 days (end capped with phenylboronic acid and bromobenzene). After then, the solution was precipitated in a mixture of methanol and ammonia (4:1 v/v, 250 mL). This was filtered off through paper filter under the vacuum, washed on Soxhlet apparatus with methanol (1d), acetone (1d) and hexane (1d) to remove low molecular weight. Finally, Soxhlet extracted chloroform fraction

re-precipitated into methanol and filtered off through 0.45 μm Teflon filter. 170 mg (87%) of the polymer was recovered as a dark-green powder ($M_n = 2.50 \times 10^4$ g/mol, PDI=1.32). ^1H NMR (600 MHz, CDCl_3) δ (ppm) 9.42-9.23 (br, 2H), 7.95-6.28 (br, 8H), 3.96-3.67 (br, 4H), 2.04-1.26 (br, 64H) 0.95-0.85 (br, 12H). Elemental Analysis: C, 77.77; H, 9.68; N, 5.85; O, 3.34; S, 3.35 Found: C, 77.03; H, 9.62; N, 5.74; O, 3.32; S, 3.26.

PIIG-TPD: In a Schlenk flask, 6,6'-(*N,N'*-2-octyldodecyl)-pinacoldiboronisoindigo (**3**) (219 mg, 0.204 mmol) and 1,3-dibromo-5-hexyl-thieno[3,4-c]pyrrole-4,6-dione (81 mg, 0.204 mmol) was dissolved in toluene (7 mL), to this a solution of K_3PO_4 (217 mg, 1.02 mmol), tri-*o*-tolylphosphine (3.7 mg, 12.2 μmol) and deionized water (1.5 ml) was added. The mixture was vigorously stirred at room temperature under argon. After 30 min, $\text{Pd}_2(\text{dba})_3$ (2.8 mg, 3.06 μmol) was added to the reaction mixture and stirred at 90 °C for 3 days (end capped with phenylboronic acid and bromobenzene). After then, the solution was precipitated in a mixture of methanol and ammonia (4:1 v/v, 250 mL). This was filtered off through paper filter under the vacuum, washed on Soxhlet apparatus with methanol (1d), acetone (1d) and hexane (1d) to remove low molecular weight. Finally, Soxhlet extracted chloroform fraction re-precipitated into methanol and filtered off through 0.45 μm Teflon filter. 134 mg (61%) of the polymer was recovered as a black powder ($M_n = 5.71 \times 10^4$ g/mol, PDI=3.30). ^1H NMR (600 MHz, CDCl_3) δ (ppm) 9.27-9.02 (br, 2H), 8.57-8.10 (br, 2H), 7.36-6.65 (br, 2H), 4.14-3.32 (br, 6H) 2.44-0.99 (br, 79H), 0.86-0.70 (br, 15H). Elemental Analysis: C, 77.37; H, 9.92; N, 3.87; O, 5.89; S, 2.95 Found: C, 77.12; H, 9.83; N, 3.74; O, 5.94; S, 2.81.

OFET Fabrication and Measurement: Bottom-gate top-contact OFET devices based on the isoindigo (IIG) copolymers were fabricated on a highly *n*-doped Si substrate with thermally grown 300-nm-thick SiO₂ layer ($C_i = 10 \text{ nFcm}^{-2}$), where the highly *n*-doped Si and SiO₂ layer were used as the gate electrode and dielectric, respectively. The surface of SiO₂/Si wafer was modified with *n*-octadecyltrimethoxysilane (OTS), as reported previously.³⁻⁵ After cleaning the SiO₂/Si wafers with piranha solution (a 7:3 mixture of H₂SO₄ and H₂O₂), OTS solution (3 mM in trichloroethylene) was spin-coated on the SiO₂/Si substrate at 3000 rpm for 30 s. The OTS-coated wafers were exposed to ammonia vapor in a desiccator for 12 h. Then, the wafers were rinsed with toluene, acetone, and isopropyl alcohol. The contact angle (DI water) on the hydrophobic OTS-modified wafer was typically ~110°.

The IIG-based copolymers (**PIIG-BT** and **PIIG-TPD**) were dissolved in anhydrous chloroform (~3 mg mL⁻¹) and the polymer films were prepared on the OTS-modified SiO₂/Si substrates by drop-casting method. Then, the polymer films were annealed on a hot plate at 150 °C for 30 min under N₂ atmosphere. Gold electrodes (40 nm) were thermally evaporated through a shadow mask with a channel length (L) of 50 μm and width (W) of 1000 μm. The current–voltage characteristics were measured in a N₂-filled glovebox by using a Keithley 4200 semiconductor parametric analyzer. The field-effect mobility was calculated in the saturation regime using the following equation:

$$I_{DS} = \frac{1}{2}(W/L)\mu C_i(V_G - V_T)^2$$

where I_{DS} is the drain current, W and L are the semiconductor channel width and length, respectively, μ is the mobility, C_i is the capacitance per unit area of the gate dielectric, and V_G and V_T are the gate voltage and threshold voltage, respectively.

Table S1. Peak assignments for the out-of-plane XRD patterns obtained from IIG-based copolymer thin films

Condition	(00 <i>n</i>)	PIIG-BT		PIIG-TPD	
		2θ [°]	<i>d</i> -spacing [Å]	2θ [°]	<i>d</i> -spacing [Å]
As-cast	(001)	3.86	22.87	3.60	24.52
	(002)	7.64	-	-	-
After annealing at 150 °C	(001)	3.78	23.36	-	-
	(002)	7.48	-	-	-
	(003)	11.18	-	-	-

Table S2. Detailed electrical parameters of OFET devices for **PIIG-BT** and **PIIG-TPD** films

Condition		μ_{max} [cm ² V ⁻¹ s ⁻¹]	μ_{avg} [cm ² V ⁻¹ s ⁻¹]	$I_{\text{on}}/I_{\text{off, avg}}$	$V_T, \text{avg}^{\text{c}}$ [V]
PIIG-BT	As-cast	0.005	0.003 (±0.0009) ^a	1.0×10^7 (±7.2×10 ⁶)	48.3 (±3.1)
	150 °C	0.22	0.09 (±0.06)	1.3×10^7 (±2.3×10 ⁷)	41.5 (±7.1)
PIIG-TPD	As-cast	0.004	0.003 (±0.01)	2.4×10^6 (±7.5×10 ⁵)	10.1 (±3.5)
	150 °C	0.01	0.008 (±0.003)	4.1×10^6 (±4.4×10 ⁶)	8.3 (±6.4)
PIIG-TPD^b	150 °C	0.001	6.0×10^{-4} (±2.0×10 ⁻⁴)	6.5×10^6 (±7.5×10 ⁵)	27.1 (±5.8)

^aThe standard deviation. ^bThe fractionated **PIIG-TPD** ($M_n = 32.0$ kDa, PDI = 1.5).

^cThe relatively higher V_T of **PIIG-BT** might originate from the larger injection barrier (due to the higher LUMO level) for electrons with respect to gold electrodes.

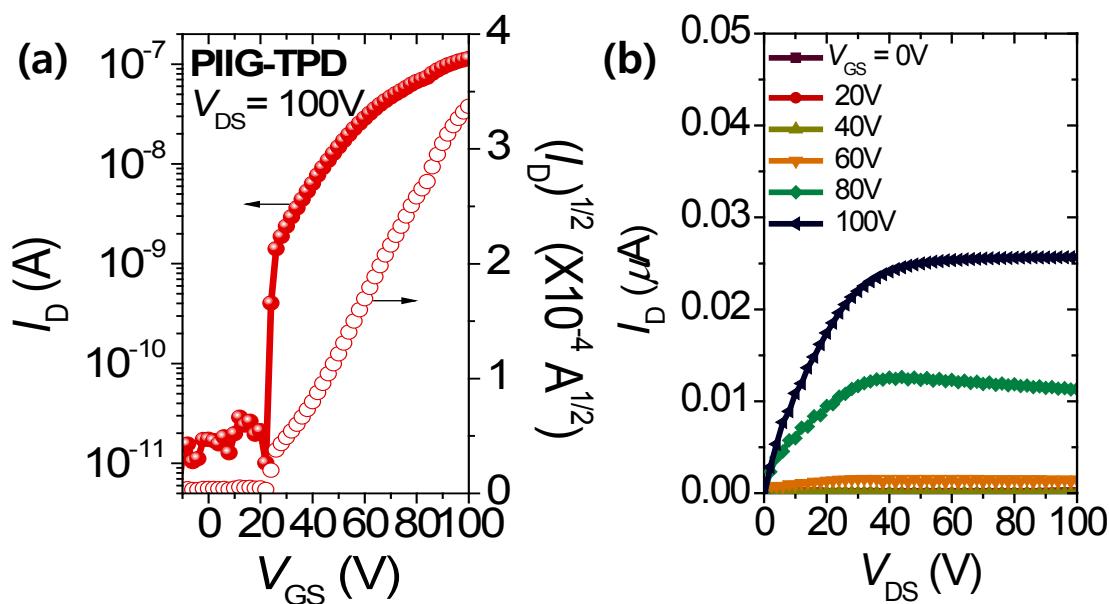


Fig. S1 OFET performance of the fractionated PIIG-TPD ($M_n = 32.0$ kDa, PDI = 1.5) thin films after annealing at 150 °C. (a) Transfer curve at $V_{DS} = +100V$ and (b) output characteristics.

References

1. R. Stalder, J. Mei and J. R. Reynolds, *Macromolecules*, 2010, **43**, 8348-8352.
2. T. Lei, Y. Cao, Y. Fan, C.-J. Liu, S.-C. Yuan and J. Pei, *J. Am. Chem. Soc.*, 2011, **133**, 6099-6101.
3. Y. Ito, A. A. Virkar, S. Mannsfeld, J. H. Oh, M. Toney, J. Locklin and Z. Bao, *J. Am. Chem. Soc.*, 2009, **131**, 9396-9404.
4. R. Schmidt, J. H. Oh, Y.-S. Sun, M. Deppisch, A.-M. Krause, K. Radacki, H. Braunschweig, M. Könemann, P. Erk and Z. Bao, *J. Am. Chem. Soc.*, 2009, **131**, 6215-6228.
5. A. Virkar, S. Mannsfeld, J. H. Oh, M. F. Toney, Y. H. Tan, G. y. Liu, J. C. Scott, R. Miller and Z. Bao, *Adv. Funct. Mater.*, 2009, **19**, 1962-1970.