



## Supporting Information for:

### Synthesis of poly(stearyl methacrylate)-poly(2-hydroxypropyl methacrylate) diblock copolymer nanoparticles via RAFT dispersion polymerization of 2-hydroxypropyl methacrylate in mineral oil

Csilla György, Saul J. Hunter, Chloé Girou, Matthew J. Derry and Steven P. Armes\*

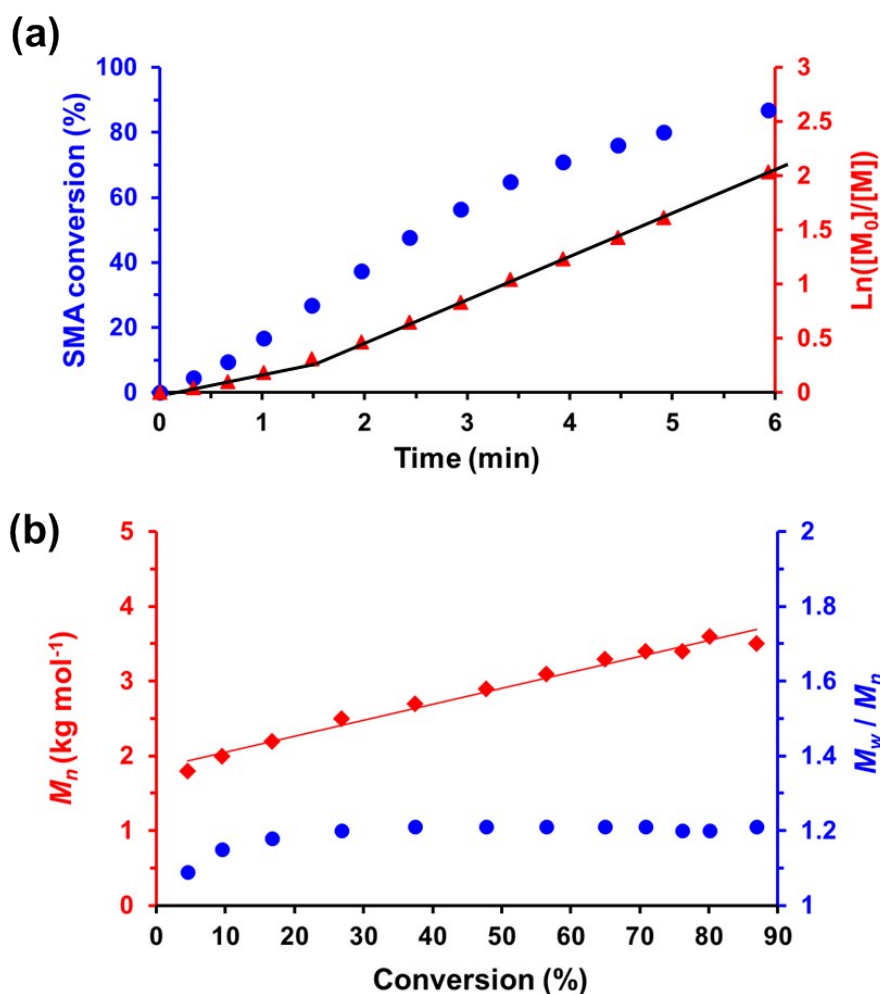

**Figure S1.** RAFT solution polymerization of SMA in toluene at 50% w/w solids and 70 °C using CPDB as a RAFT agent (target PSMA DP = 5; CPDB/initiator molar ratio = 5.0). **(a)** Conversion vs. time (blue circles) and corresponding  $\ln([M]_0/[M])$  vs. time (red triangles) plots. **(b)** Evolution in  $M_n$  (red diamonds) and  $M_w/M_n$  (blue circles) obtained by THF GPC analysis using a series of near-monodisperse poly(methyl methacrylate) calibration standards.

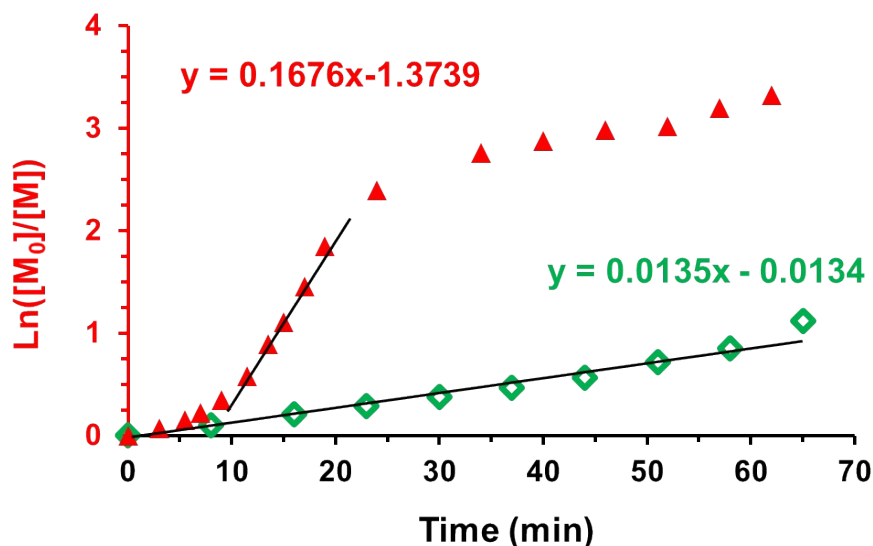

**Figure S2.** Semilogarithmic plots obtained for the RAFT dispersion homopolymerization of either HPMA or BzMA in mineral oil at 90 °C targeting either 15% w/w PSMA<sub>9</sub>-PHPMA<sub>150</sub> vesicles (red triangles) or 18% w/w PSMA<sub>9</sub>-PBzMA<sub>150</sub> vesicles (open green diamonds).

**Table S1.** Summary of the GPC, DLS and TEM data obtained for a series of PSMA<sub>9</sub>-PHPMA<sub>x</sub> diblock copolymer nano-objects prepared at 15% w/w in mineral oil. The PSMA<sub>9</sub> precursor is also included as a reference.

Target Composition	Solids Content (% w/w)	THF GPC		DLS		TEM Morphology
		$M_n$ (g mol <sup>-1</sup> )	$M_w/M_n$	$D$ (nm)	PDI	
PSMA <sub>9</sub> macro-CTA	-	4,500	1.12	-	-	-
PSMA <sub>9</sub> -PHPMA <sub>30</sub>	15	8,100	1.16	23	0.20	Spheres
PSMA <sub>9</sub> -PHPMA <sub>50</sub>	15	10,000	1.16	26	0.09	Spheres
PSMA <sub>9</sub> -PHPMA <sub>60</sub>	15	11,000	1.16	34	0.18	Spheres
PSMA <sub>9</sub> -PHPMA <sub>70</sub>	15	11,900	1.19	40	0.12	Spheres
PSMA <sub>9</sub> -PHPMA <sub>80</sub>	15	12,800	1.19	57	0.12	Mixed
PSMA <sub>9</sub> -PHPMA <sub>90</sub>	15	13,600	1.22	104	0.11	Mixed
PSMA <sub>9</sub> -PHPMA <sub>100</sub>	15	14,400	1.25	153	0.25	Mixed
PSMA <sub>9</sub> -PHPMA <sub>105</sub>	15	14,300	1.22	170	0.16	Mixed
PSMA <sub>9</sub> -PHPMA <sub>110</sub>	15	14,700	1.24	204	0.28	Mixed
PSMA <sub>9</sub> -PHPMA <sub>115</sub>	15	15,000	1.26	156	0.11	Mixed
PSMA <sub>9</sub> -PHPMA <sub>125</sub>	15	16,400	1.26	156	0.05	Mixed
PSMA <sub>9</sub> -PHPMA <sub>130</sub>	15	17,000	1.29	162	0.03	Vesicles
PSMA <sub>9</sub> -PHPMA <sub>150</sub>	15	18,800	1.37	170	0.07	Vesicles

**Table S2.** Summary of the GPC, DLS and TEM data obtained for a series of PSMA<sub>9</sub>-PHPMA<sub>x</sub> diblock copolymer nano-objects prepared at 20% w/w in mineral oil.


Target Composition	Solids Content (% w/w)	THF GPC		DLS		TEM Morphology
		$M_n$ (g mol <sup>-1</sup> )	$M_w/M_n$	$D$ (nm)	PDI	
PSMA <sub>9</sub> -PHPMA <sub>30</sub>	20	7,700	1.15	19	0.12	Spheres
PSMA <sub>9</sub> -PHPMA <sub>50</sub>	20	10,100	1.16	27	0.10	Spheres
PSMA <sub>9</sub> -PHPMA <sub>55</sub>	20	10,500	1.18	30	0.12	Spheres
PSMA <sub>9</sub> -PHPMA <sub>60</sub>	20	12,000	1.24	34	0.12	Spheres
PSMA <sub>9</sub> -PHPMA <sub>65</sub>	20	11,500	1.19	53	0.14	Mixed
PSMA <sub>9</sub> -PHPMA <sub>70</sub>	20	12,400	1.31	76	0.16	Mixed
PSMA <sub>9</sub> -PHPMA <sub>75</sub>	20	12,300	1.20	87	0.16	Mixed
PSMA <sub>9</sub> -PHPMA <sub>80</sub>	20	13,600	1.30	148	0.22	Mixed
PSMA <sub>9</sub> -PHPMA <sub>90</sub>	20	14,400	1.34	420	0.73	Mixed
PSMA <sub>9</sub> -PHPMA <sub>100</sub>	20	14,200	1.23	162	0.17	Mixed
PSMA <sub>9</sub> -PHPMA <sub>105</sub>	20	14,300	1.24	176	0.13	Mixed
PSMA <sub>9</sub> -PHPMA <sub>110</sub>	20	15,700	1.25	177	0.14	Mixed
PSMA <sub>9</sub> -PHPMA <sub>115</sub>	20	16,300	1.26	169	0.11	Vesicles
PSMA <sub>9</sub> -PHPMA <sub>120</sub>	20	16,700	1.27	182	0.14	Vesicles
PSMA <sub>9</sub> -PHPMA <sub>125</sub>	20	17,100	1.32	233	0.22	Vesicles
PSMA <sub>9</sub> -PHPMA <sub>130</sub>	20	17,600	1.28	211	0.14	Vesicles
PSMA <sub>9</sub> -PHPMA <sub>150</sub>	20	20,100	1.37	573	0.11	Vesicles

**Table S3.** Summary of the GPC, DLS and TEM data obtained for a series of PSMA<sub>9</sub>-PHPMA<sub>x</sub> diblock copolymer nano-objects prepared at 25% w/w in mineral oil.


Target Composition	Solids Content (% w/w)	THF GPC		DLS		TEM Morphology
		$M_n$ (g mol <sup>-1</sup> )	$M_w/M_n$	$D$ (nm)	PDI	
PSMA <sub>9</sub> -PHPMA <sub>50</sub>	25	9,900	1.15	31	0.19	Spheres
PSMA <sub>9</sub> -PHPMA <sub>60</sub>	25	11,000	1.17	85	0.42	Mixed
PSMA <sub>9</sub> -PHPMA <sub>70</sub>	25	12,600	1.19	156	0.54	Worms
PSMA <sub>9</sub> -PHPMA <sub>80</sub>	25	12,700	1.19	1715	0.80	Mixed
PSMA <sub>9</sub> -PHPMA <sub>85</sub>	25	13,000	1.22	437	0.75	Mixed
PSMA <sub>9</sub> -PHPMA <sub>90</sub>	25	13,300	1.21	276	0.40	Mixed
PSMA <sub>9</sub> -PHPMA <sub>100</sub>	25	14,700	1.23	256	0.35	Mixed
PSMA <sub>9</sub> -PHPMA <sub>105</sub>	25	15,000	1.24	210	0.16	Mixed
PSMA <sub>9</sub> -PHPMA <sub>110</sub>	25	15,700	1.24	189	0.16	Mixed
PSMA <sub>9</sub> -PHPMA <sub>115</sub>	25	16,000	1.25	318	0.35	Vesicles
PSMA <sub>9</sub> -PHPMA <sub>120</sub>	25	16,000	1.25	246	0.24	Vesicles
PSMA <sub>9</sub> -PHPMA <sub>125</sub>	25	17,200	1.26	445	0.19	Vesicles
PSMA <sub>9</sub> -PHPMA <sub>150</sub>	25	18,700	1.28	448	0.27	Vesicles

**Table S4.** Summary of the GPC, DLS and TEM data obtained for a series of PSMA<sub>9</sub>-PHPMA<sub>x</sub> diblock copolymer nano-objects prepared at 30% w/w in mineral oil.


Target Composition	Solids Content (% w/w)	THF GPC		DLS		TEM Morphology
		$M_n$ (g mol <sup>-1</sup> )	$M_w/M_n$	$D$ (nm)	PDI	
PSMA <sub>9</sub> -PHPMA <sub>40</sub>	30	9,000	1.15	22	0.15	Spheres
PSMA <sub>9</sub> -PHPMA <sub>50</sub>	30	9,900	1.16	26	0.07	Mixed
PSMA <sub>9</sub> -PHPMA <sub>60</sub>	30	10,200	1.16	46	0.12	Mixed
PSMA <sub>9</sub> -PHPMA <sub>67</sub>	30	11,400	1.18	157	0.58	Worms
PSMA <sub>9</sub> -PHPMA <sub>70</sub>	30	12,100	1.21	736	0.91	Worms
PSMA <sub>9</sub> -PHPMA <sub>80</sub>	30	12,300	1.22	471	0.60	Mixed
PSMA <sub>9</sub> -PHPMA <sub>90</sub>	30	14,300	1.24	715	0.66	Mixed
PSMA <sub>9</sub> -PHPMA <sub>100</sub>	30	15,000	1.27	923	1.00	Mixed
PSMA <sub>9</sub> -PHPMA <sub>110</sub>	30	16,000	1.26	219	0.21	Mixed
PSMA <sub>9</sub> -PHPMA <sub>120</sub>	30	16,900	1.31	1400	0.97	Mixed
PSMA <sub>9</sub> -PHPMA <sub>130</sub>	30	17,800	1.35	764	0.26	Mixed

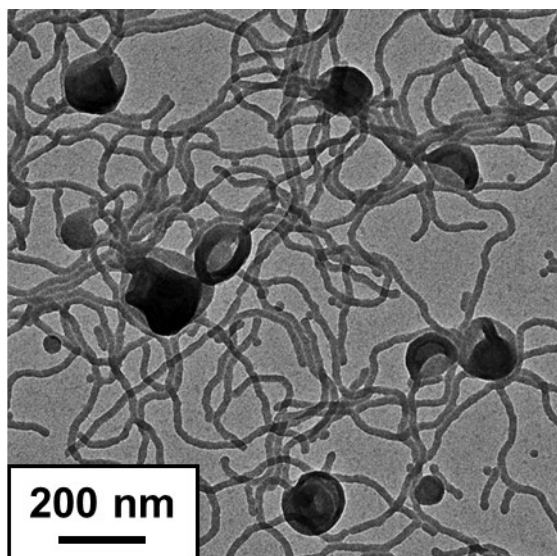


**Figure S3.** Representative TEM image recorded for a mixed phase of PSMA<sub>9</sub>-PHPMA<sub>70</sub> vesicles and worms (prepared at 25% w/w solids) obtained after oscillatory rheology studies.

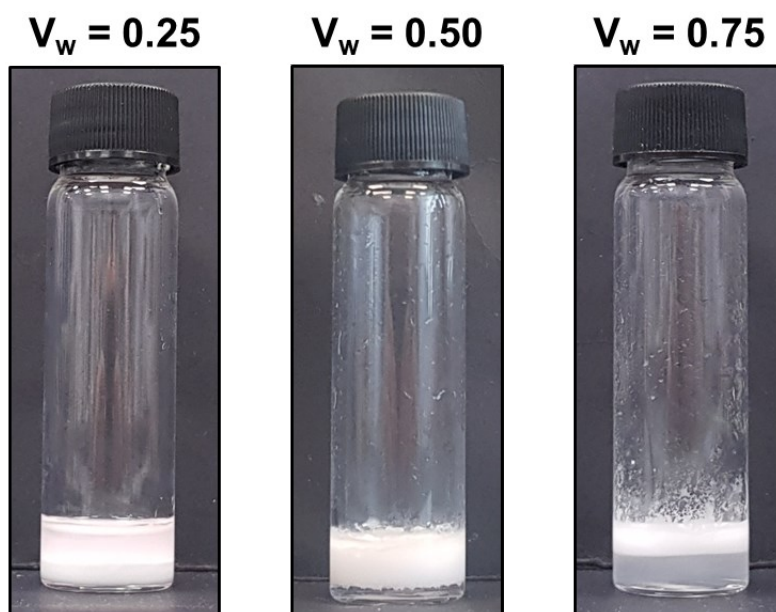


**Figure S4.** Digital photographs obtained for the Pickering emulsions prepared at 20 °C *via* high-shear homogenization at 13 500 rpm for 2 min using 1.0% w/w PSMA<sub>9</sub>-PHPMA<sub>50</sub> spheres in mineral oil at water volume fractions ( $V_w$ ) of 0.25, 0.50 or 0.75. Sedimentation of the denser aqueous droplets occurs for the emulsion prepared at a water volume fraction of 0.25, indicating the formation of a water-in-oil emulsion. In contrast, preparing the emulsions at a water volume fraction of 0.50 or 0.75 leads to droplet creaming, indicating the formation of (mainly) oil droplets within an aqueous continuous phase.

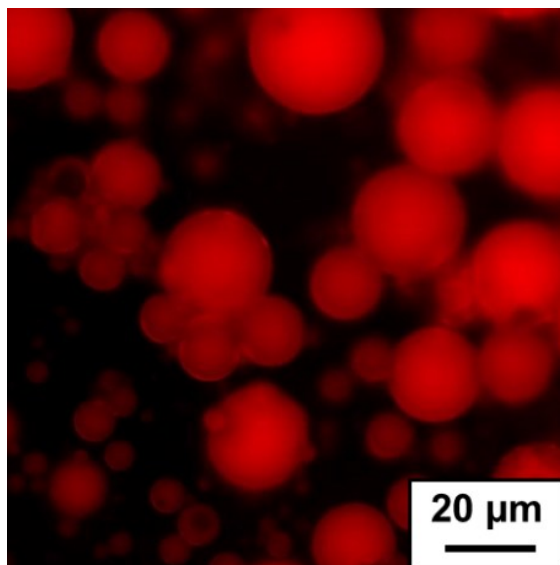


**Figure S5.** Fluorescence microscopy image recorded for an emulsion prepared using 1.00% w/w PSMA<sub>9</sub>-PHPMA<sub>50</sub> diblock copolymer spheres in mineral oil at a water volume fraction of 0.875. The location of the oil-soluble Nile Red dye suggests the formation of a (mainly) oil-in-water emulsion. However, some of the droplets contain dark domains, indicating the formation of a water-in-oil-in-water double emulsion.

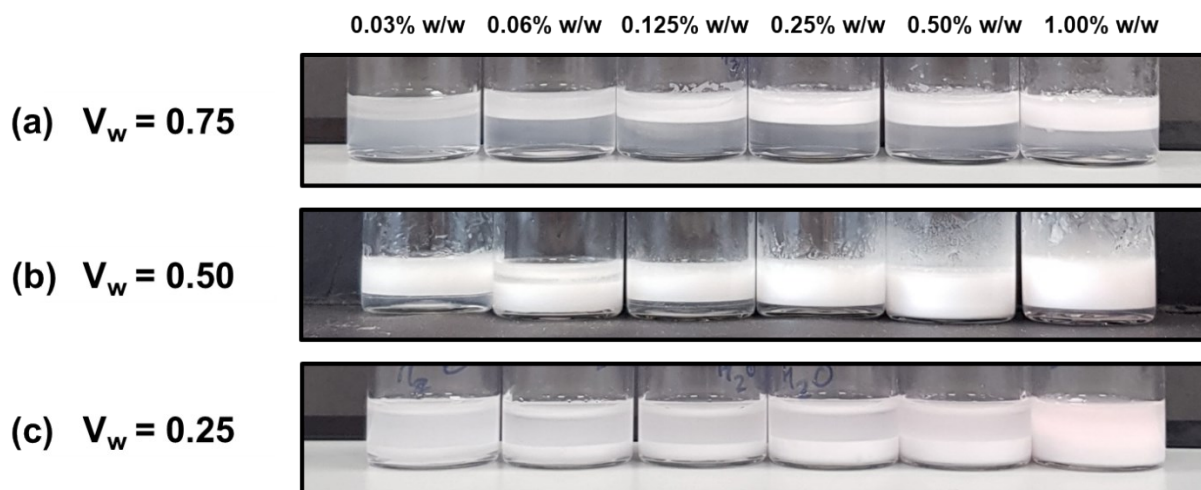

**Figure S6.** Digital photographs recorded for a series of Pickering emulsions prepared at 20 °C *via* high-shear homogenization at 13 500 rpm for 2 min using 0.03 to 1.00% w/w PSMA<sub>9</sub>-PHPMA<sub>50</sub> spheres at water volume fractions ( $V_w$ ) of (a) 0.75, (b) 0.50 or (c) 0.25.

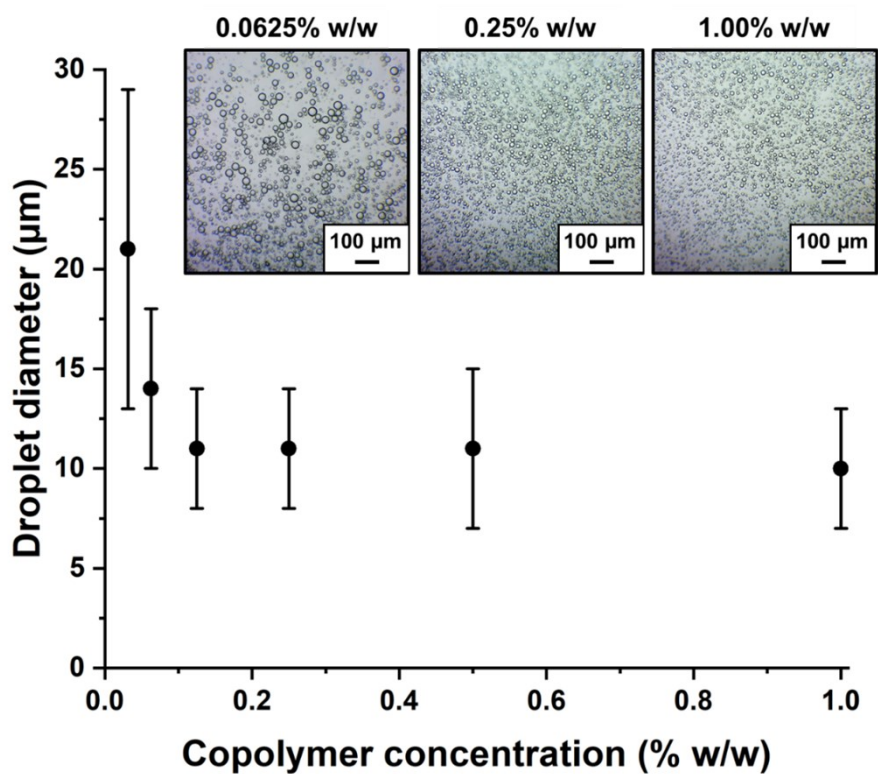

**Figure S7.** Variation in number-average droplet diameter (estimated from optical microscopy images by analyzing at least 100 droplets in each case) with copolymer concentration obtained for water-in-oil Pickering emulsions produced *via* high-shear homogenization (13 500 rpm for 2 min at 20 °C) of PSMA<sub>9</sub>-PHPMA<sub>50</sub> diblock copolymer spheres in mineral oil at a constant water volume fraction of 0.25. Inset: representative optical microscopy images recorded for aqueous droplets prepared using copolymer concentrations of 0.0625, 0.25 or 1.00% w/w, respectively.

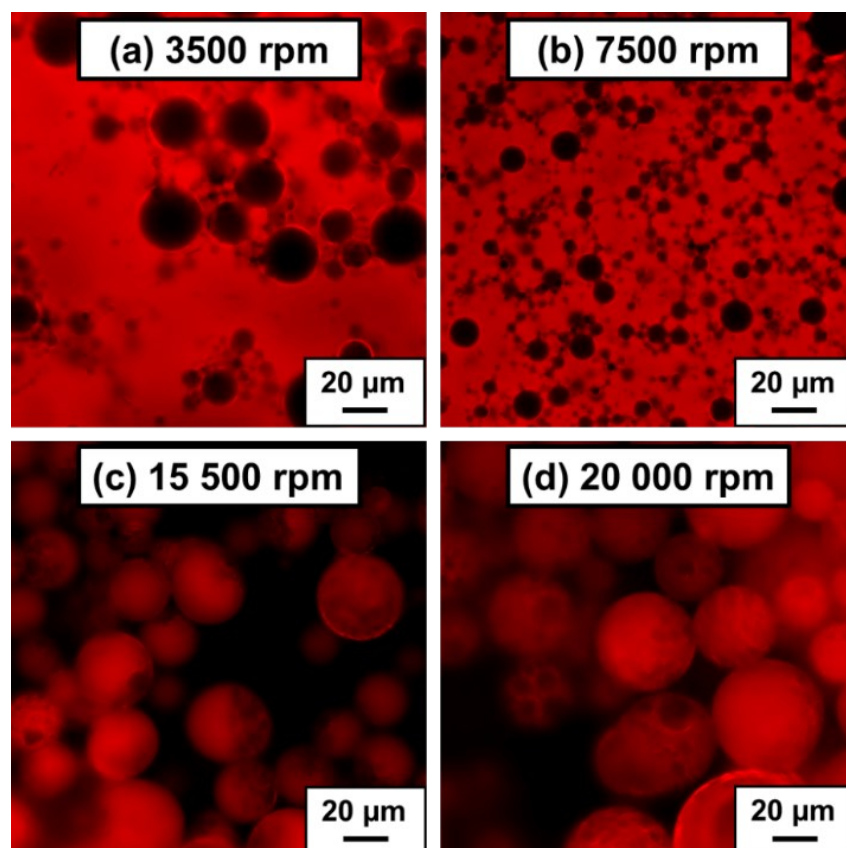

**Figure S8.** Fluorescence microscopy images recorded for the emulsions formed *via* high-shear homogenization at the stated stirring rate using 1.00% w/w PSMA<sub>9</sub>-PHPMA<sub>50</sub> diblock copolymer spheres in mineral oil and a constant water volume fraction of 0.50. Lower stirring rates (either 3 500 or 7 500 rpm) lead to the formation water-in-oil emulsions, whereas higher stirring rates (15 500 or 20 000 rpm) generate water-in-oil-in-water double emulsions.