

Electronic Supplementary Information:

**Rapid, Energy-Efficient and Pseudomorphic Microwave-Induced-Metal-Plasma
(MIMP) Synthesis of Mg₂Si and Mg₂Ge**

Zhen Fan,^a Hsi-Nien Ho,^b Robert Szczęśny,^c Wei-Ren Liu,^b and Duncan H Gregory.*^a

a. WestCHEM, School of Chemistry, Joseph Black Building, University of Glasgow,
Glasgow, G12 8QQ, United Kingdom.

b. Department of Chemical Engineering, Chung Yuan Christian University, R&D Center for
Membrane Technology, Research Center for Circular Economy, 32023, No. 200, Chun Pei
Rd., Chung Li District, Taoyuan City 32023, Taiwan.

c. Faculty of Chemistry, Nicolaus Copernicus University in Toruń, ul. Gagarina 7, 87-100
Toruń, Poland.

* Corresponding Author. Email: Duncan.Gregory@glasgow.ac.uk Tel: +44-141-330-8128.

1. Supplementary SEM/EDS and SAED Results for Mg₂Si

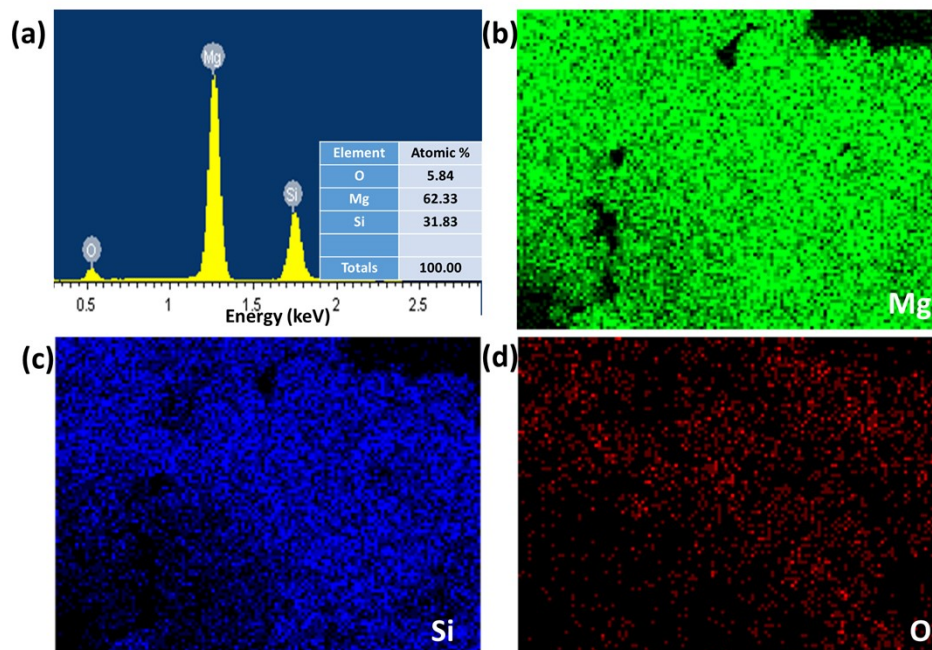


Figure S1. (a) The representative EDX spectrum corresponding to the SEM image in Figure 2d; and the corresponding (b-d) Elemental mappings of Mg, Si and O, respectively.

Table S1. Indexed lattice planes from the SAED patterns shown in Figure 1h.

Diffraction No.	Indexed Diffraction Distance / nm	Lattice Plane – Mg ₂ Si
1	0.230	(220)
2	0.190	(311)
3	0.150	(331)
4	0.120	(511)
5	0.106	(531), (600)
6	0.094	(533), (622)

2. Structure of the Nanoporous Ge Reactant Powders

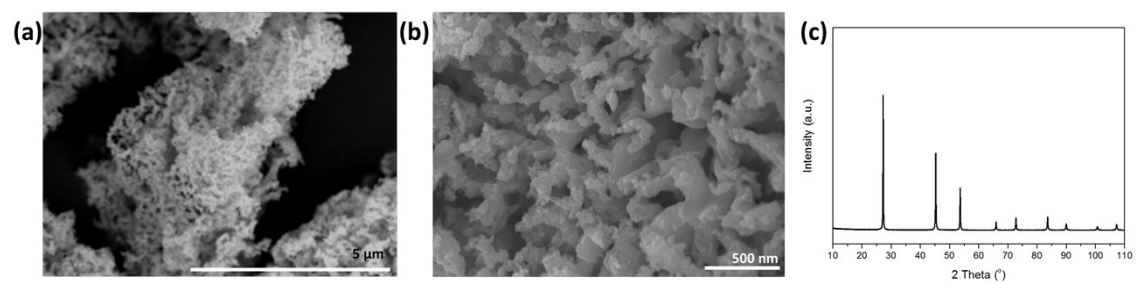


Figure S2. (a, b) SEM images and (c) PXRD patterns of the nanoporous Ge reactant powders.

3. Mg₂Ge synthesized from Mg and Ge, irradiated for 30 s.

Table S2. Crystallographic data obtained from the Rietveld refinement of the MIMP-synthesised product of Mg₂Ge with an irradiation time of 30 s (see also Figure 3a).

Chemical Formula	Mg ₂ Ge	Mg	Ge
Crystal System	Cubic	Hexagonal	Cubic
Space Group	<i>Fm-3m</i> (225)	<i>P6₃/mmc</i> (194)	<i>Fd-3m</i> (227)
Lattice Parameter / Å	6.3935(2)	3.2124(5) 5.2136(17)	5.6568 ^a
Cell Volume / Å ³	261.349(22)	46.593(14)	181.014 ^a
Formula Weight / g mol ⁻¹	484.800	48.610	580.720
Formula Units, <i>Z</i>	4	2	8
Calculated Density / g cm ⁻³	3.080	1.732	5.327
Phase Fraction / wt. %	94.3(3)	4.1(3)	1.5(1)
No. of Variables		19	
No. of Observations		2090	
<i>wRp</i>		0.2646	
<i>Rp</i>		0.1788	
χ^2		1.960	

^a. Not refined.

Table S3. Atomic parameters for MIMP-synthesised Mg₂Ge (irradiated for 30 s).

Atom	Site	<i>x</i>	<i>y</i>	<i>z</i>	100 × <i>U</i> _{iso} / Å ²	SOF ^a
Mg	8 <i>c</i>	0.25	0.25	0.25	2.54(18)	1
Ge	4 <i>a</i>	0	0	0	2.24(12)	1

^a. Not refined.

4. MIMP-synthesised Mg_2Ge from Commercial Bulk Ge Powders

In order to investigate between the premise that the reaction between Mg and nanoporous Ge was pseudomorphic, a supplementary MIMP synthesis was conducted. Commercial Ge powders (Trace metal basis, 99.999%, Acros Organics) were initially ground manually using a mortar and pestle. Mg powder (35 mg) and as-ground Ge powder (45 mg) were mixed thoroughly. The MW synthesis was performed with an incident power of 200 W for an irradiation time of 90 s under a static vacuum of $P < 10^{-6}$ mbar. The Rietveld refinement results (Figure S3a; Table S4) confirmed the *antifluorite* structure of Mg_2Ge with a lattice parameter of $a = 6.3894(4)$ Å. The refined phase fraction of the main phase was 95.9(4) wt.%, with the presence of small amounts of MgO (3.2(2) wt.%) and Ge (0.9(6) wt.%) impurity phases indicated. In contrast to the Mg_2Ge sample synthesised from nanoporous Ge starting material (Figures 4a,b), the STEM image in Figure S3b showed that the Mg_2Ge produced from commercial Ge was composed of dense bulk particles and was not porous.

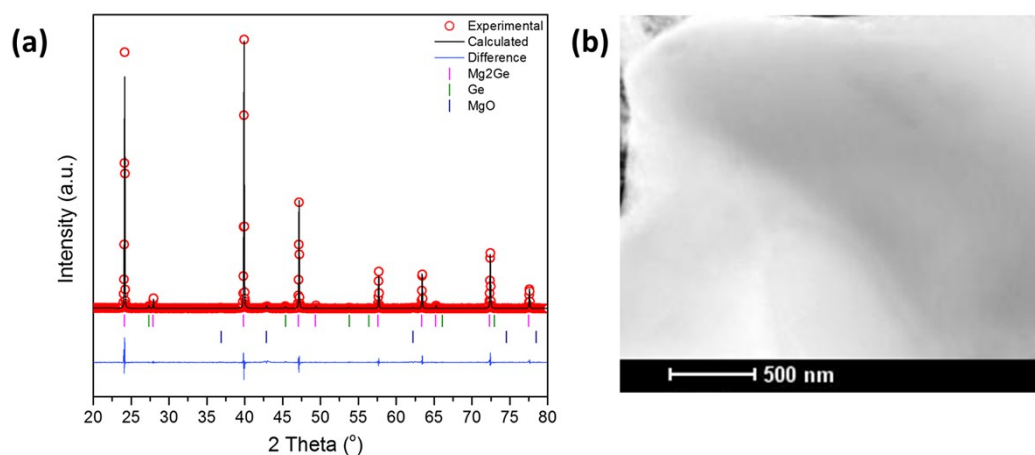


Figure S3. (a) Profile plot of the Rietveld refinement against PXRD data, and (b) a STEM image of the Mg_2Ge product as obtained from the MW synthesis experiment using a commercial Ge starting material, illustrating the relatively large particle size obtained.

Table S4. Crystallographic data obtained from the Rietveld refinement of the MIMP-synthesised Mg₂Ge synthesised from commercial Ge powder (see also Figure S3a).

Chemical Formula	Mg₂Ge	MgO	Ge
Crystal System	Cubic	Cubic	Cubic
Space Group	<i>Fm-3m</i> (225)	<i>Fm-3m</i> (225)	<i>Fd-3m</i> (227)
Lattice Parameter / Å	6.3894(4)	4.2170 ^a	5.6568 ^a
Cell volume / Å ³	260.85(5)	74.991 ^a	181.014 ^a
Formula Weight / g mol ⁻¹	484.800	161.216	580.720
Formula Units, <i>Z</i>	4	4	8
Calculated Density / g cm ⁻³	3.086	3.570	5.327
Phase Fraction / wt.%	95.9(4)	3.2(2)	0.9(6)
No. of Variables		27	
No. of Observations		2093	
<i>wRp</i>		0.2071	
<i>Rp</i>		0.1397	
χ^2		0.2199	

^a. Not refined.

Table S5. Atomic parameters for MIMP-synthesised Mg₂Ge from commercial Ge powder (see also Figure S3a).

Atom	Site	<i>x</i>	<i>y</i>	<i>z</i>	100 × <i>U</i>_{iso} / Å²	SOF ^a
Mg	8 <i>c</i>	0.25	0.25	0.25	2.77(14)	1
Ge	4 <i>a</i>	0	0	0	2.26(9)	1

^a. Not refined.