


## Supplementary Information

### Synthesis and crystal structures of lanthanide 4-benzyloxy benzoates: Influence of electron-withdrawing and electron-donating groups on luminescent properties


Sarika Sivakumar,<sup>a</sup> M. L. P. Reddy,\*<sup>a</sup> Alan H. Cowley<sup>b</sup> and Kalyan V. Vasudevan<sup>b</sup>

<sup>a</sup>*Chemical Sciences and Technology Division, National Institute for Interdisciplinary  
Science & Technology (NIIST), Thiruvananthapuram-695 019, India*


<sup>b</sup>*Department of Chemistry and Biochemistry, The University of Texas at Austin, 1  
University Station A5300, Austin, Texas 78712*

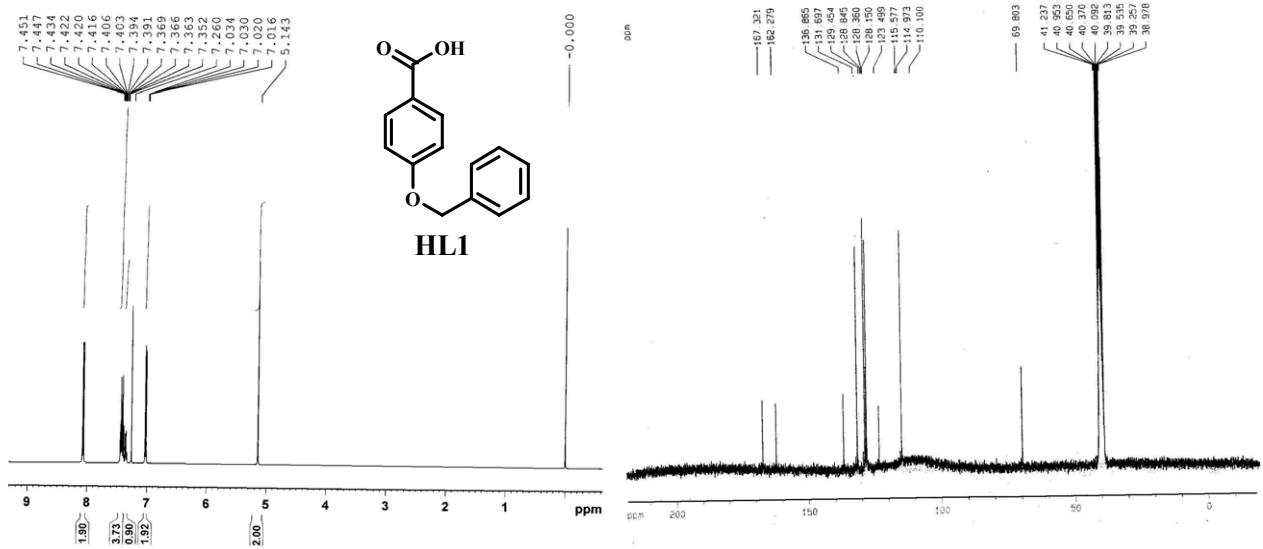


**Fig. S1** <sup>1</sup>H NMR spectrum of HL1 in CDCl<sub>3</sub> and <sup>13</sup>C NMR in DMSO-d<sub>6</sub> solutions.

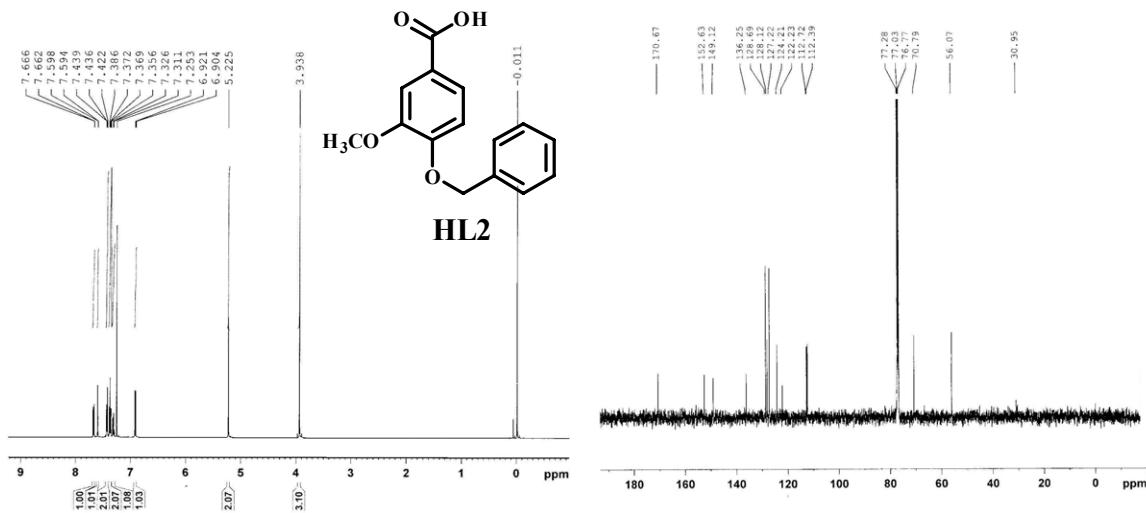


**Fig. S2** <sup>1</sup>H and <sup>13</sup>C NMR spectra of HL2 in CDCl<sub>3</sub> solution.

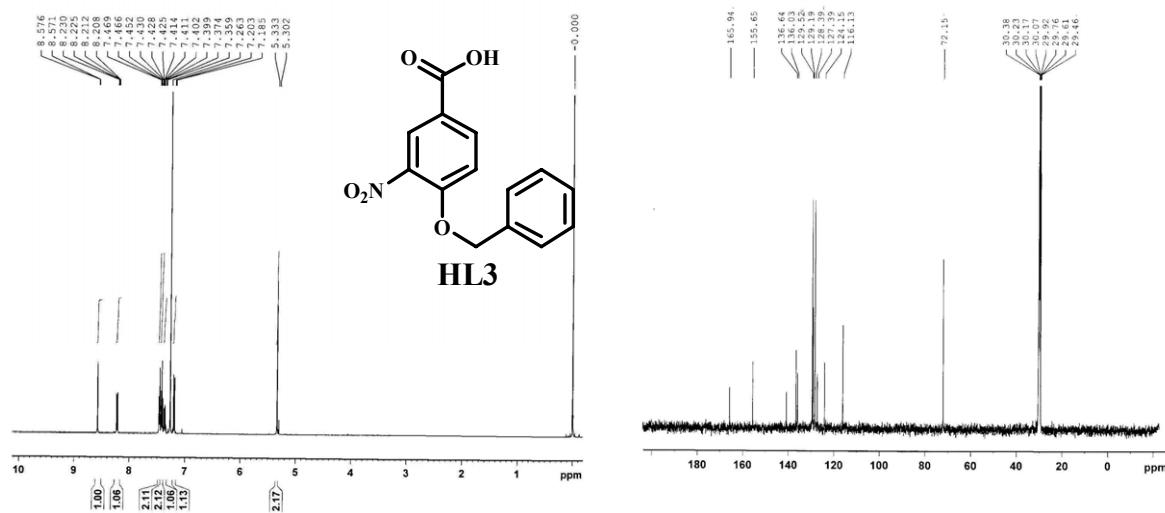


**Fig. S3**  $^1\text{H}$  NMR spectrum of HL3 in  $\text{CDCl}_3$  solution and  $^{13}\text{C}$  NMR in acetone- $\text{d}_6$  solution.

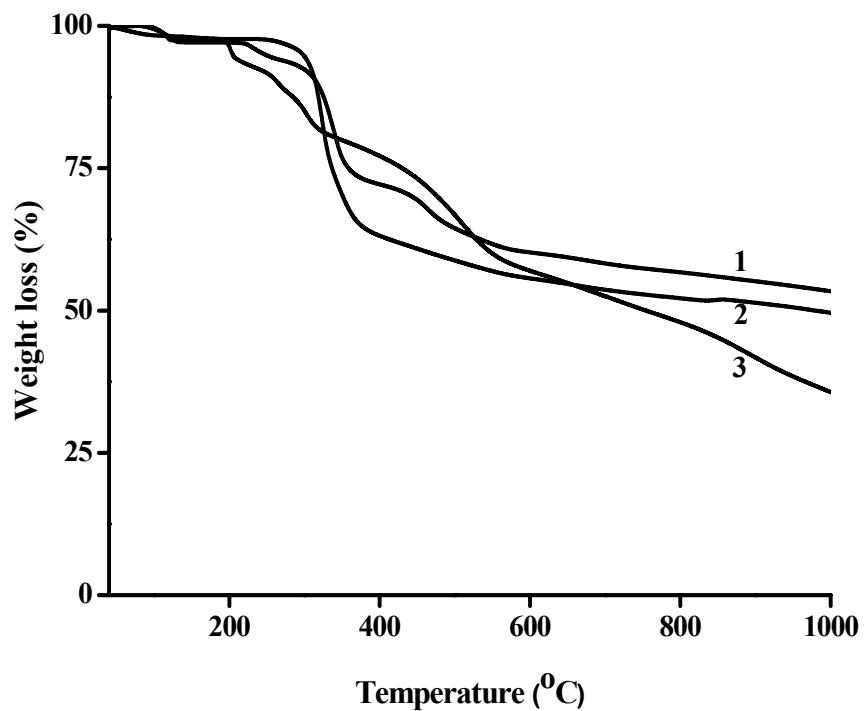


**Fig. S4** Thermogravimetric plot for complexes 1-3.

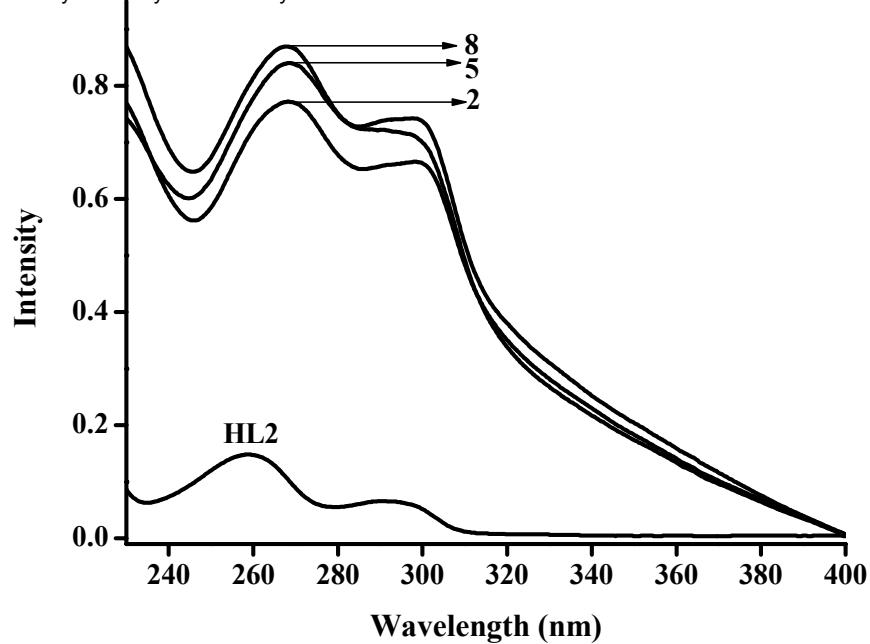


**Fig. S5** UV-visible absorption spectra of 3-methoxy-4-benzyloxy benzoic acid and complexes **2**, **5** and **8** in  $\text{CH}_3\text{CN}$  solution ( $2 \times 10^{-5}$  M).

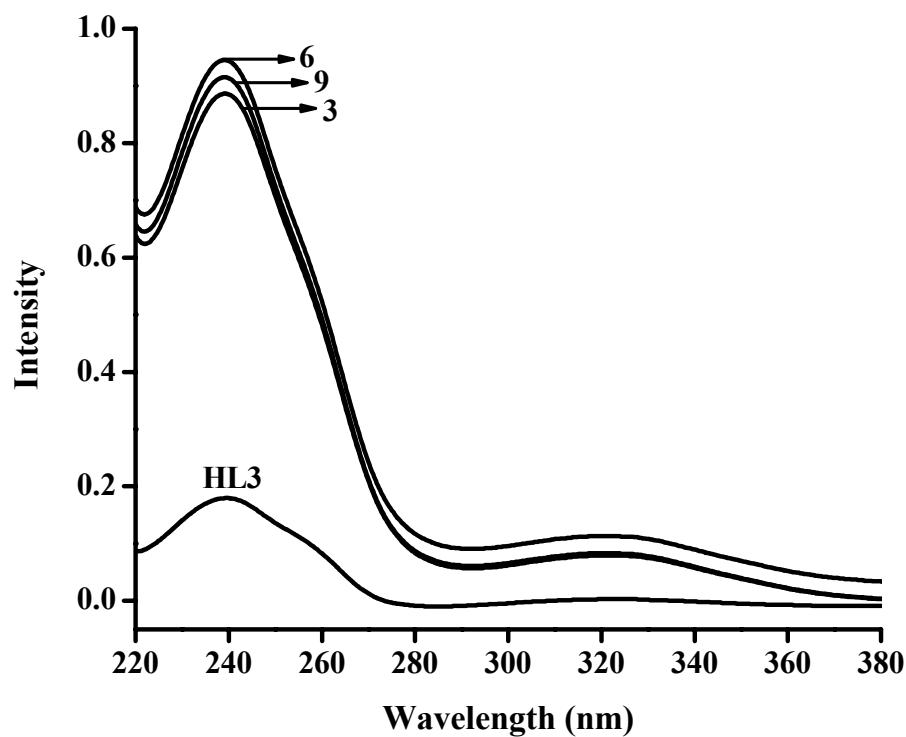


**Fig. S6** UV-visible absorption spectra of 4-(benzyloxy)-3-nitro benzoic acid and complexes **3**, **6** and **9** in  $\text{CH}_3\text{CN}$  solution ( $2 \times 10^{-5}$  M).

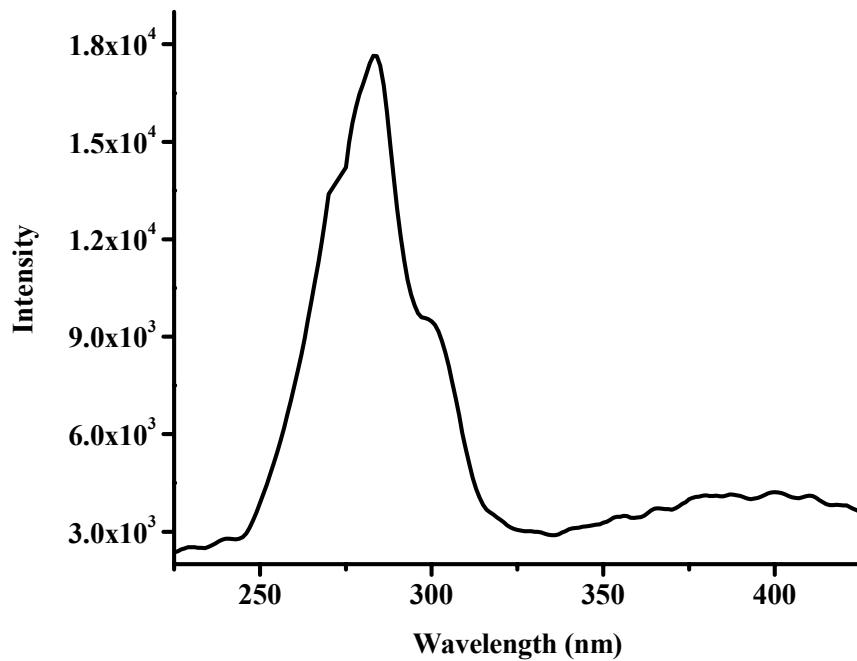


**Fig. S7** Room-temperature excitation spectrum for complex 3.

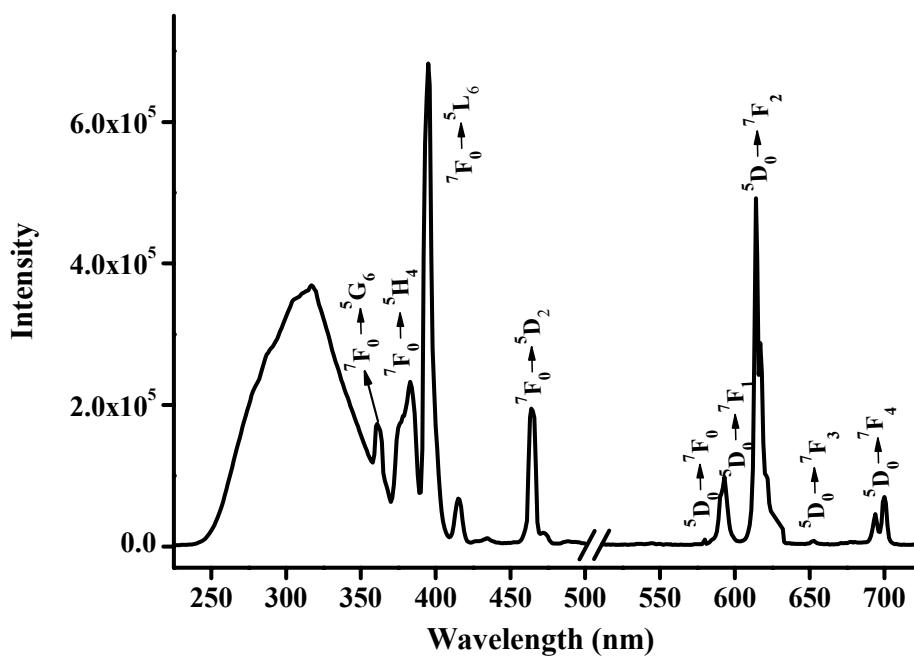


**Fig. S8** Room-temperature excitation and emission spectra for complex 4 ( $\lambda_{\text{ex}} = 314$  nm) with emission monitored at approximately 612 nm.

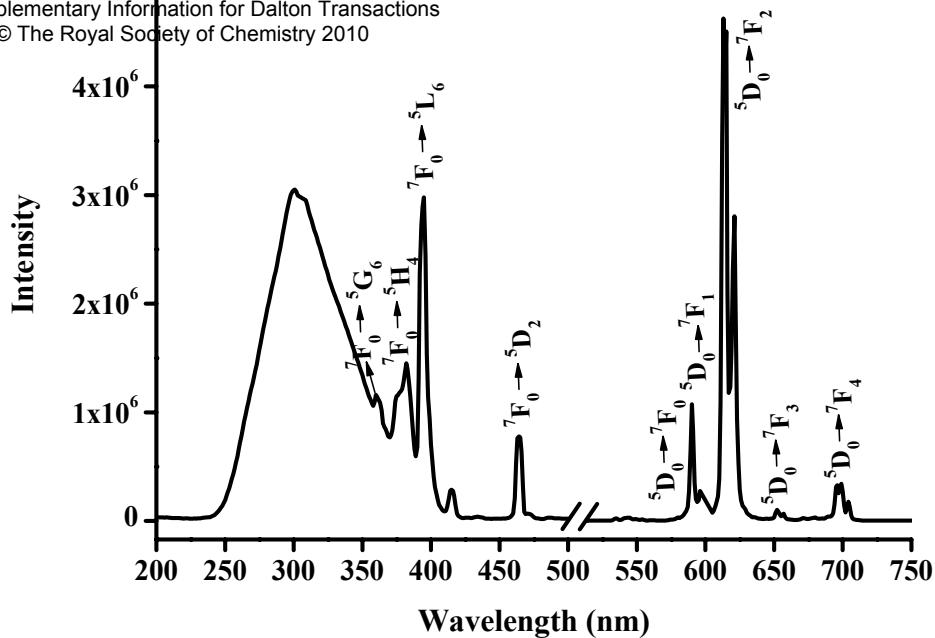


**Fig. S9** Room-temperature excitation and emission spectra for complex 5 ( $\lambda_{\text{ex}} = 300\text{nm}$ ) with emission monitored at approximately 612 nm.

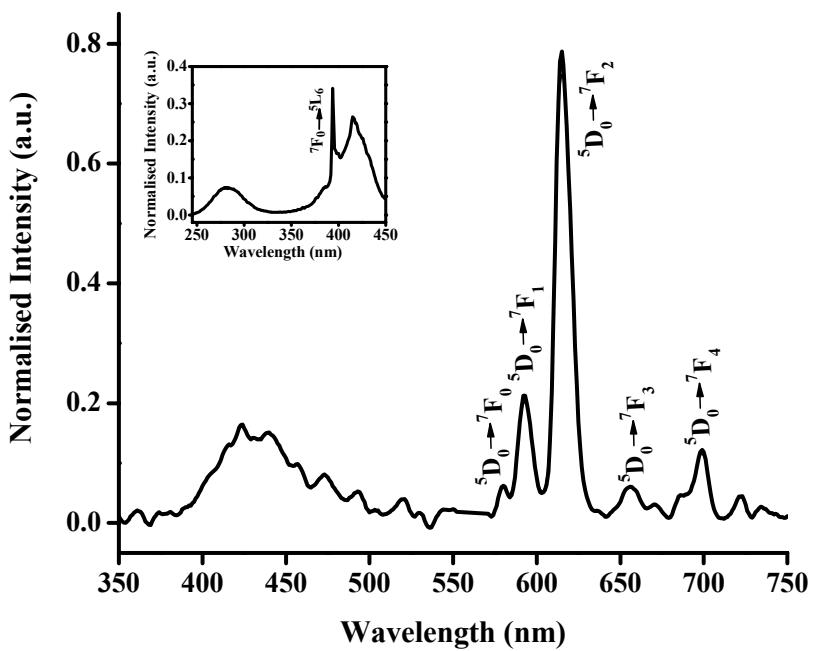

**Fig. S10** Room-temperature emission spectrum for complex 6 ( $\lambda_{\text{ex}} = 280\text{ nm}$ ). (Inset shows the excitation spectrum of the complex 6 with emission monitored at approximately 612 nm).

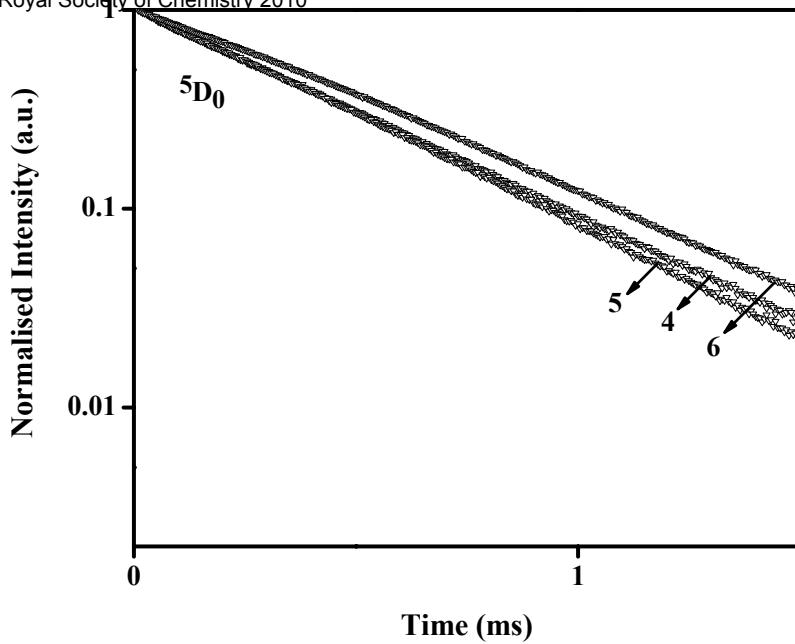

**Fig. S11** Luminescence decay profile of complexes **4**, **5** and **6** excited at 314, 300 and 280 nm, respectively and monitored at approximately 612 nm.

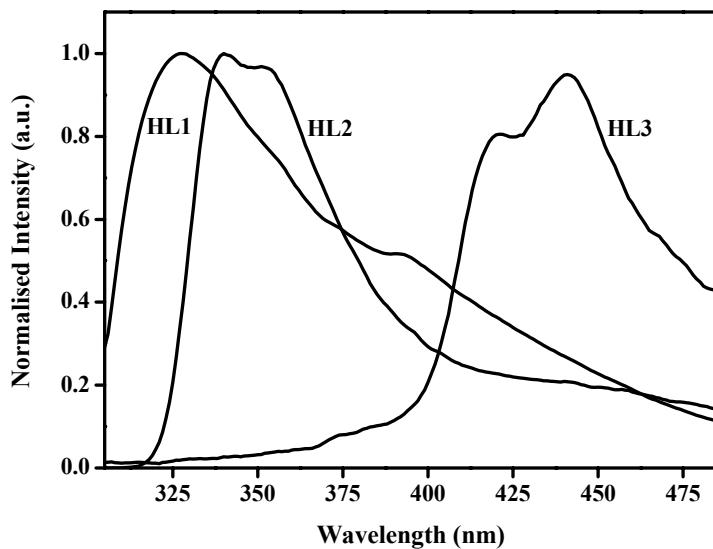

**Fig. S12** Room-temperature emission spectra of ligands HL1-HL3.

**Table S1** Infrared vibrational frequencies for the carboxylate functionalities of ligands HL1-HL3 and complexes **1-9**.

	$\nu_{as}(C=O) \text{ cm}^{-1}$	$\nu_s(C=O) \text{ cm}^{-1}$	$\Delta\nu_{(C=O)} \text{ cm}^{-1}$
HL1	1686	1454	
HL2	1678	1454	
HL3	1689	1454	
<b>1</b>	1586, 1610	1380, 1439	230,147
<b>2</b>	1597, 1627	1395, 1423	232,174
<b>3</b>	1588, 1614	1350, 1424	264,164
<b>4</b>	1586, 1608	1380, 1432	228,154
<b>5</b>	1599, 1627	1396, 1423	231,176
<b>6</b>	1584, 1626	1338,1423	288,161
<b>7</b>	1586, 1610	1380, 1435	230,151
<b>8</b>	1599, 1628	1396, 1423	232,176
<b>9</b>	1589, 1615	1350, 1424	265,165

**Table S2** Values for the absorption maxima and molar absorption coefficients for ligands HL1-HL3 and compounds **1-9** in acetonitrile solution ( $c = 2 \times 10^{-5}$  M).

Compound	$\lambda_{\max} \pi-\pi^*/\text{ILCT}$ (nm)	$\epsilon$ (mol <sup>-1</sup> liter cm <sup>-1</sup> )
HL1	253	$8.69 \times 10^3$
HL2	260, 295	$7.39 \times 10^3$
HL3	238, 318	$9.20 \times 10^3$
<b>1</b>	254	$4.58 \times 10^4$
<b>2</b>	267, 299	$3.86 \times 10^4$
<b>3</b>	239, 321	$4.46 \times 10^4$
<b>4</b>	255	$4.78 \times 10^4$
<b>5</b>	268, 299	$4.21 \times 10^4$
<b>6</b>	239, 321	$4.75 \times 10^4$
<b>7</b>	256	$4.84 \times 10^4$
<b>8</b>	267, 299	$4.35 \times 10^4$
<b>9</b>	239, 321	$4.60 \times 10^4$

**Procedures for calculating radiative ( $A_{\text{RAD}}$ ) and nonradiative ( $A_{\text{NR}}$ ) decay rates, radiative lifetimes ( $\tau_{\text{RAD}}$ ), intrinsic quantum yields ( $\Phi_{Ln}$ ), energy transfer efficiencies ( $\Phi_{\text{sen}}$ ), and overall quantum yields ( $\Phi_{\text{overall}}$ ) for Eu<sup>3+</sup> and Tb<sup>3+</sup> complexes 1-6.**

The overall quantum yield ( $\Phi_{\text{overall}}$ ) for a Ln<sup>3+</sup> coordination compound is the product of the intrinsic quantum yield  $\Phi_{Ln}$  (measured upon f-f excitation), which reflects the extent of nonradiative deactivation processes that take place within the luminescent edifice, and the sensitization efficiency of the ligand ( $\Phi_{\text{sen}}$ ), which reflects the efficacy with which the latter transfers its excitation energy onto the metal ion.<sup>1</sup>

$$\Phi_{\text{overall}} = \Phi_{\text{sen}} \Phi_{Ln} \quad (1)$$

Here,  $\Phi_{sen}$  represents the efficiency of energy transfer from the ligand to the  $\text{Ln}^{3+}$  ion and  $\Phi_{Ln}$  represents the intrinsic quantum yield of the  $\text{Ln}^{3+}$  ion, which can be calculated as shown in Equation (2).

$$\phi_{Ln} = \left( \frac{A_{RAD}}{A_{RAD} + A_{NR}} \right) = \frac{\tau_{obs}}{\tau_{RAD}} \quad (2)$$

For the  $\text{Eu}^{3+}$  complexes, the radiative lifetime ( $\tau_{RAD}$ ) can be calculated using Equation (3),<sup>2</sup> assuming that the energy of the  $^5\text{D}_0 \rightarrow ^7\text{F}_1$  transition (MD) and its oscillator strength are constant

$$A_{RAD} = \frac{1}{\tau_{RAD}} = A_{MD,0} n^3 \left( \frac{I_{TOT}}{I_{MD}} \right) \quad (3)$$

where,  $A_{MD,0}$  ( $14.65 \text{ s}^{-1}$ ) is the spontaneous emission probability of the  $^5\text{D}_0 \rightarrow ^7\text{F}_1$  transition in vacuo,<sup>2</sup>  $I_{TOT}/I_{MD}$  is the ratio of the total area of the corrected  $\text{Eu}^{3+}$  emission spectrum to the area of the  $^5\text{D}_0 \rightarrow ^7\text{F}_1$  band and  $n$  is the refractive index of the medium. An average index of refraction equal to 1.5 was employed.<sup>3</sup> The intrinsic quantum yield of  $\text{Tb}^{3+}$  ( $\Phi_{Tb}$ ) can be estimated by means of Equation (4) using the assumption that the decay process at 77 K in deuterated solvents is purely radiative.<sup>4</sup>

$$\phi_{Tb} = \frac{\tau_{obs(298K)}}{\tau_{RAD(77K)}} \quad (4)$$

The radiative lifetime ( $\tau_{RAD}$ ), intrinsic quantum yields ( $\Phi_{Ln}$ ), and sensitization efficiencies ( $\Phi_{sen}$ ) of the ligands for  $\text{Ln}^{3+}$  complexes **1-6** were calculated and are presented in Table 3. The quantum yields were measured for complexes **1-6** by employing the technique for powdered samples described by Bril *et al.*<sup>5</sup>

## References

- 1 (a) M. Xiao and P. R. Selvin, *J. Am. Chem. Soc.*, 2001, **123**, 7067; (b) S. Comby, D. Imbert, C. Anne-Sophie, J.-C.G. Bünzli, L. J. Charbonniere and R. F. Ziessel, *Inorg. Chem.*, 2004, **43**, 7369.

- 2 (a) S. Viswanathan and A. de Bettenacourt-Dias, *Inorg. Chem.*, 2006, **45**, 10138; (b) Y. H. Kim, N. S. Baek and H. K. Kim, *Chem. Phys. Chem.*, 2006, **7**, 213.
- 3 (a) G. F. de Sa, O. L. Malta, C. de Mello Donega, A. M. Simas, R. L. Longo, P. A. Santa-Cruz and E. F. da Silva Jr, *Coord. Chem. Rev.*, 2000, **196**, 165; (b) D. B. Ambili Raj, S. Biju and M. L. P. Reddy, *Inorg. Chem.*, 2008, **47**, 8091.
- 4 (a) N. Sabbatini, M. Guardigli and J.-M. Lehn, *Coord. Chem. Rev.*, 1993, **123**, 201; I. Nasso, S. Bedel, C. Galaup and C. Picard, *Eur. J. Inorg. Chem.*, 2008, **12**, 2064.
- 5 A. Bril., A. W De Jager- Veenis, *J. Electrochem. Soc.*, 1976, **123**, 396.