

Supplementary Information for

**A Dual Coaxial Nanocable Sulfur Composite for High-Rate  
Lithium-Sulfur Batteries**

Zhen Li<sup>a</sup>, Lixia Yuan<sup>\*a</sup>, Ziqi Yi<sup>a</sup>, Yang Liu<sup>a</sup>, Ying Xin<sup>b</sup>, Zhaoliang Zhang<sup>b</sup>, Yunhui Huang<sup>\*a</sup>

<sup>a</sup> Key Laboratory for Advanced Battery Materials and System (MOE), School of Materials Science and Engineering, Huazhong University of Science and Technology, 1037 Luoyu Road, Wuhan, Hubei 430074, China

<sup>b</sup> Shandong Provincial Key Laboratory of Fluorine Chemistry and Chemical Materials, School of Chemistry and Chemical Engineering, University of Jinan, 106 Jiwei Road, Jinan, Shandong 250022, China

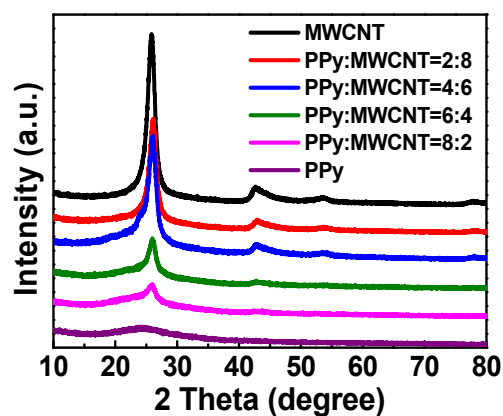


Fig. S1 XRD patterns of pure MWCNT, PPy : MWCNT = 2 : 8, PPy : MWCNT = 4 : 6, PPy : MWCNT = 6 : 4, PPy : MWCNT = 8 : 2 and pure PPy.

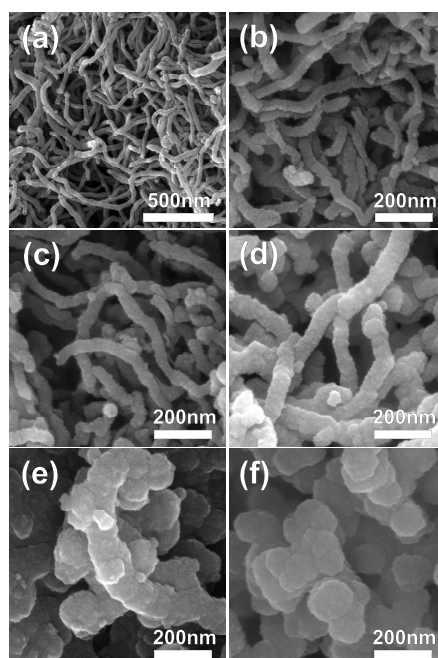


Fig. S2 SEM images for (a) pure MWCNT, (b) PPy : MWCNT = 2 : 8, (c) PPy : MWCNT = 4 : 6, (d) PPy : MWCNT = 6 : 4, (e) PPy : MWCNT = 8 : 2, and (f) pure PPy.

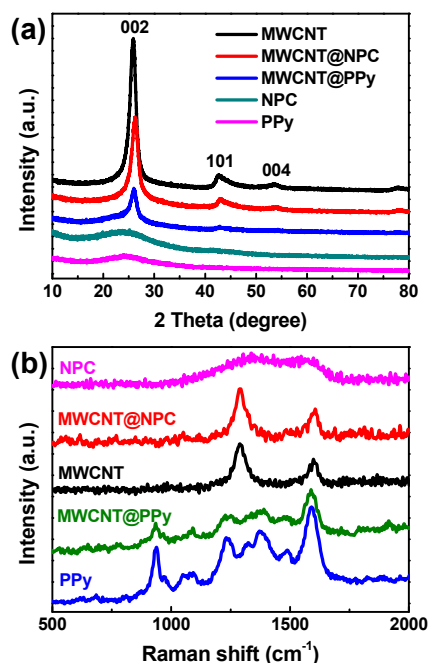


Fig. S3. (a) XRD patterns and (b) Raman patterns for MWCNT, PPy, MWCNT@PPy and MWCNT@NPC.

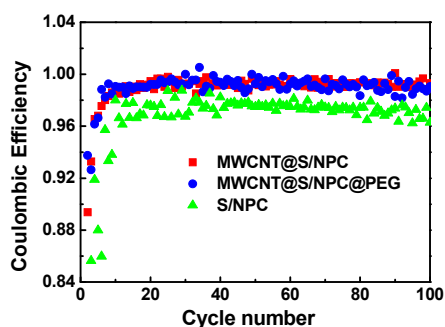


Fig. S4 The Coulombic efficiencies of S/NPC, MWCNT@S/NPC, MWCNT@S/NPC@PEG cycled at 1 C in the voltage range of 2.8 – 1.8 V vs Li<sup>+</sup>/Li.

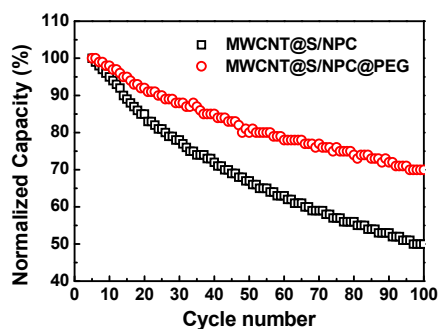


Fig. S5 Normalized discharge capacity of MWCNT@S/NPC and MWCNT@S/NPC@PEG.

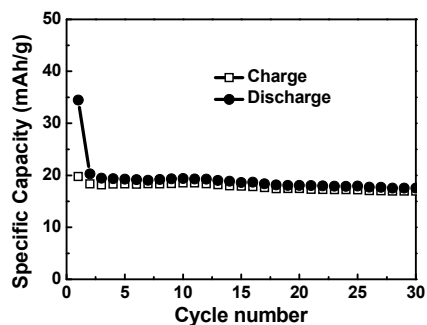


Fig. S6 The capacity of pure MWCNT@NPC at 168 mA  $g^{-1}$  in the range of 2.8 – 1.8 V vs  $Li^+/Li$ .

Fig. S6 shows the capacity over cycling for pure MWCNT@NPC carbon in the range of 2.8 – 1.8 V vs  $Li^+/Li$ . The capacity of carbon was only 20 mAh  $g^{-1}$ , which was only ~2% of that of sulfur. So, it can be concluded that the carbon matrix has almost no contribution to the sulfur/carbon composites.

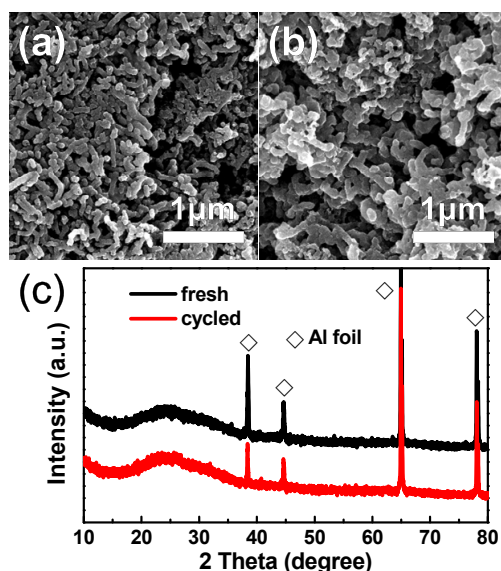


Fig. S7 SEM images of fresh (a) and cycled (b) electrode films of MWCNT@S/NPC@PEG; (c) XRD patterns comparison of fresh and cycled electrode films of MWCNT@S/NPC@PEG.

The SEM images in Fig. S7a, b prove the structural stability of the MWCNT@S/NPC@PEG composite. Moreover, the cross-linked nanotube provides excellent conducting webs for both electrons and lithium ions. The XRD patterns in Fig. S4c indicate the phase stability of the MWCNT@S/NPC@PEG composite during cycle.

Table S1 The comparison of this work with some other similar composites.

| Composites       | Sulfur content (wt%) | Specific capacity (mAh g <sup>-1</sup> ) |            |            |     |     |     | Cycle performance (mAh g <sup>-1</sup> )       | Ref.     |
|------------------|----------------------|------------------------------------------|------------|------------|-----|-----|-----|------------------------------------------------|----------|
|                  |                      | 0.5C                                     | 1C         | 2C         | 3C  | 4C  | 5C  |                                                |          |
| MWCNT@S/NPC@PEG  | 54                   | 1000                                     | 790        | 680        | 580 | 500 | 450 | 100 <sup>th</sup> , 527@1C                     | Our work |
| MWCNT@PPy/S      | 52.6                 | 492                                      | \          | \          | \   | \   | \   | 40 <sup>th</sup> , 961@0.2C                    | [1]      |
| MWCNT@S@PPy      | 60.3                 | ~300                                     | ~120       | \          | \   | \   | \   | 40 <sup>th</sup> , 600@0.03C                   | [2]      |
| MWCNT@S@PPy      | 68.3                 | 1060 (0.3C)                              | 860 (0.9C) | 665 (1.2C) | \   | \   | \   | 200 <sup>th</sup> , 560@0.9C                   | [3]      |
| MWCNT@PPy/S      | 70                   | \                                        | \          | \          | \   | \   | \   | 100 <sup>th</sup> , 726@0.1m Acm <sup>-2</sup> | [4]      |
| Nanowire-PPy/S   | 66.7                 | \                                        | \          | \          | \   | \   | \   | 20 <sup>th</sup> , 570@0.1m Acm <sup>-2</sup>  | [5]      |
| Nanowire-PPy/S   | 65                   | \                                        | \          | \          | \   | \   | \   | 40 <sup>th</sup> , 500@0.06C                   | [6]      |
| S@PPy core-shell | 63.3                 | \                                        | 450        | \          | \   | \   | \   | 50 <sup>th</sup> , 634@0.2C                    | [7]      |
| S/NPC            | 24                   | \                                        | \          | \          | \   | \   | \   | 20 <sup>th</sup> , 573@0.05C                   | [8]      |
| MWCNT@MesoC/S    | 60                   | ~900 (0.6)                               | 720 (1.6C) | \          | \   | \   | \   | 50 <sup>th</sup> , 640@0.06C                   | [9]      |
| MWCNT@S          | 57                   | 800 (0.6C)                               | 600        | \          | \   | \   | \   | 100 <sup>th</sup> , 1000@0.2C                  | [10]     |

## References:

- [1] Zhang, Y.; Zhao, Y.; Doan, T. N. L.; Konarov, A.; Gosselink, D.; Soboleski, H. G.; Chen, P., *Solid State Ionics* **2013**, *238*, 30-35.
- [2] Wang, J.; Lu, L.; Shi, D.; Tandiono, R.; Wang, Z.; Konstantinov, K.; Liu, H., *ChemPlusChem* **2013**, *78* (4), 318-324.
- [3] Wang, C.; Wan, W.; Chen, J. T.; Zhou, H. H.; Zhang, X. X.; Yuan, L. X.; Huang, Y. H., *Journal of Materials Chemistry A* **2013**, *1* (5), 1716-1723.
- [4] Liang, X.; Wen, Z.; Liu, Y.; Zhang, H.; Jin, J.; Wu, M.; Wu, X., *Journal of Power Sources* **2012**, *206*, 409-413.
- [5] Sun, M. M.; Zhang, S. C.; Jiang, T.; Zhang, L.; Yu, J. H., *Electrochemistry Communications* **2008**, *10* (12), 1819-1822.
- [6] Zhang, Y.; Bakenov, Z.; Zhao, Y.; Konarov, A.; Doan, T. N. L.; Malik, M.; Paron, T.; Chen, P., *Journal of Power Sources* **2012**, *208*, 1-8.
- [7] Fu, Y. Z.; Manthiram, A., *Journal of Physical Chemistry C* **2012**, *116* (16), 8910-8915.
- [8] Sun, X.-G.; Wang, X.; Mayes, R. T.; Dai, S., *ChemSusChem* **2012**, *5* (10), 2079-2085.
- [9] Wang, D.; Yu, Y.; Zhou, W.; Chen, H.; DiSalvo, F. J.; Muller, D. A.; Abruna, H., *Physical Chemistry Chemical Physics* **2013**, *15* (23), 9051-9057.
- [10] Chen, J. J.; Zhang, Q.; Shi, Y. N.; Qin, L. L.; Cao, Y.; Zheng, M. S.; Dong, Q. F., *Physical Chemistry Chemical Physics* **2012**, *14* (16), 5376-5382.